

Hydrogenation of sunflower oil over M/SiO₂ and M/Al₂O₃ (M=Ni,Pd,Pt,Co,Cu) catalysts

Emilio A. Cepeda, Unai Iriarte-Velasco, Beatriz Calvo and Irene Sierra*

Department of Chemical Engineering, Faculty of Pharmacy, University of the Basque Country (UPV/EHU), Paseo de la Universidad, 7, 01006 Vitoria-Gasteiz, Spain.

*Corresponding author. Tel.: +34 945013290; Fax +34 945013014 E-mail: irene.sierra@ehu.eus

Abstract

This work is aimed at evaluating the performance of several catalysts in the partial hydrogenation of sunflower oil. The catalysts are composed of noble (Pd and Pt) and base metals (Ni, Co and Cu), supported on both silica and alumina. The following order can be proposed for the effect of the metal on the hydrogenation activity: Pd > Pt > Ni > Co > Cu. At a target iodine value of 70 (a typical value for oleomargarine), the production of *trans* isomers is minimum for supported nickel catalysts (25.7-32.4 %, depending on the operating conditions). Regarding the effect of the support, Al₂O₃ allows for more active catalysts based on noble metals (Pd and Pt) and Co, the effect being much more pronounced for Pt. Binary mixtures of catalysts have been studied, in order to strike a balance between catalyst activity and product distribution. The results evidence that Pd/Al₂O₃-Co/SiO₂ mixture has a good balance between activity and selectivity, and leads to a very low production of *trans* isomers (11.8 %) and a moderate amount of saturated stearic acid (13.5 %). Consequently, the utilization of cobalt-based catalysts (or the addition of cobalt to other metallic catalysts) could be considered a promising alternative for the hydrogenation of edible oil.

KEYWORDS: Vegetable oil, partial hydrogenation, Ni-Pd-Pt-Co-Cu, *trans* isomers, catalyst mixtures.

Introduction

The partial hydrogenation of vegetable oils is of great importance in the production of frying oils, shortenings, margarines, industrial oils and greases. Hydrogenation leads to a reduction of colour and odour and raises the melting point, resulting in a solid or semisolid product at room temperature. As a consequence of the hydrogenation process, the chemical stability of the product is effectively increased, which allows the product to be used as edible oil, as well as in industrial applications.

Although only *cis* isomers usually exist in untreated vegetable oils, during the hydrogenation process some double bonds are isomerised into the *trans* form. The excessive intake of *trans* fatty acids is associated with a higher risk of coronary heart disease. Dietary studies reveal a four to five-fold higher risk of *trans* fatty acids consumed, as compared to saturated fatty acids [1]. The European Union has recently considered the influence on health of *trans* isomers, and the European Commission is committed to submit a report on the presence of *trans* fats in foods, accompanied by a legislative frame if appropriate, by December 2014 [2].

In the hydrogenation process the composition and properties of the final product depend on various operating conditions, which affect mass and heat transfer, including catalyst concentration, agitation level, hydrogen pressure and temperature. Furthermore, the process is also sensitive to the architecture of the catalyst. Indeed, the mass transport limitations on hydrogen and unsaturated triglycerides to the active sites of the catalysts have a strong influence on both catalyst activity and selectivity. Thus, the isomerisation reactions which result in the production of *trans* isomers can be influenced by the type of metal, the structure of the support and the metal-support interaction.

Industrially, the partial hydrogenation of edible oil is carried out in semibatch reactors using supported nickel catalysts. These catalysts require temperatures around 150-180 °C and pressures between 0.1 and 0.6 MPa [3]. Nickel catalysts have several advantages, including high activity, low cost and ease of separation from processed oil. However, these catalysts produce a significant amount of *trans* and saturated fatty acids. In addition, traces of nickel remaining in the oil should be removed, due to toxicity and quality concerns.

Different metallic catalysts have been investigated as an alternative to nickel catalysts. Among them, noble metals have been extensively studied. Although the cost is an important drawback, their much higher activity and the possibility to be reused make noble metal catalysts a promising alternative. In this regard, palladium catalysts are more selective to *cis* isomers than nickel catalysts during the hydrogenation of polyunsaturated fatty acids [4]. Platinum has been found to be highly active and, in general, forms less *trans* isomers than nickel during hydrogenation [5]. Between both metals, it has been reported in the literature that the formation of *trans* isomers is lower for platinum catalysts, compared to palladium catalysts [4].

An alternative to noble metal-based catalysts is the use of formulations using less expensive base metals. Copper-based catalysts, although possess lower activity than Ni catalysts, have long been known for displaying no activity towards monoenes. These catalysts exhibit an excellent ability to enrich the oil in oleic acid, whereas the formation of saturated stearic acid is very low [6]. Nevertheless, one drawback of copper catalysts is that traces of metal promote the autoxidation of fats [7]. Consequently, traces of metal remaining in the oil should be removed.

Cobalt-containing catalysts are widely used in hydrogen transfer reactions, the Fischer-Tropsch reaction being the most common application, in which cobalt catalysts are used in industrial scale. A cobalt-based catalyst has recently been used in the hydrogenation of vegetable oil for the production of liquid bio-chemicals [8]. Nevertheless, cobalt-based catalysts have been scarcely used in the hydrogenation of edible oil. Cobalt has also the disadvantage of being a pro-oxidant of fats [9].

Several authors have proposed the utilization of a mixture of catalysts, with the aim of improving the activity and selectivity of the catalytic material. Moulton et al. [10] used mixtures of copper and nickel catalysts to hydrogenate soybean oil, and found a ratio that provides a higher selectivity than nickel and a higher activity than copper, used separately. Wright et al. [11] reported that mixtures of ruthenium and nickel increase the activity and minimize the formation of *trans* isomers. The same authors studied the addition of nickel to a palladium catalyst, in order to improve the selectivity toward *cis* isomers.

Although there are studies in the literature on the influence of the type of catalyst, there is no comprehensive study concerning the performance (activity, selectivity and production of *trans* isomers) of several metallic catalysts (including noble and base

metals) composed of Ni, Pd, Pt, Co and Cu, supported on silica and alumina, in the partial hydrogenation of sunflower oil. The specific objectives are: (i) the preparation and characterization of supported metallic catalysts; (ii) the investigation of their activity and selectivity towards monoenes and saturated stearic acid; (iii) the investigation of alternative strategies such as the use of mixtures of catalysts.

Materials and methods

Catalyst preparation

Two different types of supports were used: silica (Köstrosrob 1020) and γ -Al₂O₃ (Spheralite 511B, Procatalyse). The supports were crushed and sieved, in order to retain particles with a size of 17-80 μ m.

Nickel catalysts were prepared by deposition-precipitation [12]. This method is based on the heterogeneous precipitation of nickel, using 100 ml of an aqueous solution of nickel nitrate (0.14 M Ni(NO₃)₂·6H₂O, Fluka), 0.02 M nitric acid (Probus) and 0.42 M urea (Scharlau), slurried with silica or alumina (3 g). The slurry was shaken at 90 °C during 14 h in a rotary evaporator RE11 (Büchi). The precipitation was produced by the slow and homogeneous change in the pH from 4.6 to 5.5, induced by the thermal decomposition of urea. The precipitate was then cooled at room temperature, filtered, washed and dried (110 °C, 14 h).

Supported palladium catalysts were prepared by diffusional impregnation [13]. Silica and alumina were impregnated with an aqueous solution of PdCl₂ (0.28 M, pH = 2, Fluka). The solution of PdCl₂ was prepared by dissolving palladium metal in aqua regia. This solution was then evaporated to dryness, and the precipitate was dissolved in an HCl solution (Panreac). The solution and the support were in contact for 20 min, using an impregnation ratio of 3 ml/g_{support}. The solvent was then slowly removed by heating at 60 °C in vacuum, and the solid was dried (110 °C, 10 h) and calcined (300 °C, 4 h).

Platinum catalysts were prepared following the incipient wetness technique [14]. Silica and alumina supports were impregnated with an aqueous solution of H₂PtCl₆ (Sigma Aldrich) under constant agitation. The volume of solution used was equal to the pore volume of the support. The solution concentration was that required to obtain the prefixed metal concentration. The solids were then dried (120 °C, 1 h) and calcined (300 °C, 4 h).

Supported cobalt catalysts were prepared following the ammonia method used by Barbier et al. [15]. 25 g of $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ (Probus) was added to 150 ml of water at room temperature and under agitation, to prevent the oxidation of Co^{2+} . Afterwards, a solution of ammonia (30 wt%, Sigma Aldrich) was poured over the solution to produce the precipitation of $\text{Co}(\text{OH})_2$. The precipitate was dissolved by an excess of ammonia (20 ml), and 10 g of support (silica or alumina) was added to the solution. After the solution reached an equilibrium pH value near 12, the system was stirred for 72 h. Finally, the solid was filtered, washed, dried (110 °C, 10 h) and calcined (400 °C, 4 h).

Copper catalysts were prepared by chemisorption-hydrolysis, following the method used by Boccuzzi et al. [16]. Ten grams of the support (silica or alumina) was added to a $[\text{Cu}(\text{NH}_3)_4]^{2+}$ solution, prepared by adding NH_4OH (Sigma Aldrich) to a $\text{Cu}(\text{NO}_3)_2 \cdot 3\text{H}_2\text{O}$ solution (Sigma Aldrich) until a pH of 9. After 20 min of stirring, the slurry was diluted slowly in an ice bath at 0 °C, in order to allow the hydrolysis of the copper complex, as well as the deposition of the finely dispersed product. The solid was then separated by filtration, washed, dried (110 °C, 12 h) and calcined (300 °C, 4 h).

Before the hydrogenation process, all catalyst precursors were activated by reduction in a CHESA quartz tube furnace. First, samples were dried at 150 °C in a flow of pure hydrogen for 1 h to remove any trace of water. Then, temperature was raised up to the final reduction temperature. Samples were kept at the final temperature for a period of 6 h, in order to complete the reduction of the most stable fraction. The reduction temperature was established based on the results of temperature programmed reduction discussed below.

Catalyst characterization

Samples of catalyst precursors were subjected to the temperature programmed reduction (TPR) technique, in order to determine the temperature interval at which the reduction process takes place. Measurements were performed using a Micromeritics AutoChem II 2920 apparatus, equipped with a thermal conductivity detector. Samples (20 mg) were heated from room temperature to 900 °C, at a heating rate of 5 °C min^{-1} , under a flow of 5% H_2/Ar and at atmospheric pressure. Prior to the analysis, samples were subjected to a sweeping treatment with argon at 450 °C for 15 min.

The metal content of the catalysts was determined by inductively coupled plasma-atomic emission spectrometry analysis (Agilent 7700 X), after dissolving them in

concentrated HNO₃. The textural properties (specific surface area, pore volume and pore diameter) of supports and catalysts were determined by nitrogen adsorption-desorption at 77 K in a Micromeritics ASAP 2010 equipment.

Hydrogenation experiments

Experiments were performed using as feedstock a commercial refined sunflower oil (iodine value 138.1±0.4) with the following composition in fatty acids: palmitic acid (16:0) 6.02±0.12%, stearic acid (18:0) 3.77±0.08%, oleic acid (18:1) 20.11±0.37%, linoleic acid (18:2) 69.76±0.89%, linolenic acid (18:3) 0.15±0.02% and arachidonic acid (20:4) 0.19±0.03%.

Hydrogenation experiments were carried out in a 300 ml stainless steel reactor, operated in a semi-continuous mode. The reactor was provided with four baffles to prevent vortex formation, thus allowing a suitable turbulence level. The reactor was heated using a PID controlled electric resistance attached to a Pt100 temperature sensor immersed in the liquid. A continuous flow of hydrogen was used, in excess of the stoichiometric amount, in order to obtain higher yield, as well as reproducible results.

In a typical hydrogenation run, 75 g of sunflower oil and the required amount of each catalyst (to yield a fixed metal to oil ratio) were charged into the reactor. After loading, the reactor was purged with nitrogen to ensure an oxygen free environment. The system was heated up to the reaction temperature while stirring, and then a flow of hydrogen was introduced. The reactor was purged for 15 s to eliminate nitrogen, and then pressure was increased up to the operation value. The time at which the operating pressure was reached was considered to be the initial time. During the hydrogenation process, samples of oil were collected through a sampling valve.

Refractive indices, measured at 60 °C using a refractometer (Abbé PZO-RL1), were used to monitor the progress of the hydrogenation reaction. A calibration curve was prepared, to relate the refractive index to the iodine value (IV) of partially hydrogenated oils, measured by the Hanus method.

The fatty acid composition of oil samples was measured by gas chromatography. The reaction products were converted into their methyl esters and analysed in a 8700 Perkin-Elmer gas chromatograph, equipped with a flame ionization detector and split-splitless capillary inlet in a 50 m capillary column (Tracsil TR CN100, Tecnokroma). The injector and detector temperatures were 280 and 250 °C, respectively. Helium and

hydrogen were used as carrier gases. After the oven temperature was kept constant at 80 °C for 6 min, temperature was raised up to 200 °C at a heating rate of 10 °C min⁻¹, and hold for 20 min. The total amount of *trans* isomers was calculated as the sum of all C₁₈ *trans* isomers.

Results and discussion

Catalyst characterization

Temperature programmed reduction

Figure 1 displays the TPR profiles of catalyst precursors. Supported nickel catalysts exhibit a unique broad reduction peak with a maximum near 500 °C (Figure 1a). This profile can be explained by the preparation method used. The hydrolysis of urea has the advantage of increasing the hydroxyl ion concentration, thus leading to a limited nucleation, which results in a homogeneous distribution of small particles over the support. The high temperatures required for both nickel catalysts evidence the presence of compounds of difficult reducibility. Nickel hydroxide has been reported to react with silica support to form nickel hydrosilicate, a highly dispersed phase [17]. When alumina is used as a support, the maximum of the reduction peak takes place at slightly lower temperature. In this regard, although nickel hydroaluminate might also be formed, the formation of this phase would take place to a lesser extent, thus resulting in a weaker metal-support interaction.

The TPR profile of Pd/SiO₂ (Figure 1b) has a different shape, with a negative peak at 50 °C and a positive hydrogen consumption around 120 °C. The consumption of hydrogen is due to the reduction of palladium oxide:



Regarding the negative peak, it is known that palladium crystals can adsorb hydrogen at room temperature to form palladium hydride, PdH [18]. As temperature is increased, this phase is decomposed, resulting in the release of hydrogen.

The reduction of PdO supported on alumina takes place at room temperature. Due to the low reduction temperature required, hydrogen consumption cannot be observed in the TPR profile, since the apparatus cannot operate at such low temperatures.

Figure 1c shows the TPR profiles of platinum supported precursors. Pt/SiO₂ exhibits a peak at 180 °C and a very weak band between 200-350 °C. The peak at low temperature

is attributed to the reduction of PtO₂ species. The band at higher temperature could be attributed to the reduction of oxy or hydroxychlorinated Pt species, which have a strong interaction with the support, probably due to the formation of a silicate [19]. Pt/Al₂O₃ catalyst shows a peak centred at 280 °C, attributed to the consumption of H₂ caused by the interaction between Pt oxide species and Al₂O₃ support.

The hydrogen consumption profiles of cobalt precursors are shown in Figure 1d. Three regions of H₂ consumption can be identified for Co/Al₂O₃. The first peak, with a maximum near 250 °C, could be associated with the reduction of Co₃O₄ formed by calcination to CoO, whereas the peak at 400 °C is attributed to the reduction of CoO to metallic cobalt [20]. Moreover, Co/Al₂O₃ sample exhibits a very weak band at 650 °C, which could be ascribed to Co species that interact strongly with alumina support.

Co/SiO₂ sample exhibits two peaks, at 280 and 650 °C. The first peak could be related to the reduction of Co(III) to Co(II). Regarding the second peak, its shape (different from that of Co/Al₂O₃) and the separation between the two maxima, suggests that this peak could not only be attributed to the reduction of Co(II) to metallic cobalt. It is hypothesized that the last reduction peak appears as a consequence of the reduction of Co(II) and species of cobalt having different interaction strengths with silica support [21].

Figure 1e displays the TPR profiles of supported copper precursors. For both samples, the consumption of H₂ takes place at low temperature, between 150 and 300 °C. Cu/SiO₂ exhibits a well defined reduction peak with a maximum around 200 °C, attributed to the reduction of highly dispersed CuO particles to metallic copper. Furthermore, Cu/SiO₂ sample shows a very weak and no clearly defined band at 250-300 °C. This hydrogen consumption could be related to the reduction of highly dispersed copper species and/or ions that are more difficult to reduce, since they have a strong interaction with the support.

The profile of Cu/Al₂O₃ has two peaks. The peak at high temperature is related to the reduction of Cu(II) species. The peak at low temperature region is assigned to highly dispersed copper species which are easy to reduce. These copper species might include Cu₂O oxide, isolated Cu²⁺ ions that interact strongly and weakly with alumina support and small two-dimensional or three-dimensional clusters [22].

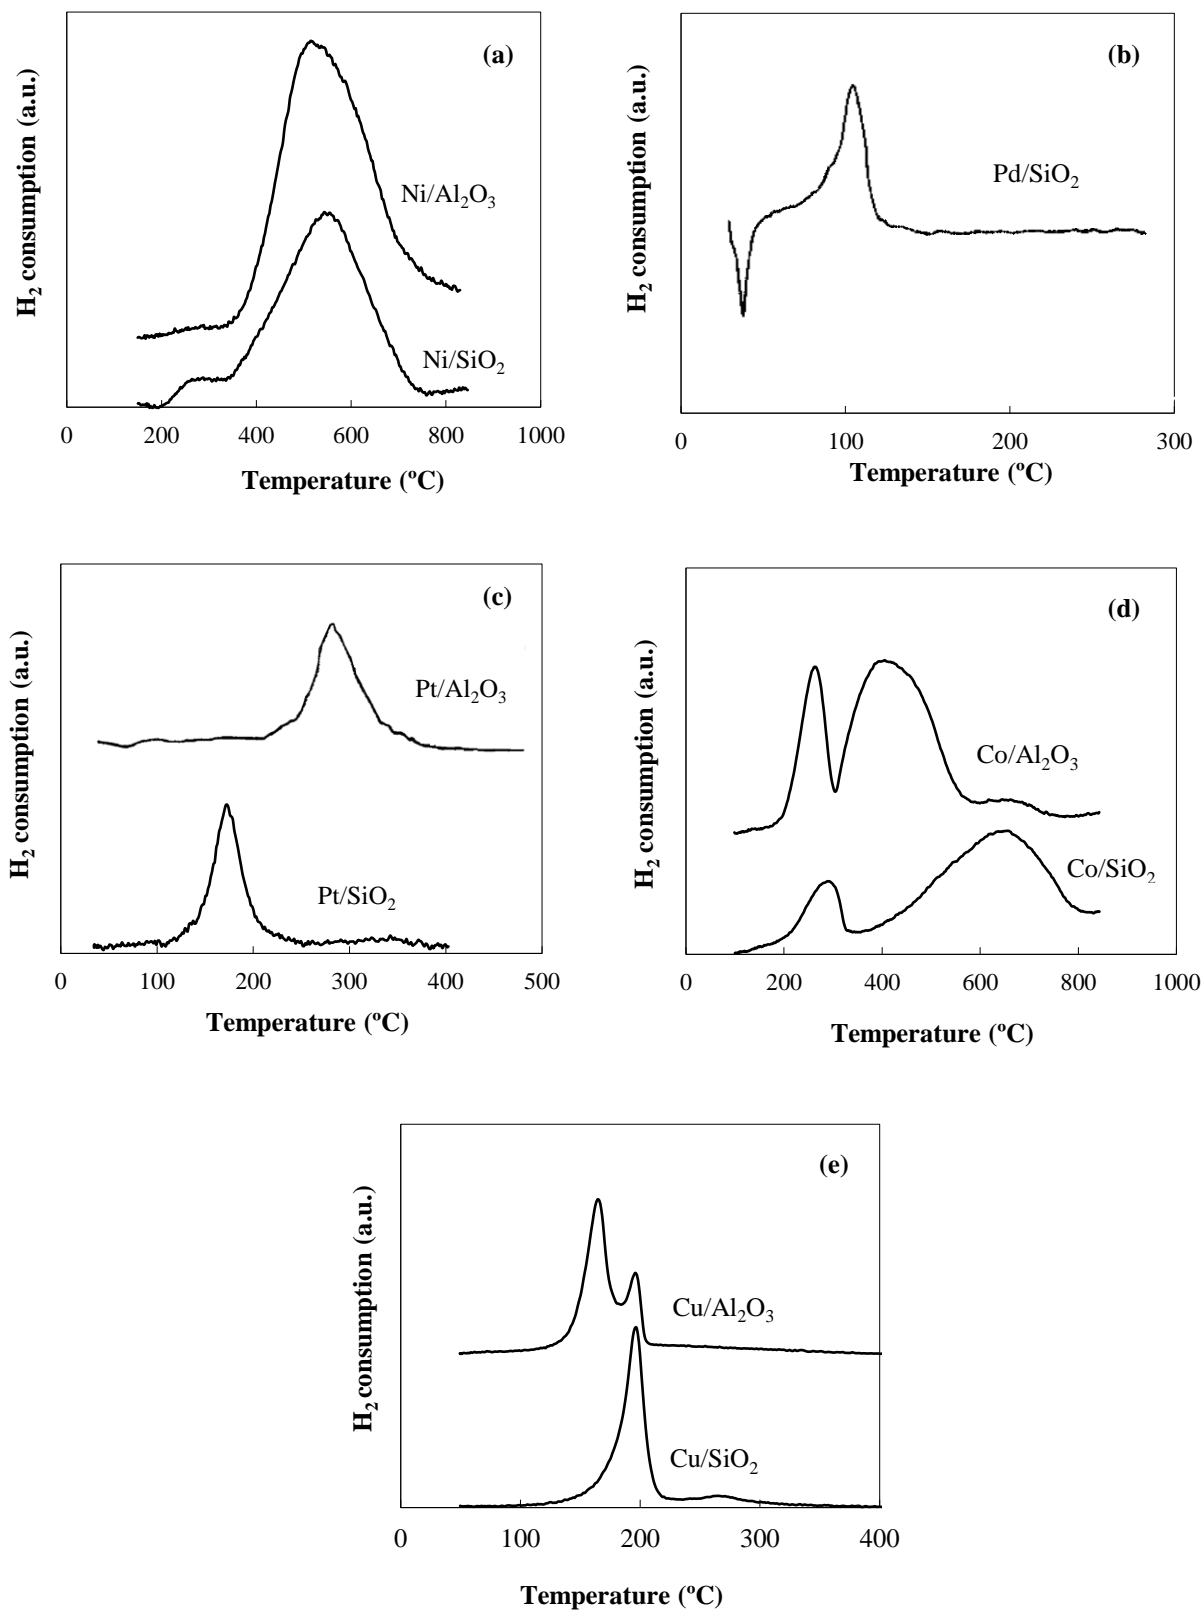


Fig. 1

The reduction temperature of the catalysts was established based on the TPR results, as well as on the preparation methods reported in the literature. Table 1 summarizes the reduction temperature used for each catalyst.

Table 1. Reduction temperature applied to each catalyst and criteria for the selection.

| Catalyst | Reduction T applied (°C) | Based on |
|---|--------------------------|-----------------------------------|
| Ni/SiO ₂ and Ni/Al ₂ O ₃ | 550 | TPR (peak at 550 °C) [23, 24] |
| Pd/SiO ₂ and Pd/Al ₂ O ₃ | 300 | TPR (peak at 120 °C) [4, 25] |
| Pt/SiO ₂ and Pt/Al ₂ O ₃ | 300 | TPR (peaks at 180-280 °C) [4, 25] |
| Co/SiO ₂ and Co/Al ₂ O ₃ | 600 | TPR (peaks at 400-650 °C) [20] |
| Cu/SiO ₂ and Cu/Al ₂ O ₃ | 320 | TPR (peaks at 200-250 °C) [26] |

Textural properties of catalysts

Table 2 shows the properties of supports and supported metal catalysts: metal content, BET specific surface area, pore volume and average pore diameter.

Table 2. Properties of supports and supported metallic catalysts.

| Catalyst | Metal (%) | S _{BET} ¹ (m ² ·g ⁻¹) | V _p ² (cm ³ ·g ⁻¹) | D _p ³ (Å) |
|---|-----------|--|---|---------------------------------|
| Silica (SiO ₂) | - | 330.0 | 1.52 | 175.3 |
| Alumina (Al ₂ O ₃) | - | 305.3 | 0.41 | 62.2 |
| Ni/SiO ₂ | 20.4 | 405.3 | 2.15 | 113.7 |
| Ni/Al ₂ O ₃ | 19.1 | 240.2 | 0.33 | 54.0 |
| Pd/SiO ₂ | 5.2 | 270.8 | 1.19 | 163.6 |
| Pd/Al ₂ O ₃ | 4.9 | 228.6 | 0.28 | 60.7 |
| Pt/SiO ₂ | 2.2 | 277.2 | 1.45 | 182.8 |
| Pt/Al ₂ O ₃ | 2.1 | 264.0 | 0.32 | 58.8 |
| Co/SiO ₂ | 35.4 | 194.3 | 0.64 | 136.2 |
| Co/Al ₂ O ₃ | 36.9 | 209.1 | 0.36 | 79.7 |
| Cu/SiO ₂ | 14.6 | 291.5 | 0.67 | 88.1 |
| Cu/Al ₂ O ₃ | 8.3 | 164.8 | 0.28 | 65.8 |

¹Specific surface area (BET method)

²Pore volume (BJH method, adsorption branch)

³Pore diameter (BJH method, adsorption branch)

It is observed that, in general, the BET surface area of metallic catalysts is lower than that of the supports (SiO_2 or Al_2O_3). This effect could be attributed to the partial blockage of support pores due to the addition of the metal. Contrary to the general trend, the specific surface area of Ni/ SiO_2 catalyst is 22.8 % higher than that of the support, which could be explained by the formation of porous structures of nickel hydrosilicate of high surface area. The effect of the support on the specific surface area depends on the type of metal. Pt and Co catalysts exhibit a similar BET surface area, irrespective of the support. On the contrary, Ni, Pd and Cu catalysts exhibit a higher surface area when silica is used as a support (68.7 % higher for Ni, 18.5 % for Pd and 76.9 % for Cu).

The pores of the catalyst must be large enough so that the active metal is accessible to triglyceride molecules. The oil molecular weight is about 890 g/mol and its diameter about 15 Å, considering spherical molecule. The results of a previous study [27] suggest that a pore diameter three times larger than triglyceride molecular radii ensures an adequate diffusion through the pores of the catalyst and therefore the progress of the reaction. Surface area in the micropore range would not be available for the hydrogenation reaction. According to data in Table 2, the accessibility of the reactants inside the catalyst pores is not hindered.

Catalyst activity

A comparative study of sunflower oil hydrogenation was performed. Due to the different activity of the catalysts, two series of experiments were carried out. The operating conditions are as follows: a) 150 °C, 3.5 bar and a metal to oil ratio of $2.5 \cdot 10^{-5} \text{ g}_{\text{metal}} \cdot \text{g}_{\text{oil}}^{-1}$ for Pd and Pt catalysts; b) 180 °C, 4.5 bar and a metal to oil ratio of $1.2 \cdot 10^{-3} \text{ g}_{\text{metal}} \cdot \text{g}_{\text{oil}}^{-1}$ for Co and Cu, as those catalysts possess a lower activity. For a better comparison, nickel-based catalysts were employed in both series of experiments, to be used as a reference.

The hydrogenation activity of the catalysts was monitored by the decay of IV (Table 3). It was measured the time required to reach a IV of 70. This value was selected because: (i) it is a typical value for oleomargarine, the final product, and (ii) it corresponds to the point at which the formation of stearic acid begins to be important.

The hydrogenation activity of the first set of catalysts decrease in the order: Pd/Al₂O₃ > Pd/SiO₂ > Pt/Al₂O₃ > Ni/SiO₂ > Ni/Al₂O₃ >> Pt/SiO₂. Thus, the activity of Pd catalysts is higher than that of Ni catalysts. On the contrary, for the catalysts based on Pt, the activity depends to a great extent on the support. In fact, Pt/Al₂O₃ is more active than Ni catalysts, whereas Pt/SiO₂ exhibits the lowest hydrogenation activity. The activity of Pt/SiO₂ catalyst is much lower than expected, based on the activity of Pd metal and on its textural properties (the specific surface area of this catalyst is very similar to that of Pt/Al₂O₃). This behaviour could be explained by the TPR profiles of both supported Pt catalysts. In fact, Pt/Al₂O₃ shows a well defined peak at 280 °C, ascribed to the interaction of platinum oxide species and the support, while this band is very weak for Pt/SiO₂. Thus, this interaction would hardly take place, thus resulting in a poorer dispersion of Pt.

Table 3. Percentage of *cis* and *trans* oleic acid and stearic acid for the indicated catalysts, corresponding to a IV of 70.

| Catalyst | T (°C) | P (bar) | Metal/oil ratio (g _{metal} ·g _{oil} ⁻¹) | Time to reach a IV=70 (min) | Content of <i>cis</i> -C18:1 (%) | Content of <i>trans</i> -C18:1 (%) | Content of C18:0 (%) |
|--|--------|---------|---|-----------------------------|----------------------------------|------------------------------------|----------------------|
| Ni/SiO ₂ | 150 | 3.5 | 2.5·10 ⁻⁵ | 122 | 42.1 | 26.0 | 19.4 |
| Ni/Al ₂ O ₃ | 150 | 3.5 | 2.5·10 ⁻⁵ | 125 | 43.4 | 25.7 | 14.6 |
| Pd/SiO ₂ | 150 | 3.5 | 2.5·10 ⁻⁵ | 97 | 36.1 | 39.1 | 18.0 |
| Pd/Al ₂ O ₃ | 150 | 3.5 | 2.5·10 ⁻⁵ | 49 | 35.7 | 44.7 | 16.3 |
| Pt/SiO ₂ ^a | 150 | 3.5 | 2.6·10 ⁻⁵ | 540 | 39.1 | 6.5 | 20.8 |
| Pt/Al ₂ O ₃ | 150 | 3.5 | 2.7·10 ⁻⁵ | 102 | 37.7 | 33.0 | 21.8 |
| Ni/SiO ₂ | 180 | 4.5 | 1.2·10 ⁻³ | 44 | 38.3 | 26.1 | 33.6 |
| Ni/Al ₂ O ₃ | 180 | 4.5 | 1.3·10 ⁻³ | 67 | 43.0 | 32.4 | 12.4 |
| Co/SiO ₂ | 180 | 4.5 | 1.3·10 ⁻³ | 119 | 34.8 | 32.4 | 8.3 |
| Co/Al ₂ O ₃ | 180 | 4.5 | 1.3·10 ⁻³ | 83 | 39.1 | 44.2 | 7.9 |
| Cu/SiO ₂ ^b | 180 | 4.5 | 1.2·10 ⁻³ | 600 | 43.7 | 42.0 | 4.9 |
| Cu/Al ₂ O ₃ ^c | 180 | 4.5 | 1.2·10 ⁻³ | 630 | 40.2 | 32.4 | 4.9 |

^a For a IV of 93

^b For a IV of 73

^c For a IV of 76

Regarding the performance of the second group of catalysts, the hydrogenation activity of Cu catalysts was found to be very low, which is attributed to the low hydrogen adsorption ability of this metal. Co catalysts show a hydrogenation activity lower than that of Ni catalysts. Overall, these results are in good agreement with the order in hydrogenation activity proposed by Kitayama [28]: Pd > Pt > Ni > Cu.

The influence of the support is different depending on the metal studied. Al₂O₃ allows for more active Pd, Pt and Co catalysts than SiO₂. The influence of the support is much more pronounced for supported Pt catalysts. In fact, Pt/SiO₂ catalyst has the lowest activity of all the catalysts studied. On the contrary, SiO₂ support results in Ni and Cu catalysts of higher activity.

Product distribution

Figures 2 and 3 display the fatty acid composition profiles of the hydrogenation of sunflower oil with Ni, Pd and Pt catalysts, and Ni, Co and Cu catalysts, respectively.

The total conversion of linoleic acid was achieved at different reaction times, depending on the catalyst (i.e. 50 min for Pd/Al₂O₃ and 600 for Cu/SiO₂). Linoleic acid was not fully converted using Pt/SiO₂ and Cu/Al₂O₃ catalysts, due to their low hydrogenation activity. Regarding the level of oleic acid, it increases first, then levels off (reaching a value of 40-50 %) and subsequently decreases, except for the catalysts with very low activity. The monoenic *trans* fatty acid profiles exhibit a similar trend, with its maximum (very different in value, depending on the catalyst) achieved after that of *cis*-C18:1. In general, the stearic acid content remains low (at 5-7 %) up to a reaction time of 40-60 min and then steadily increases.

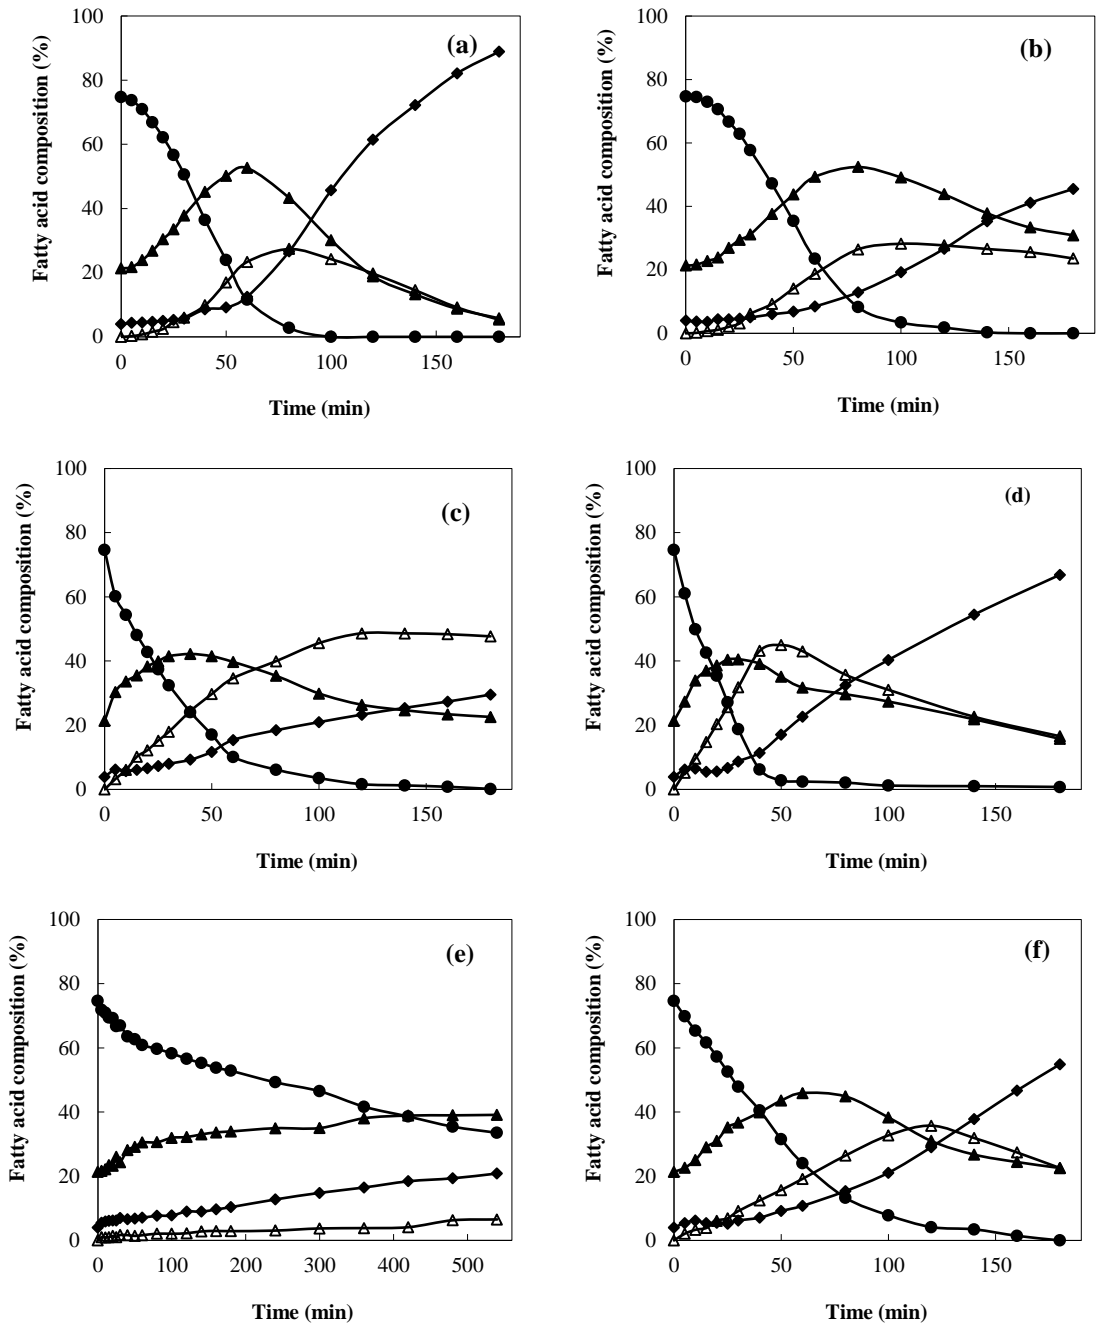


Fig. 2

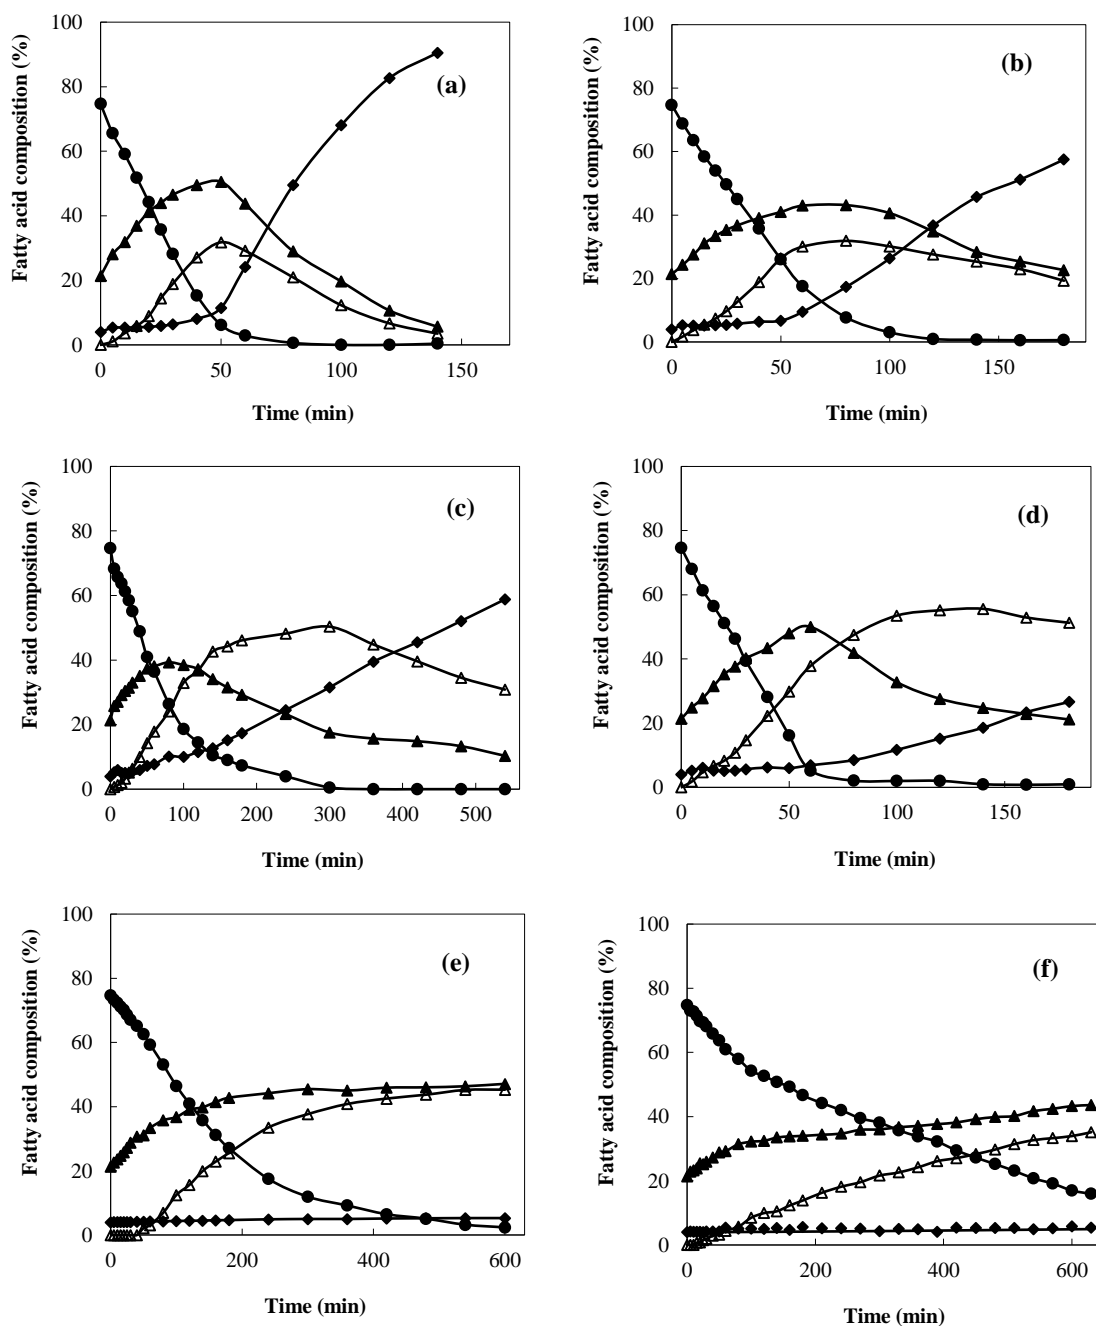


Fig. 3

Figures 2 and 3 are useful to give an overview of the performance of each catalyst over the whole reaction period. Nevertheless, it is essential to analyse the product distribution corresponding to a target IV, specially the amount of *trans* oleic acid and saturated stearic acid, which are of prime importance from the viewpoint of the quality of the final product. Table 3 shows the percentage of *cis* and *trans*-C18:1 and C18:0 for the selected IV level of 70.

Among the first group of catalysts (Ni, Pd and Pt), the highest percentage of *trans*-C18:1 is obtained with Pd, supported in either silica (39.1 %) or alumina (44.7 %), followed by Pt/Al₂O₃. The amount of *trans* isomers is the lowest (6.5%) for Pt/SiO₂. Although this percentage has been obtained for a IV of 93 (after 9 h of reaction time, due to the low activity of this catalyst), for a IV of 70 a content of *trans* isomers lower than that of the other catalyst could be expected. The higher production of *trans*-C18:1 of Pd catalysts, compared to Pt catalysts has been previously reported in the literature [4], and is attributed to their higher activity, as well as to the formation of conjugated dienes on Pd catalyst surface. Numwong et al. [25] have recently reported the following order in the selectivity towards *trans* isomers in the partial hydrogenation of vegetable oil-derived fatty acid methyl esters, using metallic catalysts supported on silica: Pd > Ni > Pt. These authors attributed the low *trans* selectivity of Pt and Ni catalysts to the subsequent hydrogenation of the intermediate *trans*-monounsaturated to saturated compounds. Regarding the formation of stearic acid, the values range between 14.6 and 21.8 %, the highest values being for supported Pt catalysts.

Among Ni, Co and Cu catalysts, the highest amount of *trans* isomers is obtained with Co/Al₂O₃ (44.2 %), followed by Cu/SiO₂ (42.0 %). Ni/SiO₂ exhibits the lowest content of *trans*-C18:1 (26.1 %), whereas the other three catalysts result in the production of a similar amount. The production of stearic acid follows the order: Ni > Co > Cu. A very low amount of stearic acid (below 5 %) is produced using supported copper catalysts.

Mixtures of catalysts

In order to strike a balance between the catalytic activity and the level of *trans* and saturated fatty acids, binary mixtures of catalysts were studied. Pd/Al₂O₃ was used in every mixture, since it provides the highest activity. The second catalyst was chosen on the basis of the production of the lowest amount of *trans*-C18:1: Pt/SiO₂, Cu/Al₂O₃, Co/SiO₂ and Ni/SiO₂.

The hydrogenation of sunflower oil was carried out at 120 °C and 3.5 bar. These milder operating conditions were selected with the aim of minimizing the production of *trans* isomers and saturated stearic acid, while obtaining an acceptable level of activity, provided by Pd/Al₂O₃ catalyst.

The concentration of the catalyst in the oil was the same as that used when the catalysts were employed separately. The ratio between the content of palladium and the other

metal is summarized in Table 4, as well as the time required to reach a IV=70 and the content of *trans* and saturated fatty acids.

Table 4. Percentage of *trans* oleic acid and stearic acid for the indicated mixtures of catalysts, corresponding to a IV=70.

| Catalyst | Pd/metal | Time to reach a IV=70 | Content of <i>cis</i> -C18:1 (%) | Content of <i>trans</i> -C18:1 (%) | Content of C18:0 (%) |
|--|----------|-----------------------|----------------------------------|------------------------------------|----------------------|
| Pd/Al ₂ O ₃ | - | 170 | 45.2 | 24.1 | 11.8 |
| Pd/Al ₂ O ₃ -Ni/SiO ₂ | 1.19 | 105 | 44.8 | 25.6 | 11.6 |
| Pd/Al ₂ O ₃ -Cu/Al ₂ O ₃ * | 0.02 | 300 | 51.6 | 20.1 | 7.7 |
| Pd/Al ₂ O ₃ -Co/SiO ₂ | 0.02 | 98 | 56.3 | 11.8 | 13.5 |
| Pd/Al ₂ O ₃ -Pt/SiO ₂ | 0.96 | 102 | 45.5 | 24.2 | 11.3 |

*For a IV=77.5

According to the data of Table 4, under the operating conditions used, Pd/Al₂O₃ results in a much lower production of *trans* monoenes (24.1 vs. 44.7 %), compared to the values obtained using a temperature of 150 °C (Table 3). The decrease in the production of stearic acid is less pronounced (11.8 vs. 16.3 %).

Regarding the content of *trans*-C18:1 and stearic acid, two mixtures result in a slight variation (compared to Pd/Al₂O₃): Pd/Al₂O₃-Ni/SiO₂ and Pd/Al₂O₃-Pt/SiO₂. Although Ni/SiO₂ and Pt/SiO₂ lead to the production of low amounts of *trans* isomers (especially Pt/SiO₂), this effect cannot be observed when used in conjunction with Pd/Al₂O₃.

On the contrary, two mixtures of catalysts provide a better product distribution. The addition of Cu/Al₂O₃ results in a decrease of 16.6 % in the production of *trans* monoenes (20.1 vs. 24.1) and a reduction of 34.7 % in saturated stearic acid (7.7 vs. 11.8 %). It should be noticed, nonetheless, that since this mixture of catalysts provide a much lower activity, the values correspond to a IV of 77.5.

Finally, Pd/Al₂O₃-Co/SiO₂ mixture results in a dramatic reduction of *trans* isomers (11.8 vs. 24.1 %, a reduction of 51.0 %), whereas it leads to a slightly higher amount of saturated stearic acid (13.5 vs. 11.8 %). This catalyst has a good balance between activity and selectivity, and provides the best product distribution of all the catalysts studied, both individually or in mixtures. Indeed, although Pt/SiO₂ used separately leads to a promising amount of *trans* isomers (6.5 % for a IV of 93), its low activity does not allow this catalyst to be considered suitable for the hydrogenation of sunflower oil.

Conclusions

The overall hydrogenation activity of the catalysts depends on both the type of metal and support. The following order can be proposed for the effect of the metal: Pd > Pt > Ni > Co > Cu. The influence of the support is different depending on the metal. Al₂O₃ allows for more active catalysts based on noble metals (Pd and Pt) and Co, the effect being much more pronounced for Pt. On the contrary, SiO₂ support results in catalysts based on Ni and Cu of higher activity. At a target IV of 70 (a typical value for oleomargarine), the production of *trans* isomers is minimum for Ni catalysts. On the contrary, the highest percentage of *trans*-C18:1 is obtained with Pd catalysts.

In order to strike a balance between the catalytic activity and product distribution, binary mixtures of catalysts have been studied. Among the mixtures studied, Pd/Al₂O₃-Co/SiO₂ results in a very low production of *trans* isomers (11.8 %), and a moderate amount of saturated stearic acid (13.5 %). This catalytic mixture has a good balance between activity and selectivity, and provides the best product distribution of all the catalysts studied. Consequently, from the standpoint of catalyst performance, the utilization of cobalt-based catalysts (or the addition of cobalt to other metallic catalysts), used in other hydrogenation processes, could be considered a promising alternative for the partial hydrogenation of vegetable oil. Further research is required to study the issue of autoxidation of fats (and thus, the economic feasibility), which is the main drawback of cobalt-based catalysts.

Acknowledgements

The authors gratefully acknowledge the financial support for this work provided by the Spanish Ministry of Science and Technology (Project PPQ2001-0270-C02-01). They are also grateful to Prof. A. T. Aguayo (UPV/EHU) for his assistance in catalyst characterization.

References

1. Mozaffarian D, Katan MB, Ascherio A, Stampfer MJ, Willett WC (2006) Trans fatty acids and cardiovascular disease. *New Engl J Med* 354: 1601-1613
2. Regulation of the European Parliament and of the Council of 25 October 2011 (2011). *Official Journal of the European Union*, 343 No 1169/2011: 18-63
3. Tonetto GM, Sánchez M. JF, Ferreira ML, Damiani DD (2009) Partial hydrogenation of sunflower oil: Use of edible modifiers of the cis/trans-selectivity. *J Mol Catal A-Chem* 299: 88-92
4. Edvardsson J, Rautanen P, Littorin A, Larsson M (2001) Deactivation and coke formation on palladium and platinum catalysts in vegetable oil hydrogenation. *J Am Oil Chem Soc* 78: 319-327
5. Dijkstra AJ (2006) Revisiting the formation of trans isomers during partial hydrogenation of triacylglycerol oils. *Eur J Lipid Sci Tech* 108: 249-264
6. Trasarti AF, Segobia DJ, Apesteguia CR, Santoro F, Zaccheria F, Ravasio N (2012) Selective hydrogenation of soybean oil on copper catalysts as a tool towards improved bioproducts. *J Am Oil Chem Soc* 89: 2245-2252
7. Choe E, Min DB (2006) Mechanisms and factors for edible oil oxidation. *Compr Rev Food Sci F* 5: 169-186
8. Pinto F, Martins S, Gonçalves M, Costa P, Gulyurtlu I, Alves A, Mendes B (2013) Hydrogenation of rapeseed oil for production of liquid bio-chemicals. *Appl Energy* 102: 272-282
9. Brimberg UI, Kamal-Eldin A (2003) On the kinetics of the autoxidation of fats: influence of pro-oxidants, antioxidants and synergists. *Eur J Lipid Sci Tech* 105: 83-91
10. Moulton KJ, Beal RE, Griffin EL (1973) Hydrogenation of soybean oil with copper catalysts containing small amounts of nickel catalysts. *J Am Oil Chem Soc* 50: 450-454
11. Wright AJ, Mihele AL, Diosady LL (2003) Cis selectivity of mixed catalyst systems in canola oil hydrogenation. *Food Res Int* 36: 797-804
12. Cepeda EA, Calvo B (2008) Sunflower oil hydrogenation: Study using response surface methodology. *J Food Eng* 89: 370-374
13. Andrade Sales E, Bugli G, Ensuque A, Mendes MDJ, Bozon-Verduraz F (1999) Palladium catalysts in the selective hydrogenation of hexa-1,5-diene and hexa-1,3-diene in the liquid phase. Effect of tin and silver addition Part 1. Preparation and characterization: from the precursor species to the final phases. *Phys Chem Chem Phys* 1: 491-498
14. Neri G, Milone C, Galvagno S, Pijpers APJ, Schwank J (2002) Characterization of Pt-Sn/carbon hydrogenation catalysts. *Appl Catal A-Gen* 227: 105-115

15. Barbier A, Hanif A, Dalmon J, Martin GA (1998) Preparation and characterization of well-dispersed and stable Co/SiO₂ catalysts using the ammonia method. *Appl Catal A-Gen* 168: 333-343
16. Boccuzzi F, Coluccia S, Martra G, Ravasio N (1999) Cu/SiO₂ and Cu/SiO₂-TiO₂ catalysts: I. TEM, DR UV-Vis-NIR, and FTIR characterisation. *J Catal* 184: 316-326
17. Ermakova MA, Ermakov DY, Cherepanova SV, Plyasova LN (2002) Synthesis of ultradispersed nickel particles by reduction of high-loaded NiO-SiO₂ systems prepared by heterophase sol-gel method. *J Phys Chem B* 106: 11922-11928
18. Neri G, Musolino MG, Milone C, Pietropaolo D, Galvagno S (2001) Particle size effect in the catalytic hydrogenation of 2,4-dinitrotoluene over Pd/C catalysts. *Appl Catal A-Gen* 208: 307-316
19. Torres GC, Ledesma SD, Jablonski EL, De Miguel SR, Scelza OA (1999) Hydrogenation of carvone on Pt-Sn/Al₂O₃ catalysts. *Catal Today* 48: 65-72
20. Bechara R, Balloy D, Dauphin J-, Grimblot J (1999) Influence of the characteristics of γ -aluminas on the dispersion and the reducibility of supported cobalt catalysts. *Chem Mater* 11: 1703-1711
21. Ernst B, Bensaddik A, Hilaire L, Chaumette P, Kiennemann A (1998) Study on a cobalt silica catalyst during reduction and Fischer-Tropsch reaction: In situ EXAFS compared to XPS and XRD. *Catal Today* 39: 329-341
22. Wang Z, Liu Q, Yu J, Wu T, Wang G (2003) Surface structure and catalytic behavior of silica-supported copper catalysts prepared by impregnation and sol-gel methods. *Appl Catal A-Gen* 239: 87-94
23. Cepeda EA, Calvo B (2008) Sunflower oil hydrogenation: Study using response surface methodology. *J Food Eng* 89: 370-374
24. Bartholomew CH, Farrauto RJ (1976) Chemistry of nickel-alumina catalysts. *J Catal* 45: 41-53
25. Numwong N, Luengnaruemitchai A, Chollacoop N, Yoshimura Y (2013) Effect of metal type on partial hydrogenation of rapeseed oil-derived FAME. *J Am Oil Chem Soc* 90: 1431-1438
26. Epron F, Gauthard F, Pinéda C, Barbier J (2001) Catalytic reduction of nitrate and nitrite on Pt-Cu/Al₂O₃ catalysts in aqueous solution: Role of the interaction between copper and platinum in the reaction. *J Catal* 198: 309-318
27. Cepeda EA, Calvo B, Sierra I, Iriarte-Velasco U (2015) Effect of the support and preparation method on the activity and selectivity of nickel catalysts for vegetable oil hydrogenation. *Korean J Chem Eng*, in press

28. Kitayama Y, Muraoka M, Takahashi M, Kodama T, Takahashi E, Okamura M (1997) Catalytic hydrogenation of linoleic acid over platinum-group metals supported on alumina. *J Am Oil Chem Soc* 74: 525-529

Figure captions

Fig. 1 Temperature programmed reduction of catalyst precursors

Fig. 2 Time course profiles of reactants and products (●) C18:2; (▲) C18:1 *cis*; (△) C18:1 *trans*; (◆) C18:0; during the hydrogenation of sunflower oil: (a) Ni/SiO₂ catalyst; (b) Ni/Al₂O₃ catalyst; (c) Pd/SiO₂ catalyst; (d) Pd/Al₂O₃ catalyst; (e) Pt/SiO₂ catalyst; (f) Pt/Al₂O₃ catalyst. Reaction conditions: temperature = 150 °C; H₂ pressure = 3.5 bar

Fig. 3 Time course profiles of reactants and products (●) C18:2; (▲) C18:1 *cis*; (△) C18:1 *trans*; (◆) C18:0; during the hydrogenation of sunflower oil: (a) Ni/SiO₂ catalyst; (b) Ni/Al₂O₃ catalyst; (c) Co/SiO₂ catalyst; (d) Co/Al₂O₃ catalyst; (e) Cu/SiO₂ catalyst; (f) Cu/Al₂O₃ catalyst. Reaction conditions: temperature = 180 °C; H₂ pressure = 4.5 bar