

Searching Materials Space for Hydride Superconductors at Ambient Pressure

Tiago F. T. Cerqueira, Yue-Wen Fang, Ion Errea, Antonio Sanna,*
and Miguel A. L. Marques*

A machine-learning-assisted approach is employed to search for superconducting hydrides under ambient pressure within an extensive dataset comprising over 150 000 compounds. The investigation yields ≈ 50 systems with transition temperatures surpassing 20 K, and some even reaching above 70 K. These compounds have very different crystal structures, with different dimensionality, chemical composition, stoichiometry, and arrangement of the hydrogens. Interestingly, most of these systems display slight thermodynamic instability, implying that their synthesis will require conditions beyond ambient equilibrium. Moreover, a consistent chemical composition is found in the majority of these systems, which combines alkali or alkali-earth elements with noble metals. This observation suggests a promising avenue for future experimental investigations into high-temperature superconductivity within hydrides at ambient pressure.

emphasis on achieving high T_c values above the boiling point of nitrogen (77 K). Nowadays, one of the primary goals in physics remains to find materials that exhibit superconductivity at ambient conditions to unlock new fundamental physics and enable wide applications of superconductors.

In the so-called unconventional superconductors, showcased by cuprate compounds, the highest superconducting transition temperatures are 134 and 164 K at ambient pressure and 30 GPa, respectively.^[1] Nevertheless, owing to the lack of a distinct understanding of the pairing mechanism, there is at the moment no quantitative theory that can be used to predict the superconducting properties of such systems, seriously hampering the search

for new unconventional compounds. On the other hand, the theoretical prediction and characterization of conventional superconductors, where the electrons at the Fermi surface are coupled by phonons to form Cooper pairs, can be well addressed by a combination of ab initio studies and Eliashberg theory. Unfortunately, since the experimental observation of superconductivity in MgB₂ in 2001,^[2] its T_c of 39 K remains the highest among the ambient-pressure conventional superconductors.

In the theory of electron–phonon coupled superconductors, the critical temperature T_c is proportional to the Debye temperature θ_D . Hydrogen, being the lightest element, provides a high

1. Introduction

A superconductor is a material exhibiting zero electrical resistance and perfect diamagnetism when cooled below a critical temperature T_c . Such unique properties have paved the way for groundbreaking applications of superconductors, ranging from powerful magnets in medical imaging, particle accelerators, or fusion reactors to superconducting qubits in quantum computers. Since the discovery of superconductivity in Hg in 1911, research on this field has focused on increasing T_c , with particular

T. F. T. Cerqueira
CFisUC
Department of Physics
University of Coimbra
Rua Larga, 3004-516 Coimbra, Portugal

Y.-W. Fang, I. Errea
Fisika Aplikatua Saila
Gipuzkoako Ingeniaritza Eskola
University of the Basque Country (UPV/EHU)
Europa Plaza 1, 20018 Donostia-San Sebastián, Spain

Y.-W. Fang, I. Errea
Centro de Física de Materiales (CSIC-UPV/EHU)
Manuel de Lardizabal Pasealekua 5, 20018 Donostia-San Sebastián,
Spain

I. Errea
Donostia International Physics Center (DIPC)
Manuel de Lardizabal Pasealekua 4, 20018 Donostia-San Sebastián,
Spain

A. Sanna
Max-Planck-Institut für Mikrostrukturphysik
Weinberg 2, D-06120 Halle, Germany
E-mail: sanna@mpi-halle.mpg.de

M. A. L. Marques
Research Center Future Energy Materials and Systems of the University Alliance Ruhr and Interdisciplinary Centre for Advanced Materials Simulation Ruhr University Bochum
Universitätsstraße 150, D-44801 Bochum, Germany
E-mail: miguel.marques@rub.de

The ORCID identification number(s) for the author(s) of this article can be found under <https://doi.org/10.1002/adfm.202404043>

© 2024 The Author(s). Advanced Functional Materials published by Wiley-VCH GmbH. This is an open access article under the terms of the [Creative Commons Attribution-NonCommercial-NoDerivs License](#), which permits use and distribution in any medium, provided the original work is properly cited, the use is non-commercial and no modifications or adaptations are made.

DOI: 10.1002/adfm.202404043

Debye temperature to the compounds that it forms, making hydrides the most obvious choice in the search for conventional high T_c superconductors.^[3] Over the past two decades, hundreds of binary hydrides, covering the majority of the chemical elements in the periodic table, have been either theoretically predicted or experimentally observed to exhibit superconductivity. However, in spite of chemical pre-compression in hydrides, experimental results indicate that achieving high T_c superconductivity still requires large external pressures. For example, experiments have suggested that $T_c > 200$ K generally requires pressures exceeding 150 GPa: T_c of 250 K in LaH₁₀ at 150 GPa,^[4,5] T_c of 215 K in CaH₆ at 172 GPa,^[6] and T_c of 243 K in YH₉ at 201 GPa,^[7] to name a few examples.

Recently, the search for high T_c hydrides useful for device applications, has shifted from solely prioritizing the enhancement of T_c to achieving high T_c materials at low or even ambient pressure. Unfortunately, only a few superconducting binary hydrides have been found in ambient-pressure experiments, and their critical temperatures are below or near 10 K, for instance PdH with T_c of 9 K,^[8] TiH_{0.71} with T_c of 4.3 K,^[9] MoH_{1.2} with T_c of just 0.92 K,^[10] Th₄H₁₅ with T_c of 8.2 K,^[11] NbH_{x < 0.7} with T_c of 9.4 K,^[12] and ZrH₃ with T_c of 11.6 K.^[13] All these experimental studies (except the case of ZrH₃) were carried out more than 30 years ago.

Compared to the binary hydrides, the ternary, or more generally, the multinary hydrides have a much larger structural phase space and are therefore expected to host higher T_c s at low and ambient pressures.^[14,15] There were several experimental studies in the 1970s in ternary hydrides such as HfV₂H with a T_c of 4.8 K^[16] and Pd_{0.55}Cu_{0.45}H_{0.7} with a T_c of 16.6 K.^[17] However, more recently, theoretical reports that are facilitated by high-throughput calculations, high T_c templates, crystal structure prediction, or machine learning methods, have pioneered the exploration of promising superconducting hydrides at low/ambient pressure. Due to the strong quantum ionic and anharmonic effects, both BaSiH₈^[18] and LuN₄H₁₁^[19] are predicted to exhibit dynamical stability and high T_c of 94 and 100 K, respectively, at 20 GPa. The compound CsBH₅ is predicted to have a strong electron–phonon coupling constant λ of 3.96 at 1 GPa, resulting in a high T_c of 83 K.^[20] The deep-learning-recommended MgBH₂₁^[21] and the perovskite MgHCu₃^[22] are predicted by electron-phonon coupling calculations to show T_c values of 15.5 and 42 K at atmospheric pressure, respectively. Finally, Mg₂IrH₆ with a T_c above 80 K was predicted, together with other compounds with the same cubic structure, in our recent study^[23] and in Ref. [24].

Herein, we use a machine-learning method to accelerate the search of superconductivity in a dataset of more than 150 000 hydrides. Our workflow has identified 54 compounds with T_c exceeding 20 K, most of which have not been reported previously. These results provide a huge platform for ambient-pressure superconducting hydrides, inviting worldwide experimental groups to explore their synthesis, and further study the transport properties, Meissner effect, isotope effect and potential device applications.

2. Results and Discussion

Here we are concerned with hydrides only. To identify such compounds, that are potentially high-temperature conventional su-

perconductors at ambient pressure, we used a machine learning accelerated workflow along the lines of Ref. [25]. Unfortunately, the dataset of Ref. [25] did not include any high-temperature hydride (with the exception of PdH which has a too-high T_c in the harmonic approximation), so the machine trained in this dataset had difficulties predicting hydrides. To circumvent this problem, we added manually a series of hydrides to the dataset and re-trained the machine, which was subsequently used to predict the superconducting properties of the hydrides present in the ALEXANDRIA database.^[25,26] This workflow consists of three main steps: 1) a machine learning model provides a first crude (but extremely fast) pruning of the data, filtering out materials that are unlikely to show high T_c 2) compounds predicted to have T_c above 20 K are then analyzed with density-functional perturbation theory (DFPT) and added to the dataset, while materials showing imaginary phonon frequencies are discarded 3) a set of very accurate calculations are performed for the most promising materials using state-of-the-art first principle methods. We note that step 2) validates 1) and 3) validates 2), allowing for the identification of the false positives. Eventual false positives resulting from incorrect machine learning predictions that are not captured by retraining the model are, unfortunately, overlooked. Our final model had an error of 1.93 K for T_c , 22.47 K for ω_{log} , and 0.16 for λ . This should be compared to the average values in the training set of 3.41 K, 233.38 K, and 0.48, respectively.

In **Tables 1** and **2** we present all the hydrides predicted to have superconducting transition temperatures above 20 K (see **Supporting Information** for extra details for each compound). We note that the values presented in the tables are the ones obtained with density-functional perturbation theory and the Allen–Dynes formula, and not the values predicted by the machine-learning model. We divided the compounds by families, and ordered by T_c , in order to facilitate the analysis. As we can see, many compounds belong to just a few families such as the SM₂-TM-H₆ family,^[23,27] perovskites (both normal and inverted), and double perovskites. There is also a striking regularity in what concerns the chemical compositions. In fact, the large majority of the hydrides include both a simple metal (SM), typically an alkali, alkali earth, or even a IIIA or IVA element, and a transition (TM) or noble metal.

2.1. SM₂-TM-H₆

Four elements of the SM₂-TM-H₆ family have already been discussed in Ref. [23], namely Mg₂RhH₆, Mg₂IrH₆, Mg₂PdH₆, Mg₂PtH₆, and a few more were proposed in Ref. [27]. This structure, depicted in **Figure 1a**, is described by a face-centered cubic lattice with space group *Fm* $\bar{3}$ *m*. Here, the SM atoms are in the 8c, the TM atoms in the 4a, and the H atoms in the 24e Wyck-off positions. As we can see from **Figure 1a**, the H atoms form isolated octahedra around the TM atoms. All high-temperature superconductors we found within this family were perfectly symmetric and did not exhibit any deformation of the octahedra.

From the chemical point of view, in all our systems SM is a simple metal from groups IA, IIA, or IIIA while TM is a transition or a noble metal (see **Table 1**). It is simple to understand the chemical compositions in **Table 1** by a simple electron counting argument. The parent compound of this family, Mg₂RuH₆,^[29,30] is a stable semiconductor. Considering the standard oxidation

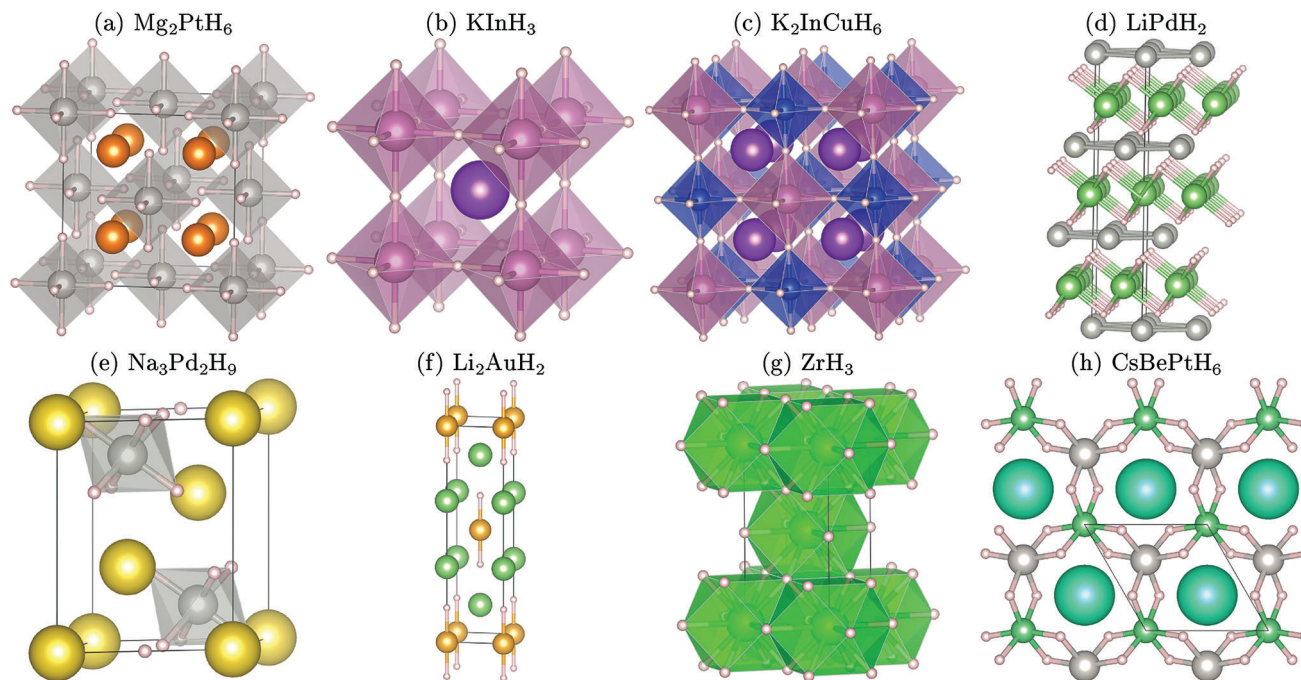


Figure 1. Crystal structures of selected hydrides. The lines indicate the conventional cell. In the pictures H atoms are white, Li and Be green, Na yellow, Mg orange, K violet, Cu dark blue, Zr green, In pink, Cs cyan, Pd and Pt grey, and Au orange.

states of +2 for Mg and -1 for H in hydrides, this leads to +2 for Ru, a standard oxidation state found in this metal (although less common than the +3 or +4 states). In total, this compound has 18 valence electrons that fill completely the electronic valence states. A superconducting state emerges when this compound is doped with electrons, either one per formula unit (e.g., Mg_2IrH_6 , Al_2TcH_6 , or Na_2AuH_6) or two per formula unit (e.g., Mg_2PtH_6 or Ga_2RuH_6).

From the electronic point of view, all compounds with SM being an alkali or an alkali earth are quite similar. The SM atom is fully ionized, so the top of the valence bands and the bottom of the conduction bands^[31] are dominated by H and TM states. There are, of course, some changes to the dispersion of the bands that are system-specific, leading to different densities of states at the Fermi level, even for compounds that are isoelectronic. The situation is slightly more complicated when the SM is a group IIIA metal, as its states are not entirely ionized. This leads to an entirely different dispersion of the bands and therefore a different Fermi surface. In spite of this, the superconducting properties are in line with the ones of the IA and IIA-based compounds.

Concerning the phonon dispersions (see [Supporting Information](#)), the low energy modes are usually dominated by the TM atom, as expected by their larger mass, followed by a manifold composed mainly by the SM atom. However, in some cases where SM is a group IIIA metal, we see a strong mixture of SM and TM states in the low energy range (e.g., in Al_2TcH_6 or in Al_2ReH_6). The higher energy states, that contribute mostly to λ are dominated by the vibrations of the hydrogen octahedra. The maximum phonon frequencies present in the spectrum can go from ≈ 125 to almost 240 meV, depending on the chemical composition.

These compounds exhibit a wide range of values for ω_{\log} with the lowest being 292 K (Ga_2RuH_6) up to more than 770 K

(Mg_2PtH_6 and Mg_2RhH_6). On the other hand, the values of the electron-phonon coupling constant are typically ≈ 1 –1.2. Exceptions to this are Ga_2RuH_6 , which has a very soft mode at the X-point (that is also responsible for the abnormally low value of ω_{\log} for this compound), and Mg_2NiH_6 which has the low-value $\lambda = 0.61$ (partially compensated by the high value of $\omega_{\log} = 921$ K). The combination of high ω_{\log} and relatively high λ allows for dynamically stable crystals with the very high values of T_c present in Table 1.

For the materials of this family with distances to the hull below 100 meV per atom, we performed ab initio molecular dynamics simulations in order to analyze their kinetic stability. The results did not show any phase transition up to 150 K with suggests the stability of these materials at temperatures above their T_c (see [Supporting Information](#)).

2.2. Perovskites

Concerning the hydride perovskites, we find both normal (see Figure 1b) and inverted systems. There are a series of hydride perovskites that have been synthesized experimentally.^[32] Many of these are charge compensated, often combining an alkali and an alkali earth in positions 1a and 1b, such as LiBeH_3 ,^[33] BaLiH_3 ,^[34] or KMgH_3 .^[35] Not surprisingly, such systems are semiconducting. There are, however, a few non-charge compensated systems that have been discovered, such as AlSrH_3 ^[36] (obtained through a high-pressure synthesis procedure) or $\text{SrPdH}_{2.7}$.^[37] There are also a few inverted (anti-)perovskites reported in the experimental literature, such as ChHM_3 where $M = \text{Li}, \text{Na}$, and Ch is a chalcogen^[38] or $\text{InH}_{0.8}\text{Pd}_3$.^[39]

The band structure of KInH_3 has a characteristic very dispersive, parabolic band centered at R that crosses the Fermi level. All

Table 1. Superconducting transition temperatures calculated with the Allen-Dynes formula (T_c^{AD} in K), logarithmic average of the phonon frequencies (ω_{log} in K), average of the square of the phonon frequencies (ω^2 in K), electron–phonon coupling constant (λ) and distance to the convex hull of stability (E_{hull} in meV per atom). The first column of the table contains a running number that can be used to identify the compounds in the Supporting Information.

#		T_c^{AD}	ω_{log}	ω^2	λ	E_{hull}	Comment
SM₂-TM-H₆^[27]							
1	Li ₂ CuH ₆	86.0	491	890	1.96	171	
2	Mg ₂ PtH ₆	78.3	770	922	1.24	140	[23]
3	Mg ₂ PdH ₆	63.8	760	911	1.08	120	[23]
4	Mg ₂ IrH ₆	59.4	634	1052	1.16	61	[23]
5	Mg ₂ RhH ₆	53.8	771	1132	0.96	30	[23]
6	Na ₂ AgH ₆	46.1	511	1000	1.12	204	
7	Al ₂ MnH ₆	43.9	587	1014	1.00	68	
8	Al ₂ TcH ₆	43.1	484	964	1.11	53	
9	Al ₂ ReH ₆	36.4	505	994	0.98	55	
10	Ca ₂ AgH ₆	35.9	418	740	1.09	166	
11	Ca ₂ LiH ₆	33.0	433	706	1.01	226	
12	Na ₂ AuH ₆	31.6	632	1196	0.80	73	
13	Na ₂ CuH ₆	29.4	580	1122	0.81	135	
14	Ga ₂ RuH ₆	26.9	292	822	1.14	230	
15	Mg ₂ NiH ₆	22.7	921	1120	0.61	63	
16	Ga ₂ OsH ₆	20.9	262	841	1.04	179	
Perovskites							
17	KInH ₃	72.9	487	698	1.70	77	
18	Al ₄ H	30.4	430	546	0.97	136	[28]
19	AlHgH ₃	28.4	403	854	0.96	278	
20	PbHgH ₃	25.8	462	808	0.85	420	
21	PbOsH ₃	23.2	292	722	1.03	369	
22	TiHMg ₃	21.8	196	362	1.31	370	inverted
Double Perovskites							
23	K ₂ InCuH ₆	53.0	510	716	1.25	47	
24	K ₂ LiCuH ₆	47.1	470	719	1.21	116	
25	Na ₂ LiCuH ₆	45.9	666	950	0.95	102	
26	Na ₂ SiPdH ₆	39.8	875	1062	0.77	84	
27	Na ₂ LiZnH ₆	37.8	519	763	0.98	146	
28	Na ₂ GaRuH ₆	35.2	535	864	0.93	162	
29	Cs ₂ NaSnH ₆	34.5	324	588	1.27	67	
30	K ₂ AlHgH ₆	32.5	349	701	1.15	86	
31	K ₂ HgAuH ₆	32.5	396	913	1.06	49	
32	K ₂ InAgH ₆	31.7	660	860	0.79	32	
33	Rb ₂ AlHgH ₆	31.4	140	463	2.53	83	
34	Na ₂ CdCuH ₆	26.0	740	986	0.69	63	
35	Na ₂ MgCuH ₆	24.7	251	707	1.20	92	
36	Pb ₂ CuRuH ₆	23.7	243	712	1.19	149	
37	K ₂ AlCdH ₆	21.0	507	834	0.74	74	

other hydride perovskites have very diverse electronic band structures and Fermi surfaces. We note due to the high Fermi velocity of the bands, the density of electronic states at the Fermi level is not extremely high in most cases. The low-energy phonons of the normal hydride perovskites are as expected dominated by the heavier atoms, but have a sizeable contribution to λ . In

Table 2. Continuation of Table 1.

#		T_c^{AD}	ω_{log}	ω^2	λ	E_{hull}	comment
Other structures							
38	Be ₃ H	65.9	588	718	1.34	202	[43]
39	Mg ₂ SrPtH ₈	49.4	568	925	1.10	117	
40	Mg ₂ SrPdH ₈	49.1	652	925	1.00	93	
41	Mg ₂ BaPdH ₈	41.6	646	939	0.92	63	
42	Mg ₂ BaPtH ₈	38.4	590	961	0.92	102	
43	Na ₂ AuH ₄	43.8	394	598	1.31	35	
44	LiPdH ₂	38.6	532	849	0.98	108	[44]
45	NaPdH ₃	29.3	215	722	1.56	193	
46	Na ₃ Pd ₂ H ₉	25.3	516	1031	0.80	86	
47	Li ₂ AuH ₂	20.8	368	762	0.86	59	
48	Li ₄ BeH ₅	37.2	465	716	1.04	154	
49	PdH	34.9	343	429	1.24	8	[8,45]
50	InH	31.2	312	724	1.20	223	
51	ZrH ₃	25.8	363	748	0.97	105	[13]
52	InH ₃	20.6	218	700	1.17	286	
53	Zr ₂ HfH ₈	25.1	266	663	1.16	94	
54	KBePtH ₆	39.9	371	764	1.27	138	
55	RbBePtH ₆	37.9	379	767	1.21	135	
56	CsBePtH ₆	30.9	370	787	1.07	130	
57	Li ₂ CuGaH ₆	37.9	527	891	0.97	133	
58	K ₂ AgCdH ₆	27.5	422	775	0.92	75	
59	Na ₂ PdIrH ₆	23.5	456	736	0.82	93	

many of these systems, H modes are highly dispersive and can be found ≈ 30 – 180 meV. The inverted perovskite has a very different phonon dispersion: in TiHMg₃ the H-modes are lower in energy and are more dispersive, almost touching the low-energy Ti–Mg modes, and contribute significantly to the binding of the Cooper pairs.

Values of ω_{log} for the normal perovskites are not particularly large and are found in the range of 40–60 meV. This is however compensated by rather large values of λ that can reach 1.70 for KInH₃. In the inverted perovskite, the situation is similar, but with even lower values of ω_{log} . Finally, we would like to mention Al₄H, a material proposed in Ref. [28] where Al occupies both the 1b and 3d Wyckoff positions of the cubic perovskite structure.

2.3. Double Perovskites

In view of the number of normal perovskites we found, it is not surprising that several double perovskite systems (see Figure 1c) also appeared in our survey. From Table 1 we see that the 8c position (the counterpart of the 1a position of the ternary perovskites) is mostly occupied by an alkali (with the exception of Pb₂CuRuH₆), while the 4a and 4b positions include two cations, often combining a SM with a TM. Of course, the quaternary system allows for a much larger number of chemical compositions than the ternary one.

To our knowledge, there are no experimentally synthesized hydride double perovskites. However, these systems have been proposed theoretically as high-temperature ferromagnetic

semiconductors^[40] and the effect of strain on the hydrogen storage characteristics in K_2NaAlH_6 has been studied in Ref. [41].

What is perhaps surprising is the diversity of electronic band structures and of Fermi surfaces for the double perovskites of Table 1. In all cases with an alkali in 8c position, these atoms are fully ionized and do not contribute to the density of states at the Fermi level. The Fermi level, instead, contains states of H and of the cations in positions 4a and 4b. The chemical diversity of these ions, with some having *d* states and others not, leads to different band structures close to the Fermi level. From this we can conclude that the detailed shape of the Fermi surface or the Fermi velocity are not determinant factors for the superconducting properties of double perovskite hydrides, but only the contribution of H to the density of states at the Fermi level.^[42] The same holds true for the phonon band structure. Although the cations in the 4a and 4b positions are normally responsible for the acoustic and low-lying optical modes, the higher-lying optical modes show a variety of dispersions and frequencies. The highest optical mode is usually in the range of 135–175 K.

We can see from Table 1 that values of λ are between 0.7–1.25, while ω_{\log} is between 250 and 875 K. These compounds show extremely well that the highest T_c is obtained through the synergy between λ and ω_{\log} , and not by extreme values of either quantity. We emphasize that in none of the normal, inverted, or double perovskites we encounter any rotation or tilting of the octahedra that are so common in oxide perovskites.

2.4. Other Compounds

From the compounds in Table 2, the one with the highest predicted T_c is Be_8H . This material, proposed as a high-temperature superconductor in Ref. [43] is composed by double triangular layers of Be intercalated with triangular layers of H. It has a complicated band structure, with different bands crossing the Fermi energy. Interestingly, the large value of $\lambda = 1.34$ is mainly due to the lowest-lying optical modes of Be, although with a non-negligible contribution of the three high-frequency modes composed mostly of H vibrations.

We then encounter four closely related systems, specifically $Mg_2\{Sr, Ba\}\{Pt, Pd\}H_8$ with predicted transition temperatures of ≈ 49 K (for the Sr compounds) and 40 K for the Ba compounds. These crystallize on a trigonal phase with alternating layers of $Mg_2\{Pt, Pd\}H_6$ and $\{Sr, Ba\}H_2$. We find two bands crossing the Fermi surface, with one of the crossings (at the H point) exactly at the Fermi energy. Due to the difference in atomic masses, the phonon frequencies are well separated, with the acoustic and lowest-lying optical branches with $\{Sr, Ba\}$ and $\{Pt, Pd\}$ character, followed by modes with mostly Mg character. Finally, the H vibrations form two separated manifolds at higher energy spanning frequencies from 40 to 140 meV. The electron-phonon coupling constants for these materials are $\approx \lambda = 1$, but ω_{\log} has large values of ≈ 600 –650 K.

With transition temperatures between 20 and 44 K we find a series of systems with similar chemistry, specifically with compositions involving one light alkali metal (Li or Na) and one noble metal (Au or Pd, see examples in Figure 1d–f). The one with the highest transition temperature is Na_2AuH_4 , a tetragonal compound with alternating layers of Na and AuH_4 . In the latter com-

pound, the H atoms form the vertices of isolated squares aligned with the direction of the layer, with the Au atoms at the center of the squares. There are two bands crossing the Fermi surface, with a Dirac band crossing at the Fermi energy at a point between X and Σ . The relatively high T_c is mostly due to the electrons with the lowest-lying H-modes at ≈ 40 meV.

The next compound, $LiPdH_2$ has delafossite structure with PdH_2 layers intercalated with Li (see Figure 1d). This material, with a predicted T_c of almost 40 K has already been discussed in Ref. [44]. Next, come two Na-Pd hydrides, with very different stoichiometries, structures, and superconducting properties, but with similar T_c . The first, $NaPdH_3$, is cubic, with sharing PdH_6 octahedra tilted with respect to each other, with all H atoms shared between two octahedra. The second, $Na_3Pd_2H_9$ has aligned PdH_6 octahedra that form chains through the sharing of two H per octahedron (see Figure 1e). These two compounds exhibit very different band structures: the first has many bands crossing the Fermi surface, leading to a complicated Fermi surface; the second has two bands at the Fermi level, with several crossings at, or near, the Fermi energy. Both compounds have phonons arranged in three well-separated manifolds with comparable energies, with the acoustic and low-lying optical branches with Pd–Na character, and the two higher-lying manifolds due to H-vibrations of the octahedra. Finally, Li_2AuH_2 has a very interesting structure, with AuH_2 linear units alternating with layers of Li. The values of $\lambda = 0.86$ and $\omega_{\log} = 368$ K are relatively modest for the hydrides in this list, leading to a $T_c \approx 20$ K.

The structure of Li_4BeH_5 is very interesting, with the Li atoms forming a snub-square lattice^[46] when viewed from the *c*-axis. There are two electronic bands crossing the Fermi surface, one with high Fermi velocity while the other forms a pocket around the *M*-point. The Fermi level lies on a steep shoulder of the density-of-states, suggesting the T_c could be increased by electron doping. The phonon branches contributing the most to λ are the lower-lying modes, where one sees a strong mixture of Li, Be, and H modes.

Next in Table 2 comes a series of simple transition metal hydrides with T_c in the range of 20–35 K. PdH is a well-known superconductor^[8] where anharmonic effects have a huge effect in decreasing the transition temperature.^[45] On the other hand, ZrH_3 (see Figure 1g) has been recently reported with a $T_c = 11.6$ K.^[13] We also find two indium hydrides: the rather thermodynamically unstable InH has a very simple hexagonal structure with two atoms in the unit cell. There are two very dispersive bands crossing the Fermi surface, leading to a relatively low density of states at the Fermi surface. Indium and hydrogen phonons are well separated, with the three acoustic (indium) and the first and second optical (hydrogen) branches contributing the most to λ . Finally, Zr_2HfH_8 has a curious crystal structure that has the form of a Triakis triangular tiling, with $\{Zr, Hf\}$ in the hexagonal positions when viewed from the *a*-axis. Of course, due to the similarity between Zr and Hf we can expect a certain amount of alloying in the cation positions. The Fermi surface is quite complicated, with many bands crossing the Fermi surface, and the Fermi level lies on the steep shoulder of the density of states. Most of the value of $\lambda = 1.16$ comes from the lowest manifold of phonon bands composed exclusively of Zr and Hf vibrations and from the lowest hydrogen vibrations, while the higher optical hydrogen modes couple very weakly to the electrons.

The three compounds $\{K, Rb, Cs\}BePtH_8$ have a hexagonal structure, with $BePtH_8$ layers intercalated by alkali layers (see Figure 1h). The band structure close to the Fermi level is essentially determined by the $BePtH_8$ layers. These are characteristic of an indirect band gap semiconductor with heavy holes and light electrons. The extra electron donated by the alkali atom half-fills the conduction band leading to a metallic ground-state. The strong electron–phonon coupling constants $\lambda = 1.07$ – 1.27 are mainly due to vibrations of the heavy atoms and the lowest-lying hybridized Be–H modes. We also see that ω_{log} is basically independent of the alkali, while λ decreases going from K to Cs, leading to a decrease of T_c .

Finally, we find three systems, Li_2CuGaH_6 , K_2AgCdH_6 , and Na_2PdIrH_6 with similar chemical compositions, but different crystal structures and electronic and phononic band structures. In spite of this, they all have similar values of λ and ω_{log} , leading to T_c between 23 and 37 K.

2.5. Statistical Analysis

These examples show that there is not a unique or simple recipe linked to strong superconductivity in hydrides at ambient pressures. However, we can see some patterns from a statistical analysis of our dataset. In Figure 2a we analyze the correlation between the thermodynamic stability and T_c . This figure is obtained by grouping the materials according to their energy from the hull and, for each group, computing the histogram of T_c values (i.e., the number of materials in the figure is normalized column-wise). The figure shows that, while there is not a direct proportionality between T_c and thermodynamic stability, the chance of finding high T_c outliers increases significantly with the distance from the hull. We identify two regions (separated by a dashed line): a high T_c zone where materials are rare (“[1]” in the Figure) and a low- T_c zone with a high density of materials (“[2]” in Figure). Ideally we would be interested in high T_c stable materials, but this set appears to be rather empty. Therefore the sparse region of high stability and high T_c is the most promising search domain.

A second aspect that emerges from our analysis is the complex relation between hydrogen and superconductivity. As shown in Figure 2c there is a correlation between high hydrogen content at the Fermi level (as measured by computing the H fraction of the density of states) and T_c . High hydrogen content is linked (as it should be)^[3,42] to higher values of T_c (region “[1]” in Figure 2c. Unfortunately, the high hydrogen content also correlates with thermodynamic instability. As shown in Figure 2b, by increasing the H content the center of mass of the material distribution shifts toward higher energy (region “[1]” of the plot). Note that the data are normalized row-wise. From this figure it is clear that the region of interest is in materials for which the Fermi density of states is dominated by the host chemical composition and the H contribution is less than 50% of the total. This region is indicated by the label “[2]” in Figure 2b,c.

2.6. Analysis of Selected Hydrides

Among the superconducting hydrides predicted in our high-throughput search we have selected a small set of compounds

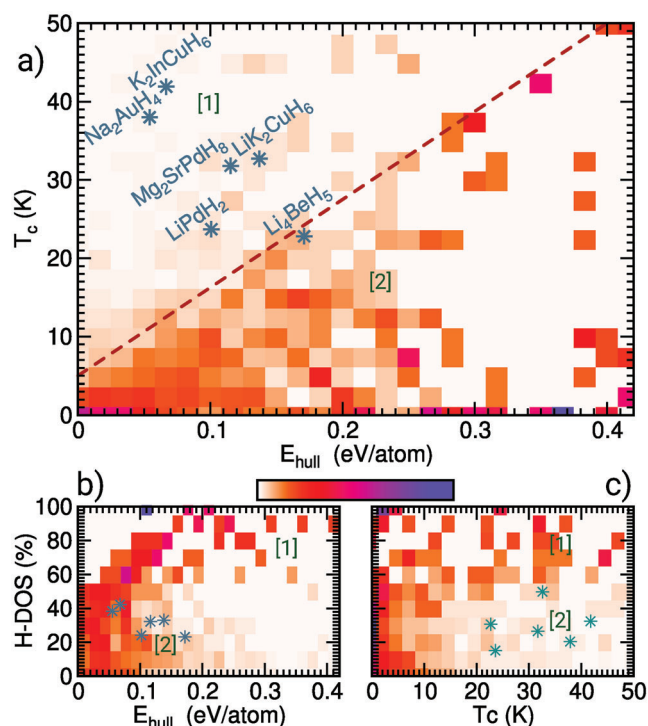


Figure 2. Analysis of superconducting hydrides: a) Histogram of T_c as a function of the distance to the convex hull. The dashed line is a guide to the eye marking a threshold in critical temperature separating high from low probability regions. The histogram is normalized column-wise and a color-bar (white to blue) indicates the normalized histogram height. b) Relation between the distance to the convex hull and the hydrogen contribution to the density of states at the Fermi level. c) Relation between T_c and the hydrogen contribution to the density of states at the Fermi level. The histograms in (b) and (c) are normalized row-wise. Stars show some of the materials discussed in Section 2.6.

and investigated these with higher accuracy and in further detail. There are two main problems we want to address here: 1) The high density of states at the Fermi level of these compounds, and the fact that the Fermi level is often at a steep shoulder or a peak, which makes the convergence with respect to smearing and k -points very complicated. 2) The replacement of the Coulomb interaction by the number μ^* that is given a rather arbitrary value (usually ≈ 0.10) is hardly justified for many of the high T_c hydrides.^[47–49] Instead, the full energy dependence of the Coulomb term should be maintained in the calculation of the superconducting properties.

The list of compounds that we selected, together with some of their properties are collected in Table 3, which includes four materials Mg_2XH_6 with $X = Rh, Pd, Ir, Pt$ already discussed in Ref. [23]. These are outlier materials with respect to the general trends discussed in the previous section, close to the hull of stability and with high T_c . First, we observe that the calculated T_c s reported in Table 3 are in most cases lower than that listed in Table 1 and Table 2. In some cases, such as $LiPdH_2$ and Mg_2SrPdH_8 , the difference is related to changes in the estimated e-ph coupling parameters (owing to the increased numerical accuracy), however, in most of the cases the e-ph coupling is confirmed and the lower T_c stems from a strong Coulomb repulsion, which here we compute from first principles.

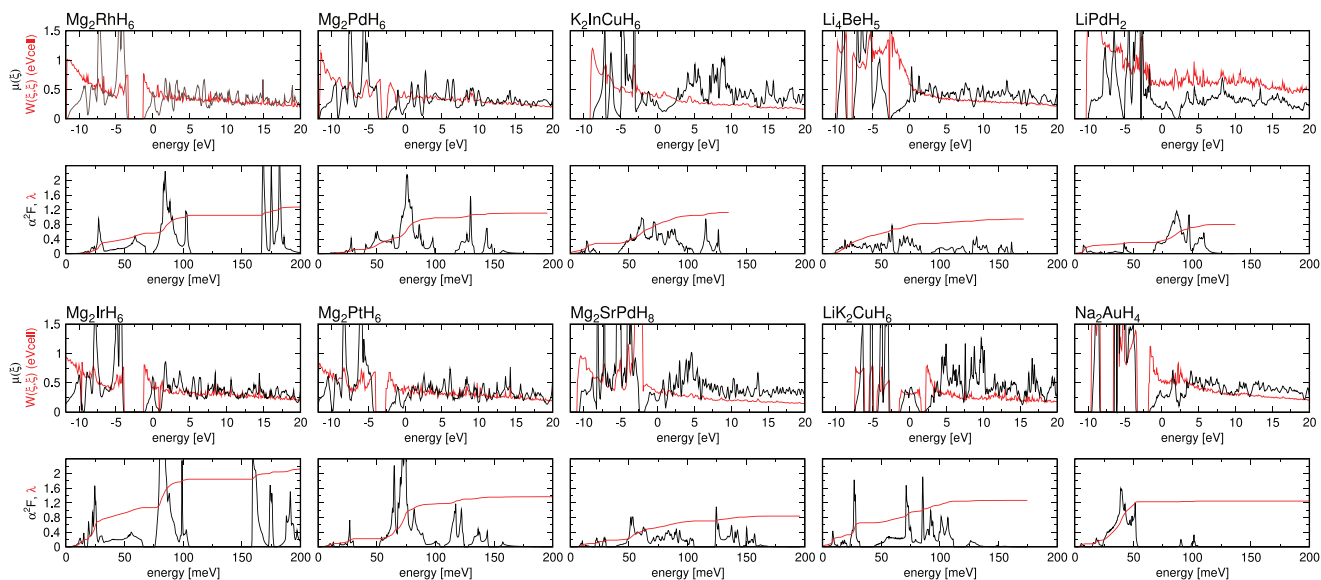


Figure 3. Coupling parameters entering the isotropic Eliashberg equations.^[53,54] The quantity $W(\xi, \xi')$ is the Coulomb interaction computed in the random phase approximation, $\mu(\xi) := W(\xi, \xi)N(\xi)$ is the product of W and the density of electronic states. Finally, $\alpha^2F(\omega)$ is the Eliashberg electron–phonon function, $\lambda(\omega) := 2 \int_0^\omega \frac{\alpha^2F(\omega')}{\omega'} d\omega'$ is the coupling integration curve.^[49] The colors of the plotted lines in each panel correspond to the labels on the vertical axes.

Table 3. Electron–phonon coupling constant λ , logarithmic average of the phonon frequencies ω_{\log} (in K), density of states at the Fermi level N_F (in $(\text{eV cell})^{-1}$), the H content at the Fermi level (%), the Coulomb potential μ , transition temperatures T_c (in K) and superconducting gaps Δ (in meV) for the twelve compounds reported here. Calculations were performed with the isotropic Eliashberg equations including full ab initio Coulomb interactions.

	λ	ω_{\log}	N_F	H%	μ	T_c	Δ
Mg ₂ RhH ₆	1.3	766	2.32	18.4	0.45	48.5	8.4
Mg ₂ PdH ₆	1.1	754	0.80	28.3	0.17	66.5	11.2
Mg ₂ IrH ₆	2.13	581	2.90	15.2	0.58	77.0	16.3
Mg ₂ PtH ₆	1.4	696	1.03	22.6	0.20	80.4	15.0
K ₂ InCuH ₆	1.14	448	1.38	32.2	0.26	41.9	7.0
K ₂ LiCuH ₆	1.28	354	2.34	49.6	0.35	32.7	5.6
Mg ₂ SrPdH ₈	0.84	608	1.10	26.3	0.19	31.8	5.1
Na ₂ AuH ₄	1.28	391	1.09	20.2	0.27	38.0	6.6
LiPdH ₂	0.80	454	0.53	14.9	0.16	23.7	3.8
Li ₄ BeH ₅	0.95	460	1.05	30.4	0.31	22.8	3.7

The hydrogen contribution to the pairing is evident from the phonon band structure and electron–phonon coupling functions reported in **Figure 3**. In fact, more than 50% of the integrated coupling constant λ originates from pure-hydrogen phonon modes, which as we discussed above, tend to be well separated from the vibrational modes of the host elements. The only exception to this is Li₄BeH₅, where we see a low-energy region of mix-modes. In stable materials at low pressure hydrogen bonds are usually completely saturated, therefore hydrogen modes have no coupling with states at the Fermi level. What makes these hydrides quite special is that hydrogen states contribute significantly to the

Fermi density of states (of the order of 25% according to atomic projections), furthermore they are not localized but strongly overlapping and hybridizing with the states of the host similar to what occurs in high-pressure superconducting hydrides.^[49]

The screened coulomb interaction W (red curves in the panels in the first and third rows of **Figure 3**) is computed in the random phase approximation which is expected to be quite accurate for this class of materials.^[50] The diagonal part of the W -function is relatively featureless, showing a nearly monotonous decrease with the band energy. This behavior, reminiscent of free electron systems, indicates that electronic states are well-screened.^[50,51] However, the strength and effectiveness of the Coulomb repulsion is strongly affected by the density of states which shows a complex material dependence. The most peculiar cases are the Mg₂IrH₆ and Mg₂RhH₆ systems where the Fermi level is pinned to a peak in the density of states, leading to a complicated (and quite poor) Coulomb renormalization mechanism.^[52] To a lesser extent a peak in the density of states also causes LiK₂CuH₆ to be characterized by a strong Coulomb repulsion. The other materials in the set are less problematic.

3. Conclusion

We presented a machine-learning-assisted approach to search for superconducting hydrides under ambient pressure within an extensive dataset comprising over 150 000 compounds. Our investigation yielded ≈ 50 systems with transition temperatures surpassing 20 K, and reaching above 70 K. These systems have a large variety of crystal structures and geometrical characteristics. However, we find a consistent chemical composition in the majority of these systems, which combines alkali or alkali-earth elements with noble metals.

On the downside, we observe that most of the systems we find, while being dynamically stable, are not on the hull of thermodynamic stability (while being close to it). This points to the fact that the experimental synthesis of our predicted compounds may require conditions beyond ambient equilibrium and skilled material engineering strategies.

A statistical analysis of our predictions, as well as in-depth theoretical characterization for a set of selected materials, provide a reasonably clear picture of the superconducting mechanism in hydrides at room pressure. The crucial aspect is that hydrogen states are present at the Fermi level, strongly hybridized with those of the host. These are delocalized (non-molecular) metallic states that are well screened and lead to large values of the density of states. In this situation, both medium or high-energy hydrogen phonon modes and low-energy host modes contribute to the coupling λ . The final value of T_c is a complex interplay of a large density of states, correct phonon energies, high hydrogen contribution to the Fermi density of states and low Coulomb repulsion. In a statistical sense, we observe that there is a direct correlation between low thermodynamic stability, high hydrogen content and high T_c . This observation suggests a promising avenue for future experimental investigations into high-temperature superconductivity within hydrides at ambient pressure.

4. Computational Methods

All density-functional perturbation theory calculations were performed using versions 6.8 and 7.1 of QUANTUM ESPRESSO^[55,56] with the Perdew–Burke–Ernzerhof (PBE) for solids (PBEsol)^[57] generalized gradient approximation.

Geometry optimizations were performed using uniform Γ -centered k -point grids with a density of 3000 k -points per reciprocal atom. If this resulted in an odd number of k -points in a given direction, the next even number was used instead. Convergence thresholds for energies, forces and stresses were set to 1×10^{-8} a.u., 1×10^{-6} a.u., and 5×10^{-2} kbar, respectively. For the electron–phonon coupling, a double-grid technique was employed with the k -grid used in the lattice optimization doubled in every direction as the coarse grid, and a k -grid quadrupled in each direction as the fine grid. For the q -sampling of the phonons, half of the k -point grid described above was used. The double δ -integration to obtain the Eliashberg function was performed with a Methfessel-Paxton smearing of 0.05 Ry.

Distances to the convex hull were computed using the PBEsol approximation.^[57] All pertinent materials available in the Alexandria database^[26,58] were considered and they were re-optimized following Ref. [59]. This set of materials included most of the experimentally known hydrides present in the Inorganic Crystal Structure Database,^[60] as well as many theoretical phases. Most of the theoretical phases were constructed by analogy, substituting the metals in known hydride structures with other “similar” chemical elements. The chemical element substitutions were suggested either by a similarity scale^[61] or by using machine learning models.^[26] It was noted that this dataset, together with the rest of Alexandria, can be freely accessed through an opti-made interface.^[62] The convex hull of Alexandria included ≈ 120 000 compounds, and was by far the largest freely available. However, as the complete hull was not known, the calculated distances to the convex hull should be regarded as a lower limit.

For the machine learning part, the ALIGNN^[63] model was trained using as targets, simultaneously, λ , ω_{\log} and T_c with the error for each property weighted equally, as these are the choices yielding the best results. The default hyperparameters were used. The final models can be downloaded from <https://github.com/hyllios/utlis/tree/main/models>.

A few superconductivity simulations were performed with isotropic Eliashberg theory^[53,54] including full ab initio Coulomb interactions. The Eliashberg α^2F function was computed using QUANTUM ESPRESSO^[55,56] and density functional perturbation theory.^[64,65] A converged momentum integration was performed by mapping the calculated electron–phonon matrix elements to a random set of 60 000 k -points accumulated on the Fermi surface.^[66,67] All calculations were done using PBEsol pseudo potentials from the strict set of PseudoDojo^[68] and a 100 Ry energy cutoff for the planewave expansion. A $16^3(8^3)$ k -grid(q -grid) was used for the zone sampling in calculating the dynamical matrices of Mg_2XH_6 and LiPdH_2 , a $12^3(6^3)$ k -grid(q -grid) was used for the other systems in Table 3. Screening was computed^[69] in the random phase approximation which was expected to be sufficiently accurate for this class of materials.^[50] The response function was calculated with a G -vector cutoff of three atomic units and an energy window of two Hartrees. The k -grids for momentum integration of the Coulomb interaction converged to 10% in the value of μ , and ranged from 5^3 in $\text{Mg}_2\text{SrPdH}_8$ to 12^3 in LiPdH_2 .

To verify the kinetic stability, NpT simulations were performed using vasp. Supercells with 270 atoms were used, obtained using the FIND_OPTIMAL_CELL_SHAPE routine from ASE.^[70] The system was first thermalized during 2000 steps, during which the temperature was increased linearly from 0 to 150 K. Then 5000 steps were performed at constant temperature. The time step was set to 1 fs, and Langevin dynamics were used to model the thermostat and the barostat. For consistency, the PBEsol approximation was used for the exchange–correlation functional.

Supporting Information

Supporting Information is available from the Wiley Online Library or from the author.

Acknowledgements

T.F.T.C. acknowledges financial support from FCT - Fundação para a Ciência e Tecnologia, I.P. through the projects UIDB/04564/2020, UIDP/04564/2020 and CEECINST/00152/2018/CP1570/CT0006, with DOI identifiers 10.54499/UIDB/04564/2020, 10.54499/UIDP/04564/2020, and 10.54499/CEECINST/00152/2018/CP1570/CT0006, respectively. Computational resources provided by UC-LCA, funded by FCT I.P. under the project Advanced Computing Project 2022.15822.CPCA. M.A.L.M. acknowledges partial funding from Horizon Europe MSCA Doctoral network grant n.101073486, EUSpeclab, funded by the European Union, and from the Keele Foundation through the SuperC collaboration. Y.-W.F. and I.E. received funding from the European Research Council (ERC) under the European Union’s Horizon 2020 research and innovation programme (Grant Agreement No. 802533) and acknowledge PRACE for awarding access to the EuroHPC supercomputer LUMI located in CSC’s data center in Kajaani, Finland through EuroHPC Joint Undertaking (EHPC-REG-2022R03-090). I.E. also acknowledges funding from the Spanish Ministry of Science and Innovation (Grant No. PID2022-142861NA-I00) and the Department of Education, Universities

and Research of the Basque Government and the University of the Basque Country (Grant No. IT1527-22). The authors acknowledge enlightening discussions with the partners of the SuperC collaboration.

Open access funding enabled and organized by Projekt DEAL.

Conflict of Interest

The authors declare no conflict of interest.

Author Contributions

T.F.T.C. and M.A.L.M. performed the machine learning prediction and the preliminary analysis of the superconducting properties. A.S. performed the statistical analysis and the analysis of selected hydrides. All authors contributed to designing the research, interpreting the results, and writing of the manuscript.

Data Availability Statement

The data that support the findings of this study are available in the supplementary material of this article.

Received: March 6, 2024

Revised: May 17, 2024

Published online:

- [1] L. Gao, Y. Y. Xue, F. Chen, Q. Xiong, R. L. Meng, D. Ramirez, C. W. Chu, J. H. Eggert, H. K. Mao, *Phys. Rev. B* **1994**, *50*, 4260.
- [2] J. Nagamatsu, N. Nakagawa, T. Muranaka, Y. Zenitani, J. Akimitsu, *Nature* **2001**, *410*, 63.
- [3] N. W. Ashcroft, *Phys. Rev. Lett.* **2004**, *92*, 187002.
- [4] M. Somayazulu, M. Ahart, A. K. Mishra, Z. M. Geballe, M. Baldini, Y. Meng, V. V. Struzhkin, R. J. Hemley, *Phys. Rev. Lett.* **2019**, *122*, 027001.
- [5] A. P. Drozdov, P. P. Kong, V. S. Minkov, S. P. Besedin, M. A. Kuzovnikov, S. Mozaffari, L. Balicas, F. F. Balakirev, D. E. Graf, V. B. Prakapenka, E. Greenberg, D. A. Knyazev, M. Tkacz, M. I. Erements, *Nature* **2019**, *569*, 528.
- [6] L. Ma, K. Wang, Y. Xie, X. Yang, Y. Wang, M. Zhou, H. Liu, X. Yu, Y. Zhao, H. Wang, G. Liu, Y. Ma, *Phys. Rev. Lett.* **2022**, *128*, 167001.
- [7] P. Kong, V. S. Minkov, M. A. Kuzovnikov, A. P. Drozdov, S. P. Besedin, S. Mozaffari, L. Balicas, F. F. Balakirev, V. B. Prakapenka, S. Chariton, D. A. Knyazev, E. Greenberg, M. I. Erements, *Nat. Commun.* **2021**, *12*, 1175.
- [8] B. Stritzker, W. Buckel, *Z. Phys. A: Hadrons Nucl.* **1972**, *257*, 1.
- [9] A. I. Kolesnikov, A. M. Balagurov, I. O. Bashkin, V. K. Fedotov, V. Y. Malyshev, G. M. Mironova, E. G. Pomyatovskiy, *J. Phys.: Condens. Matter* **1993**, *5*, 5045.
- [10] V. E. Antonov, I. T. Belash, O. V. Zharikov, A. I. Latynin, A. V. Pal'nichenko, *Fiz. Tverd. Tela* **1988**, *30*, 598.
- [11] C. B. Satterthwaite, I. L. Toepke, *Phys. Rev. Lett.* **1970**, *25*, 741.
- [12] J. M. Welter, F. J. Johnen, *Z. Physik B* **1977**, *27*, 227.
- [13] M. A. Kuzovnikov, V. E. Antonov, V. I. Kulakov, V. D. Muzalevsky, N. S. Orlov, A. V. Palnichenko, Y. M. Shulga, *Phys. Rev. Mater.* **2023**, *7*, 024803.
- [14] D. Wang, Y. Ding, H.-K. Mao, *Materials* **2021**, *14*, 7563.
- [15] L. Boeri, R. Hennig, P. Hirschfeld, G. Profeta, A. Sanna, E. Zurek, W. E. Pickett, M. Amsler, R. Dias, M. I. Erements, C. Heil, R. J. Hemley, H. Liu, Y. Ma, C. Pierleoni, A. N. Kolmogorov, N. Rybin, D. Novoselov, V. Anisimov, A. R. Oganov, C. J. Pickard, T. Bi, R. Arita, I. Errea, C. Pellegrini, R. Requist, E. K. U. Gross, E. R. Margine, S. R. Xie, Y. Quan, et al., *J. Phys.: Condens. Matter* **2022**, *34*, 183002.
- [16] P. Duffer, D. M. Gualtieri, V. U. S. Rao, *Phys. Rev. Lett.* **1976**, *37*, 1410.
- [17] B. Stritzker, *Z. Physik* **1974**, *268*, 261.
- [18] R. Lucrezi, E. Kogler, S. Di Cataldo, M. Aichhorn, L. Boeri, C. Heil, *Commun. Phys.* **2023**, *6*, 73.
- [19] Y.-W. Fang, Đ. Dangić, I. Errea, *Commun. Mater.* **2024**, *5*, 61.
- [20] M. Gao, P.-J. Guo, H.-C. Yang, X.-W. Yan, F. Ma, Z.-Y. Lu, T. Xiang, H.-Q. Lin, *Phys. Rev. B* **2023**, *107*, 180501.
- [21] K. Choudhary, K. Garrity, *npj Comput. Mater.* **2022**, *8*, 244.
- [22] C. Tian, Y. He, Y. Zhu, J. Du, S. Liu, W. Guo, H. Zhong, J. Lu, X. Wang, J. Shi, *Adv. Funct. Mater.* **2023**, *34*, 2304919.
- [23] A. Sanna, T. F. T. Cerqueira, Y.-W. Fang, I. Errea, A. Ludwig, M. A. L. Marques, *npj Comput. Mater.* **2024**, *10*, 44.
- [24] K. Dolui, L. J. Conway, C. Heil, T. A. Strobel, R. Prasankumar, C. J. Pickard, *Phys. Rev. Lett.* **2024**, *132*, 166001.
- [25] J. Schmidt, N. Hoffmann, H.-C. Wang, P. Borlido, P. J. M. A. Carriço, T. F. T. Cerqueira, S. Botti, M. A. L. Marques, *Adv. Mater.* **2023**, *35*, 2210788.
- [26] J. Schmidt, L. Pettersson, C. Verdozzi, S. Botti, M. A. L. Marques, *Sci. Adv.* **2021**, *7*, 7948.
- [27] F. Zheng, Z. Zhang, S. Wu, Q. Lin, R. Wang, Y. Fang, C.-Z. Wang, V. Antropov, Y. Sun, K.-M. Ho, *Mater. Today Phys.* **2024**, *42*, 101374.
- [28] Y. He, J. Lu, X. Wang, J. jie Shi, *Phys. Rev. B* **2023**, *108*, 054515.
- [29] M. Kritikos, D. Nore'us, *J. Solid State Chem.* **1991**, *93*, 256.
- [30] B. Huang, F. Bonhomme, P. Selvam, K. Yvon, P. Fischer, *J. Less Common Met.* **1991**, *171*, 301.
- [31] This nomenclature is relative to the band structure of the parent, semiconducting, compound.
- [32] K. Ikeda, T. Sato, S.-i. Orimo, *Int. J. Mater. Res.* **2008**, *99*, 471.
- [33] A. W. Overhauser, *Phys. Rev. B* **1987**, *35*, 411.
- [34] C. E. Messer, J. C. Eastman, R. G. Mers, A. J. Maeland, *Inorg. Chem.* **1964**, *3*, 776.
- [35] A. J. Maeland, W. D. Lahar, *Z. Phys. Chem.* **1993**, *179*, 181.
- [36] A. Kamegawa, T. Abiko, M. Okada, *Mater. Sci. Forum* **2014**, *783–786*, 1686.
- [37] W. Bronger, G. Ridder, *J. Alloys Compd.* **1994**, *210*, 53.
- [38] S. Gao, T. Broux, S. Fujii, C. Tassel, K. Yamamoto, Y. Xiao, I. Oikawa, H. Takamura, H. Ubukata, Y. Watanabe, K. Fujii, M. Yashima, A. Kuwabara, Y. Uchimoto, H. Kageyama, *Nat. Commun.* **2021**, *12*, 201.
- [39] H. Kohlmann, *J. Solid State Chem.* **2010**, *183*, 367.
- [40] C. Jia, X. Li, Q. Li, J. Yang, *Phys. Rev. B* **2023**, *107*, L140404.
- [41] M. Baaddi, R. Chami, O. Baalla, S. E. Quaoubi, A. Saadi, L. E. H. Omari, M. Chafi, *Environ. Sci. Pollut. Res.* **2023**.
- [42] F. Belli, T. Novoa, J. Contreras-García, I. Errea, *Nat. Commun.* **2021**, *12*, 5381.
- [43] Y. He, J. jie Shi, *Nano Lett.* **2023**, *23*, 8126.
- [44] T. F. T. Cerqueira, A. Sanna, M. A. L. Marques, *Adv. Mater.* **2024**, *36*, 2307085.
- [45] I. Errea, M. Calandra, F. Mauri, *Phys. Rev. Lett.* **2013**, *111*, 177002.
- [46] H.-C. Wang, A. W. Huran, M. A. L. Marques, M. Nalabothula, L. Wirtz, Z. Romestan, A. H. Romero, *J. Phys. Chem. Lett.* **2023**, *14*, 9969.
- [47] J. A. Flores-Livas, A. Sanna, E. K. U. Gross, *Eur. Phys. J. B* **2016**, *89*, 363.
- [48] R. Akashi, M. Kawamura, S. Tsuneyuki, Y. Nomura, R. Arita, *Phys. Rev. B* **2015**, *91*, 224513.
- [49] J. A. Flores-Livas, L. Boeri, A. Sanna, G. Profeta, R. Arita, M. Erements, *Phys. Rep.* **2020**, *856*, 1.
- [50] C. Pellegrini, C. Kukkonen, A. Sanna, *Phys. Rev. B* **2023**, *108*, 064511.
- [51] S. Massidda, F. Bernardini, C. Bersier, A. Continenza, P. Cudazzo, A. Floris, H. Glawe, M. Monni, S. Pittalis, G. Profeta, A. Sanna, S. Sharma, E. K. U. Gross, *Supercond. Sci. Technol.* **2009**, *22*, 034006.
- [52] D. J. Scalapino, J. R. Schrieffer, J. W. Wilkins, *Phys. Rev.* **1966**, *148*, 263.
- [53] C. Pellegrini, R. Heid, A. Sanna, *J. Phys. Mater.* **2022**, *5*, 024007.
- [54] A. Davydov, A. Sanna, C. Pellegrini, J. K. Dewhurst, S. Sharma, E. K. U. Gross, *Phys. Rev. B* **2020**, *102*, 214508.

- [55] P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, A. D. Corso, S. de Gironcoli, S. Fabris, G. Fratesi, R. Gebauer, U. Gerstmann, C. Gougoussis, A. Kokalj, M. Lazzeri, L. Martin-Samos, N. Marzari, F. Mauri, R. Mazzarello, S. Paolini, A. Pasquarello, L. Paulatto, C. Sbraccia, S. Scandolo, G. Sclauzero, A. P. Seitsonen, et al., *J. Phys.: Condens. Matter* **2009**, *21*, 395502.
- [56] P. Giannozzi, O. Andreussi, T. Brumme, O. Bunau, M. B. Nardelli, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, M. Cococcioni, N. Colonna, I. Carnimeo, A. D. Corso, S. de Gironcoli, P. Delugas, R. A. DiStasio, A. Ferretti, A. Floris, G. Fratesi, G. Fugallo, R. Gebauer, U. Gerstmann, F. Giustino, T. Gorni, J. Jia, M. Kawamura, H.-Y. Ko, A. Kokalj, E. Küçükbenli, M. Lazzeri, et al., *J. Phys.: Condens. Matter* **2017**, *29*, 465901.
- [57] J. P. Perdew, A. Ruzsinszky, G. I. Csonka, O. A. Vydrov, G. E. Scuseria, L. A. Constantin, X. Zhou, K. Burke, *Phys. Rev. Lett.* **2008**, *100*, 136406.
- [58] J. Schmidt, N. Hoffmann, H.-C. Wang, P. Borlido, P. J. M. A. Carrião, T. F. T. Cerqueira, S. Botti, M. A. L. Marques, *Adv. Mater.* **2023**, *35*, 2210788.
- [59] J. Schmidt, H.-C. Wang, T. F. T. Cerqueira, S. Botti, M. A. L. Marques, *Sci. Data* **2022**, *9*, 64.
- [60] D. Zagorac, H. Müller, S. Rühl, J. Zagorac, S. Rehme, *J. Appl. Crystallogr.* **2019**, *52*, 918.
- [61] H. Glawe, A. Sanna, E. K. U. Gross, M. A. L. Marques, *New J. Phys.* **2016**, *18*, 093011.
- [62] M. Evans, J. Bergsma, A. Merkys, C. Andersen, O. B. Andersson, D. Beltrán, E. Blokhin, T. M. Boland, R. Castañeda Balderas, K. Choudhary, A. Díaz Díaz, R. Domínguez García, H. Eckert, K. Eimre, M. E. Fuentes-Montero, A. M. Krajewski, J. J. Mortensen, J. M. Nápoles-Duarte, J. Pietryga, J. Qi, F. d. J. Trejo Carrillo, A. Vaitkus, J. Yu, A. Zettl, P. B. de Castro, J. M. Carlsson, T. F. T. Cerqueira, S. Divilov, H. Hajiyani, F. Hanke, et al., *Digital Discovery* **2024**.
- [63] K. Choudhary, B. DeCost, *npj Comput. Mater.* **2021**, *7*, 185.
- [64] S. Baroni, S. de Gironcoli, A. Dal Corso, P. Giannozzi, *Rev. Mod. Phys.* **2001**, *73*, 515.
- [65] S. Baroni, P. Giannozzi, A. Testa, *Phys. Rev. Lett.* **1987**, *58*, 1861.
- [66] A. Sanna, C. Pellegrini, E. Liebhaber, K. Rossnagel, K. J. Franke, E. K. U. Gross, *npj Quantum Mater.* **2022**, *7*, 6.
- [67] M. A. L. Marques, M. Lüders, N. N. Lathiotakis, G. Profeta, A. Floris, L. Fast, A. Continenza, E. K. U. Gross, S. Massidda, *Phys. Rev. B* **2005**, *72*, 024546.
- [68] M. van Setten, M. Giantomassi, E. Bousquet, M. Verstraete, D. Hamann, X. Gonze, G.-M. Rignanese, *Comput. Phys. Commun.* **2018**, *226*, 39.
- [69] The Elk Code, <http://elk.sourceforge.net/>.
- [70] A. H. Larsen, J. J. Mortensen, J. Blomqvist, I. E. Castelli, R. Christensen, M. Dułak, J. Friis, M. N. Groves, B. Hammer, C. Hargus, E. D. Hermes, P. C. Jennings, P. B. Jensen, J. Kermode, J. R. Kitchin, E. L. Kolsbjerg, J. Kubal, K. Kaasbjerg, S. Lysgaard, J. B. Maronsson, T. Maxson, T. Olsen, L. Pastewka, A. Peterson, C. Rostgaard, J. Schiøtz, O. Schütt, M. Strange, K. S. Thygesen, T. Vegge, et al., *J. Phys. Condens. Matter* **2017**, *29*, 273002.

ADVANCED FUNCTIONAL MATERIALS

Supporting Information

for *Adv. Funct. Mater.*, DOI 10.1002/adfm.202404043

Searching Materials Space for Hydride Superconductors at Ambient Pressure

Tiago F. T. Cerqueira, Yue-Wen Fang, Ion Errea, Antonio Sanna and Miguel A. L. Marques**

Supplementary Information for “Searching Materials Space for Hydride Superconductors at Ambient Pressure”

Tiago F. T. Cerqueira¹, Yue-Wen Fang^{2,3}, Ion Errea^{2,3,4},
Antonio Sanna^{5,*} and Miguel A. L. Marques^{6,†}

¹*CFisUC, Department of Physics, University of Coimbra, Rua Larga, 3004-516 Coimbra, Portugal*

²*Fisika Aplikatua Saila, Gipuzkoako Ingeniaritza Eskola, University of the Basque Country (UPV/EHU), Europa Plaza 1, 20018 Donostia/San Sebastián, Spain*

³*Centro de Física de Materiales (CSIC-UPV/EHU), Manuel de Lardizabal Pasealekua 5, 20018 Donostia/San Sebastián, Spain*

⁴*Donostia International Physics Center (DIPC), Manuel de Lardizabal Pasealekua 4, 20018 Donostia/San Sebastián, Spain*

⁵*Max-Planck-Institut für Mikrostrukturphysik, Weinberg 2, D-06120 Halle, Germany*

⁶*Research Center Future Energy Materials and Systems of the University Alliance Ruhr and Interdisciplinary Centre for Advanced Materials Simulation, Ruhr University Bochum, Universitätsstraße 150, D-44801 Bochum, Germany*

(Dated: May 17, 2024)

In this supplement we report on the kinetic stability of selected compounds (PART 1) and give a detailed information on crystals identified and characterized in this work (PART 2).

* sanna@mpi-halle.mpg.de

† miguel.marques@rub.de

PART 1: KINETIC STABILITY

In this section we report on the ab initio molecular dynamics (AIMD) simulations, performed to establish the kinetic stability of some selected compounds. We performed NpT simulations using VASP and the PBEsol approximation to the exchange-correlation functional. We used supercells with 270 atoms, obtained using the FIND_OPTIMAL_CELL_SHAPE routine from ASE. The systems were thermalised during 2000 steps, during which the temperature was increased linearly from 0 to 150 K. We then performed 5000 steps at a constant temperature of 150 K. The time step was set to 1 fs, and we used Langevin dynamics to model the thermostat and the barostat. In the following plots we present the results for the last 5ps of the MD simulation. The MD simulations did not show any phase transition up to 150 K.

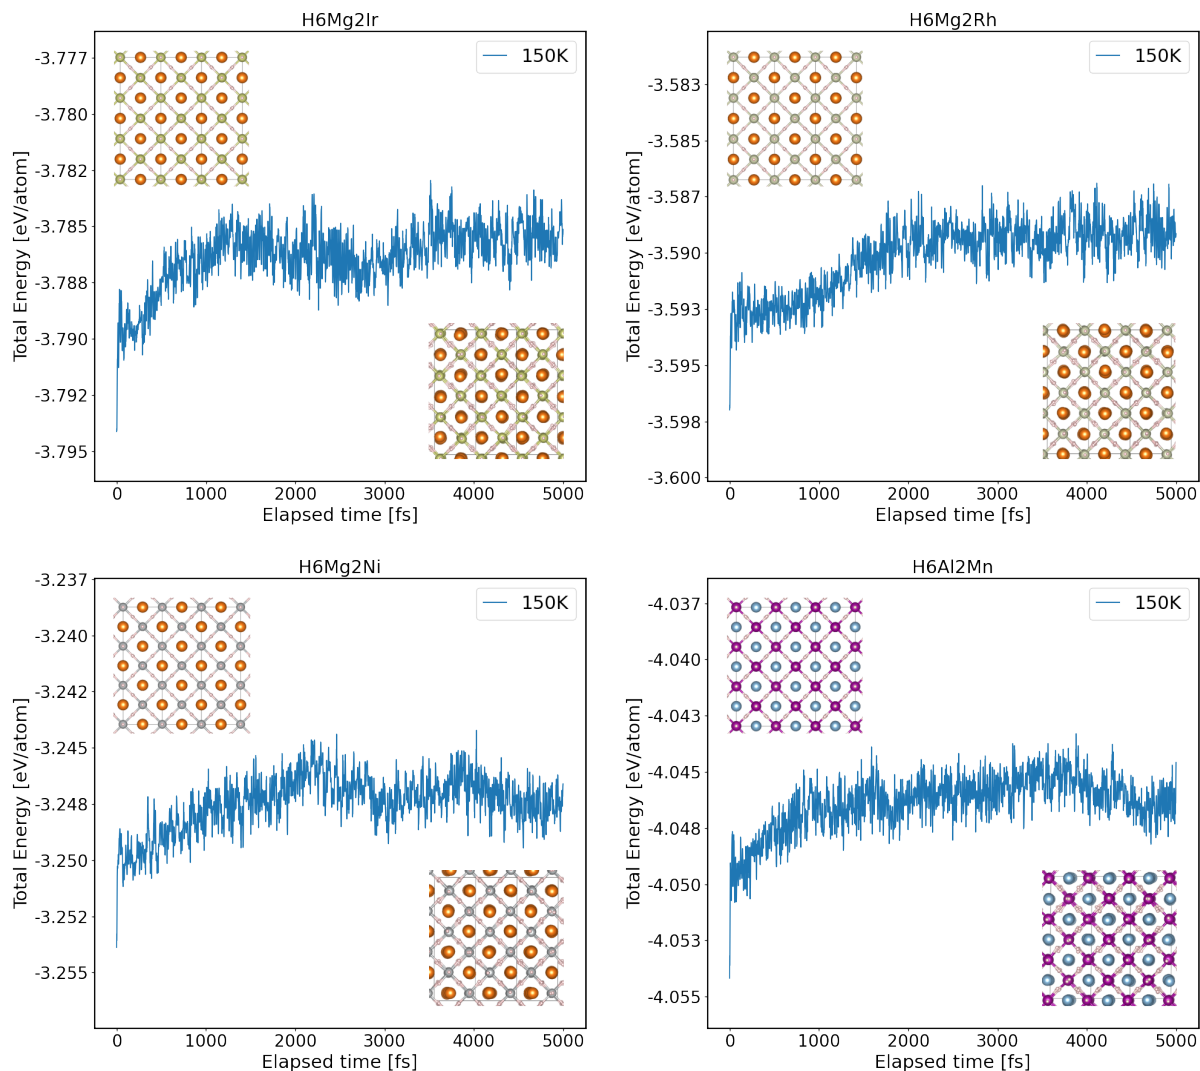


FIG. 1. Results for the ab initio molecular dynamics (AIMD) simulations at 150 K, using supercells of 30 unit cells (270 atoms). For each subplot, structures at the top left and at the bottom right represent, respectively, the structures before and after the MD.

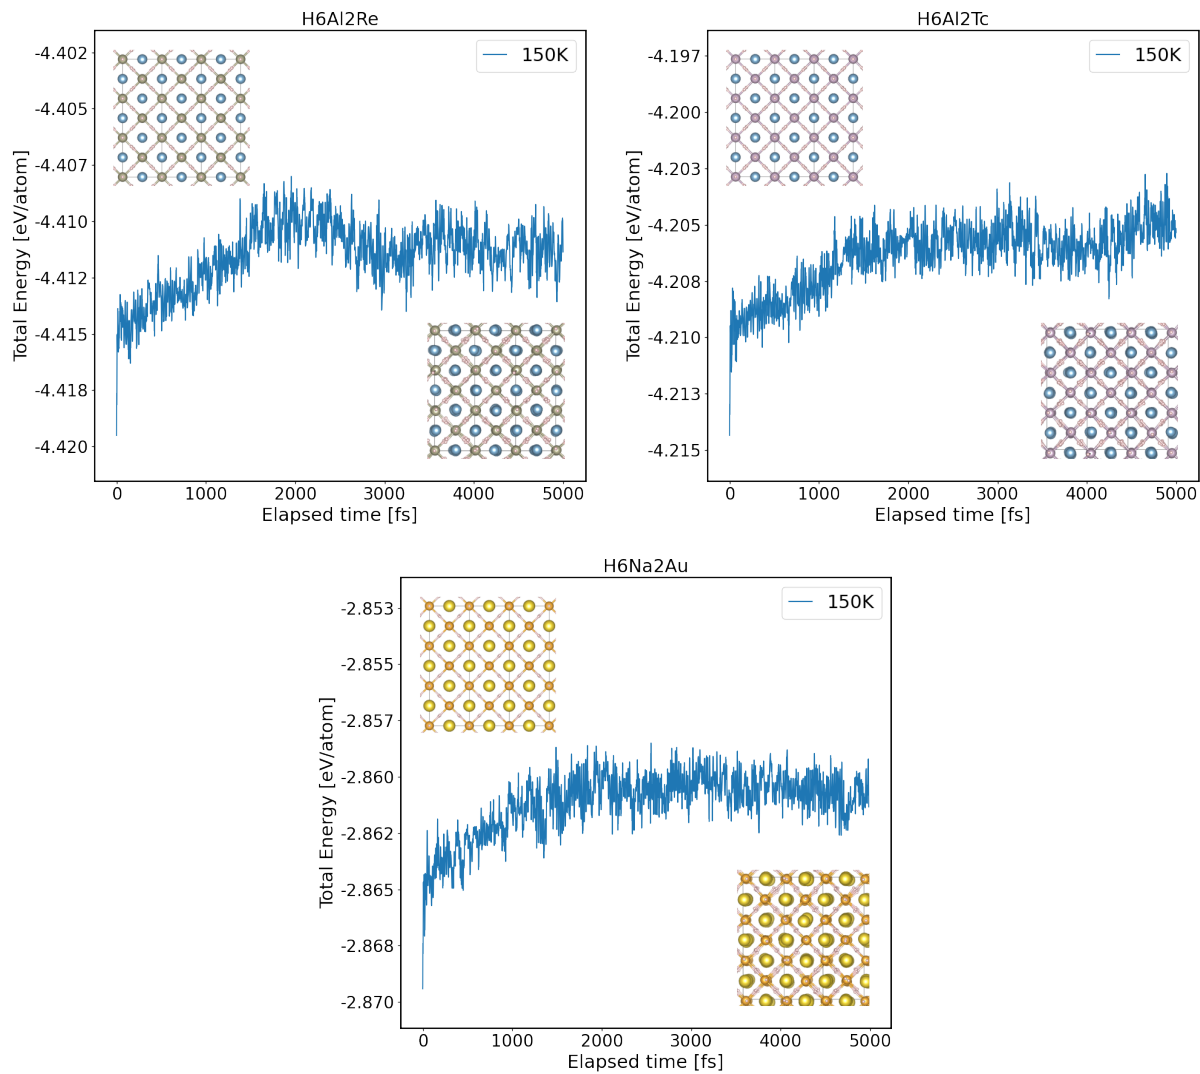


FIG. 2. Results for the ab initio molecular dynamics (AIMD) simulations at 150 K, using supercells of 30 unit cells (270 atoms). For each subplot, structures at the top left and at the bottom right represent, respectively, the structures before and after the MD.

PART 2: Extended Material Properties

In this section we provide detailed information on crystals identified and characterized in this work. The materials are listed in the same order and with the same identification number (#) as in Tab. I and II of the paper. The data includes:


- Chemical composition.
- Space group, lattice parameters and Wyckoff positions.
- Drawings of the crystal structure.
- Energy information including possible decomposition pattern.
- Computational parameters.
- Electron-phonon coupling parameters. and critical temperatures in different approximations.
- Electronic bands with total and projected density of states.
- Phonon bands with total and projected density of states and Eliashberg spectral function.

I – SM2-TM-H6

#1: Li_2CuH_6

```

mat id agm006188328
spg 225
nsites 9
e above hull 0.171 eV
e form -0.035 eV
decomposition  $\text{Li}_2\text{CuH}_3, \text{H}_2$ 
ecutwfc 120.0 Ry
kpts coarse  $12 \times 12 \times 12$ 
kpts fine  $24 \times 24 \times 24$ 
qppts  $3 \times 3 \times 3$ 
lambda 1.958
omega_log 491 K
omega_2 890 K
Tc^McMillan 69.5 K
Tc^Allen-Dynes 86.0 K
Tc^Eliashberg 105.4 K
    
```

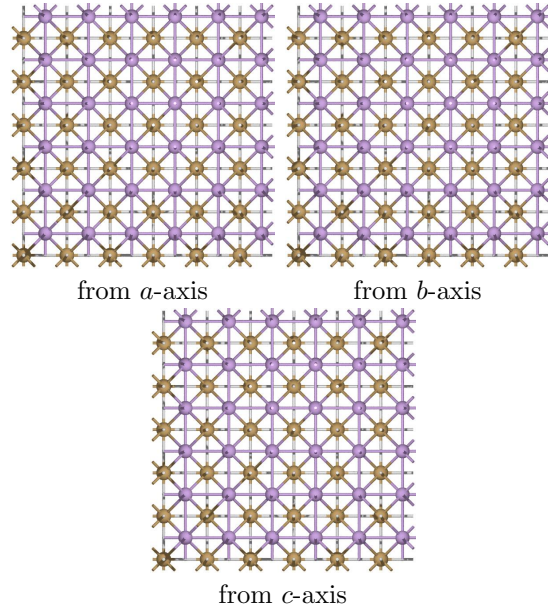


Primitive structure:


a : 4.3857 Å, b : 4.3857 Å, c : 4.3857 Å
 α : 60.00°, β : 60.00°, γ : 60.00°

```

Li [0.7500, 0.7500, 0.7500]
Li [0.2500, 0.2500, 0.2500]
Cu [0.0000, 0.0000, 0.0000]
H [0.2542, 0.7458, 0.7458]
H [0.2542, 0.2542, 0.2542]
H [0.7458, 0.7458, 0.7458]
H [0.7458, 0.2542, 0.2542]
H [0.2542, 0.7458, 0.7458]
H [0.7458, 0.2542, 0.2542]
    
```

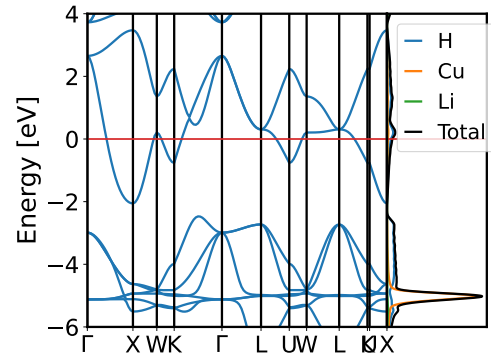

Electron band structure

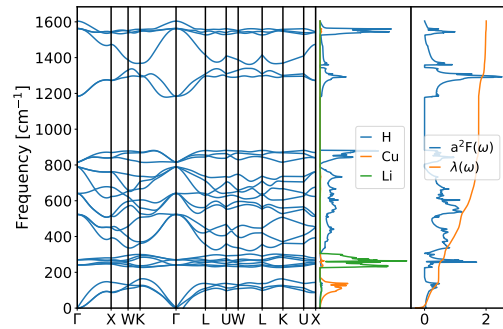

Phonon band structure

#2: Mg₂H₆Pt

```

mat id agm002154264
spg 225
nsites 9
e above hull 0.140 eV
e form -0.167 eV
decomposition Mg2H4Pt,H2
ecutwfc 100.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qpts 3×3×3
λ 1.240
ωlog 770 K
ω2 922 K
TcMcMillan 71.7 K
TcAllen-Dynes 78.3 K
TcEliashberg 84.4 K

```



Primitive structure:

a : 4.6558 Å, b : 4.6558 Å, c : 4.6558 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Mg [0.7500, 0.7500, 0.7500]
Mg [0.2500, 0.2500, 0.2500]
H [0.2717, 0.7283, 0.7283]
H [0.7283, 0.7283, 0.7283]
H [0.7283, 0.2717, 0.2717]
H [0.7283, 0.2717, 0.2717]
H [0.2717, 0.2717, 0.2717]
H [0.2717, 0.7283, 0.7283]
Pt [0.0000, 0.0000, 0.0000]

```

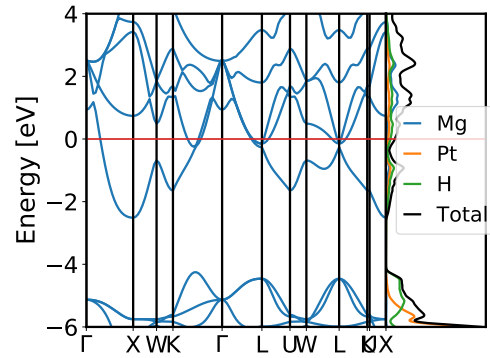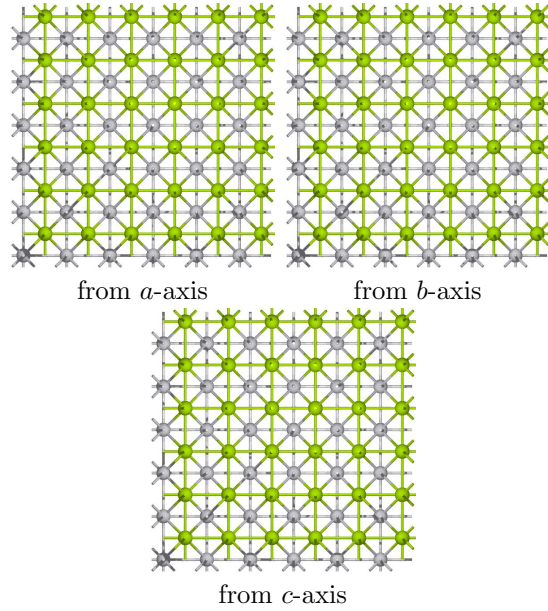

Electron band structure

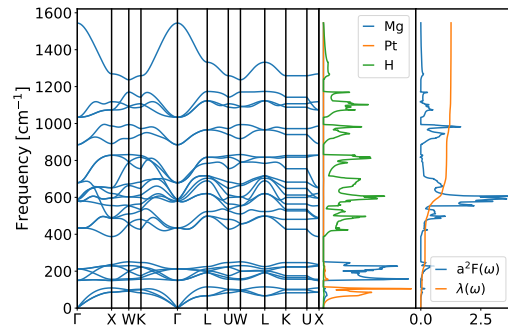

Phonon band structure

#3: Mg₂H₆Pd

```

mat id agm002153626
spg 225
nsites 9
e above hull 0.120 eV
e form -0.123 eV
decomposition MgHPd,MgH2,H2
ecutwfc 98.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qpts 3×3×3
λ 1.081
ωlog 760 K
ω2 910 K
TcMcMillan 59.4 K
TcAllen-Dynes 63.8 K
TcEliashberg 67.6 K

```



Primitive structure:

a : 4.6343 Å, b : 4.6343 Å, c : 4.6343 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Mg [0.2500, 0.2500, 0.2500]
Mg [0.7500, 0.7500, 0.7500]
H [0.2713, 0.7287, 0.7287]
H [0.7287, 0.2713, 0.2713]
H [0.7287, 0.2713, 0.2713]
H [0.2713, 0.7287, 0.7287]
H [0.7287, 0.7287, 0.7287]
H [0.2713, 0.2713, 0.2713]
Pd [0.0000, 0.0000, 0.0000]

```

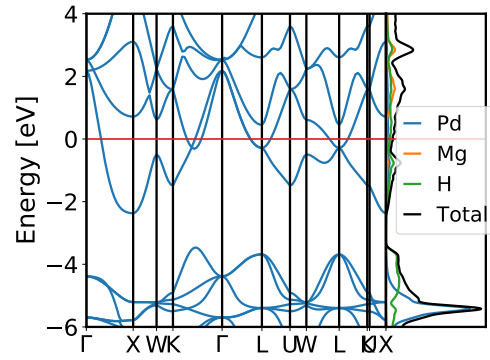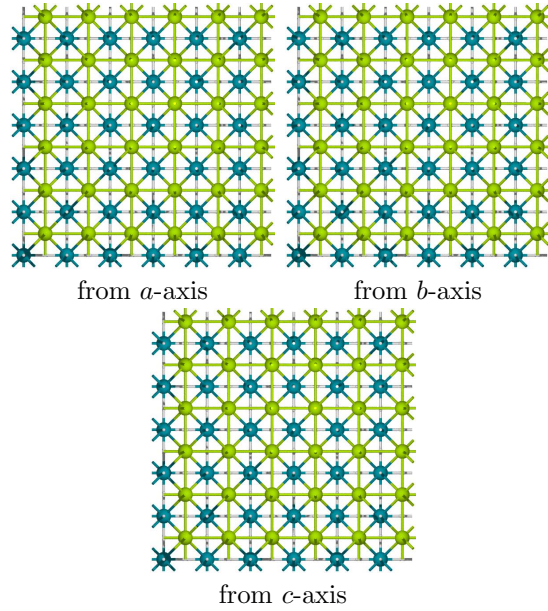

Electron band structure

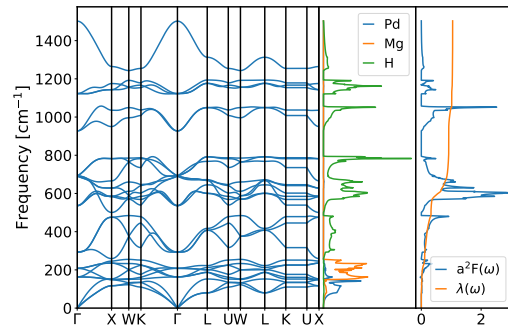

Phonon band structure

#4: Mg₂H₆Ir

```

mat id agm002153623
spg 225
nsites 9
e above hull 0.061 eV
e form -0.334 eV
decomposition Mg2H7Ir, Mg2H5Ir
ecutwfc 96.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qppts 3×3×3
λ 1.155
ωlog 634 K
ω2 1052 K
TcMcMillan 54.1 K
TcAllen-Dynes 59.4 K
TcEliashberg 63.3 K

```



Primitive structure:

a : 4.6593 Å, b : 4.6593 Å, c : 4.6593 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Mg [0.7500, 0.7500, 0.7500]
Mg [0.2500, 0.2500, 0.2500]
H [0.2610, 0.7390, 0.7390]
H [0.7390, 0.7390, 0.7390]
H [0.7390, 0.2610, 0.2610]
H [0.7390, 0.2610, 0.2610]
H [0.2610, 0.2610, 0.2610]
H [0.2610, 0.7390, 0.7390]
Ir [0.0000, 0.0000, 0.0000]

```

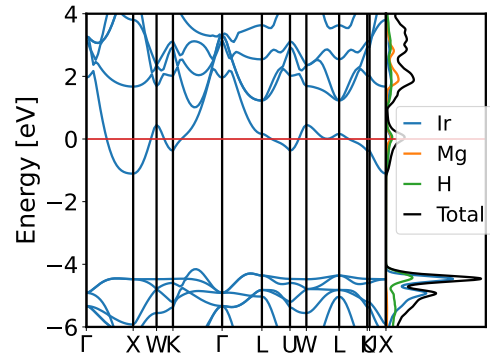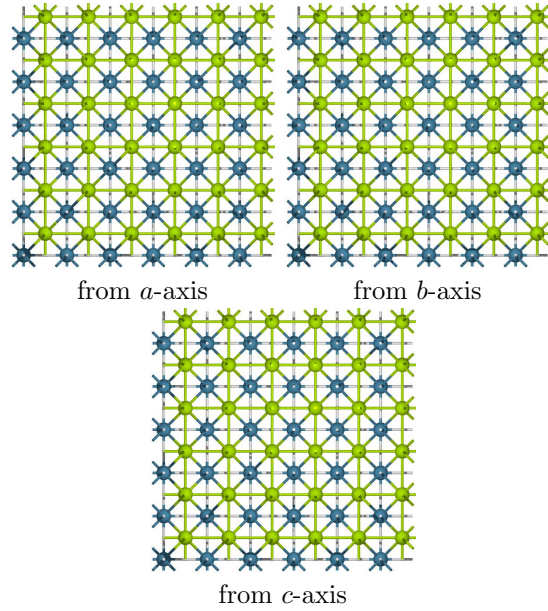

Electron band structure

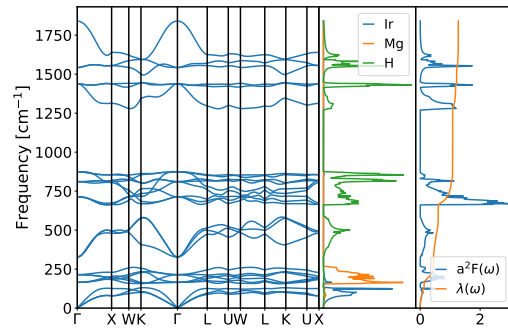

Phonon band structure

#5: Mg₂H₆Rh

```

mat id agm002153628
spg 225
nsites 9
e above hull 0.029 eV
e form -0.324 eV
decomposition Mg2H7Rh,Mg2H5Rh
ecutwfc 100.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qpts 3×3×3
λ 0.959
ωlog 771 K
ω2 1132 K
TcMcMillan 50.3 K
TcAllen-Dynes 53.8 K
TcEliashberg 55.0 K

```



Primitive structure:

a : 4.6268 Å, b : 4.6268 Å, c : 4.6268 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Mg [0.7500, 0.7500, 0.7500]
Mg [0.2500, 0.2500, 0.2500]
H [0.2603, 0.7397, 0.7397]
H [0.7397, 0.7397, 0.7397]
H [0.7397, 0.2603, 0.2603]
H [0.7397, 0.2603, 0.2603]
H [0.2603, 0.2603, 0.2603]
H [0.2603, 0.7397, 0.7397]
Rh [0.0000, 0.0000, 0.0000]

```

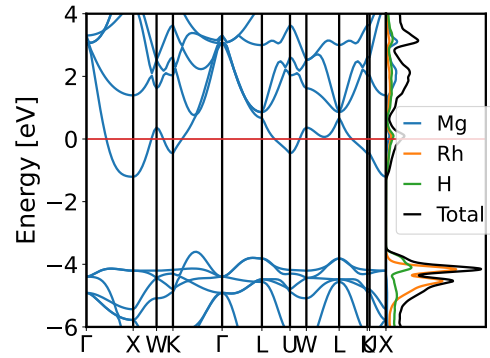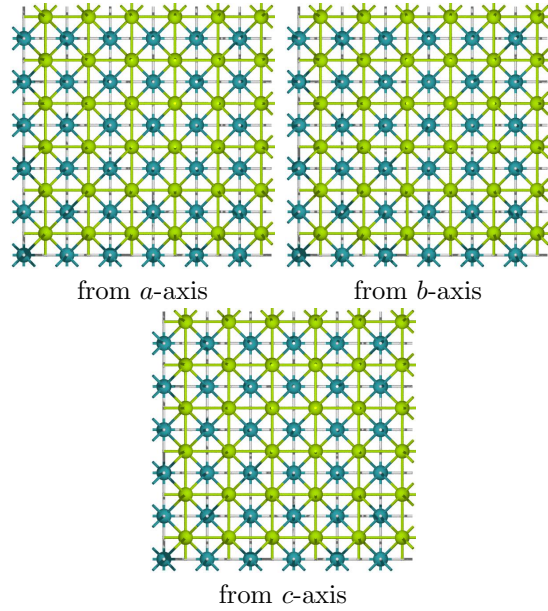

Electron band structure

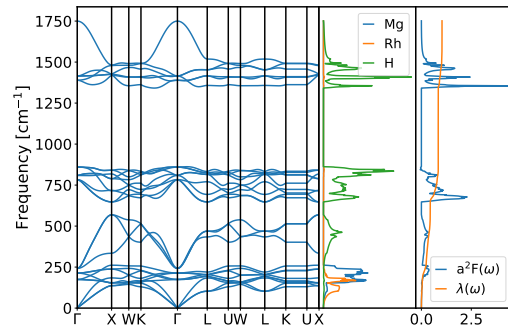


Phonon band structure

#6: Na₂AgH₆

```

mat id agm006188406
spg 225
nsites 9
e above hull 0.204 eV
e form 0.104 eV
decomposition H2,Ag,NaH
ecutwfc 96.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qpts 3×3×3
λ 1.124
ωlog 511 K
ω2 1000 K
TcMcMillan 42.1 K
TcAllen-Dynes 46.1 K
TcEliashberg 53.0 K

```

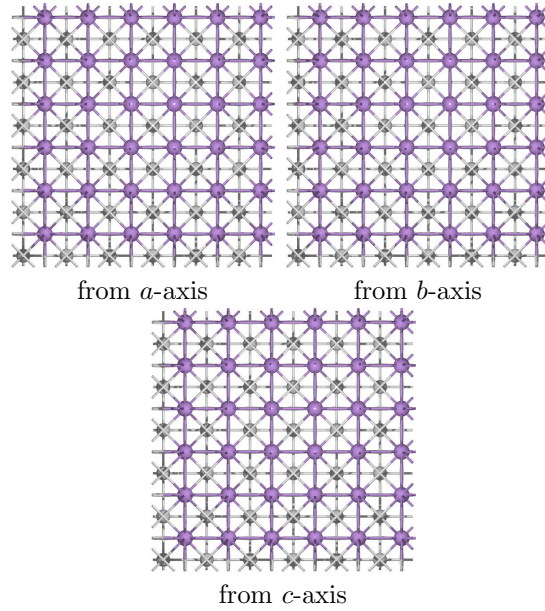


Primitive structure:

a: 4.9982 Å, *b*: 4.9982 Å, *c*: 4.9982 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Na [0.7500, 0.7500, 0.7500]
Na [0.2500, 0.2500, 0.2500]
Ag [0.0000, 0.0000, 0.0000]
H [0.2428, 0.7572, 0.7572]
H [0.2428, 0.2428, 0.2428]
H [0.7572, 0.7572, 0.7572]
H [0.7572, 0.2428, 0.2428]
H [0.2428, 0.7572, 0.7572]
H [0.7572, 0.2428, 0.2428]

```

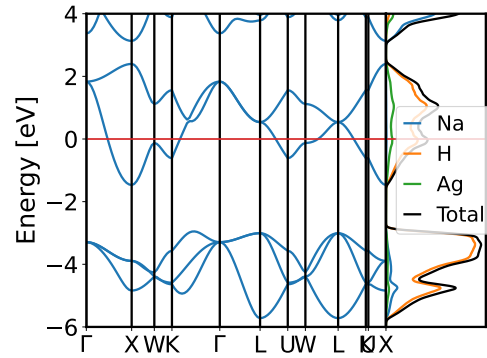

Electron band structure

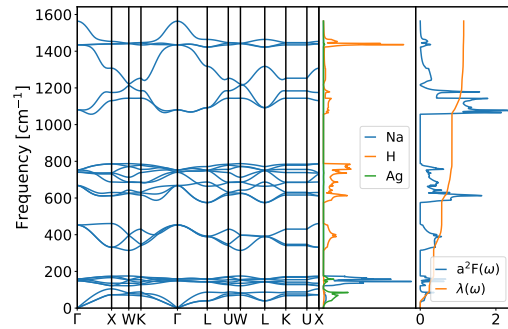


Phonon band structure

#7: $\text{Mn}(\text{AlH}_3)_2$

```

mat id agm002374192
spg 225
nsites 9
e above hull 0.068 eV
e form -0.124 eV
decomposition Mn2Al,MnAl2H7,Mn4Al11
ecutwfc 138.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qppts 3×3×3
λ 0.996
ωlog 587 K
ω2 1014 K
TcMcmillan 40.7 K
TcAllen-Dynes 43.9 K
TcEliashberg 43.9 K

```

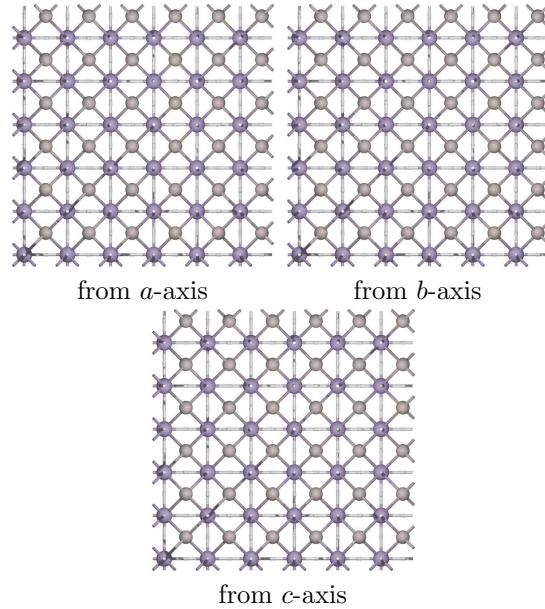


Primitive structure:

a: 4.2759 Å, *b*: 4.2759 Å, *c*: 4.2759 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Mn [0.0000, 0.0000, 0.0000]
Al [0.2500, 0.2500, 0.2500]
Al [0.7500, 0.7500, 0.7500]
H [0.7333, 0.2667, 0.2667]
H [0.7333, 0.7333, 0.7333]
H [0.7333, 0.2667, 0.2667]
H [0.2667, 0.7333, 0.7333]
H [0.2667, 0.2667, 0.2667]
H [0.2667, 0.7333, 0.7333]

```

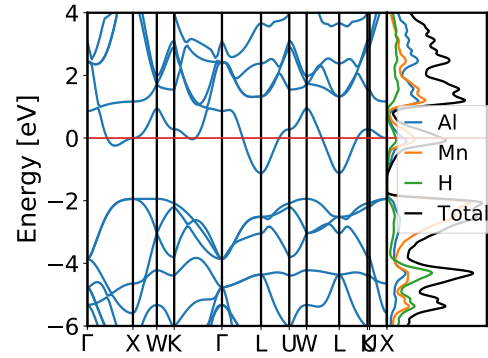

Electron band structure

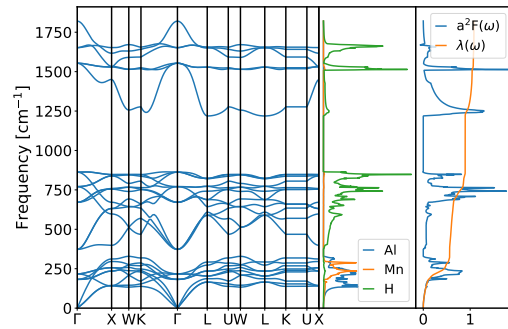

Phonon band structure

#8: Al_2TcH_6

```

mat id agm005682975
spg 225
nsites 9
e above hull 0.053 eV
e form -0.123 eV
decomposition  $\text{Al}_2\text{TcH}_7, \text{Al}_2\text{Tc}$ 
ecutwfc 96.0 Ry
kpts coarse  $12 \times 12 \times 12$ 
kpts fine  $24 \times 24 \times 24$ 
qppts  $3 \times 3 \times 3$ 
 $\lambda$  1.113
 $\omega_{\log}$  484 K
 $\omega_2$  964 K
 $T_c^{\text{McMillan}}$  39.3 K
 $T_c^{\text{Allen-Dynes}}$  43.1 K
 $T_c^{\text{Eliashberg}}$  47.3 K

```



Primitive structure:

a : 4.4503 Å, b : 4.4503 Å, c : 4.4503 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Al [0.7500, 0.7500, 0.7500]
Al [0.2500, 0.2500, 0.2500]
Tc [0.0000, 0.0000, 0.0000]
H [0.7237, 0.7237, 0.7237]
H [0.2763, 0.7237, 0.7237]
H [0.7237, 0.2763, 0.2763]
H [0.2763, 0.2763, 0.2763]
H [0.7237, 0.2763, 0.2763]
H [0.2763, 0.7237, 0.7237]

```

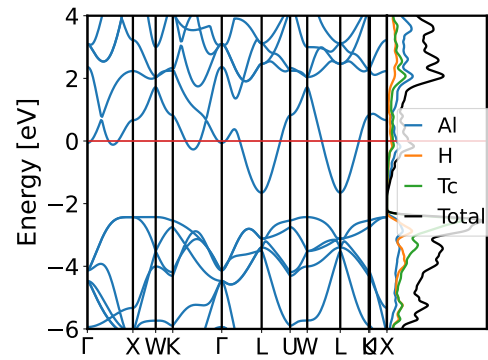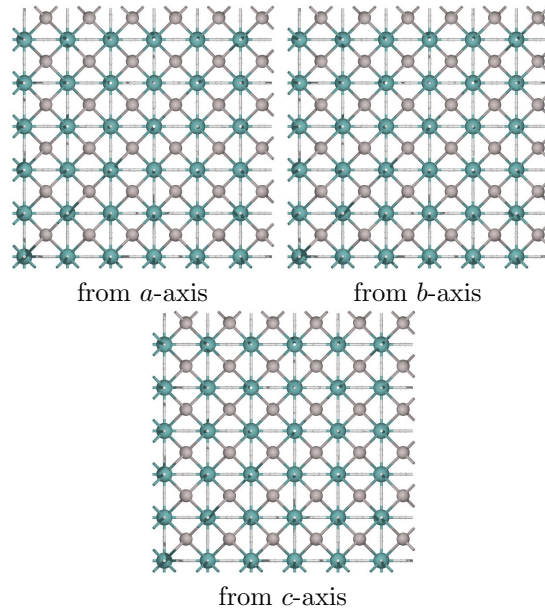

Electron band structure

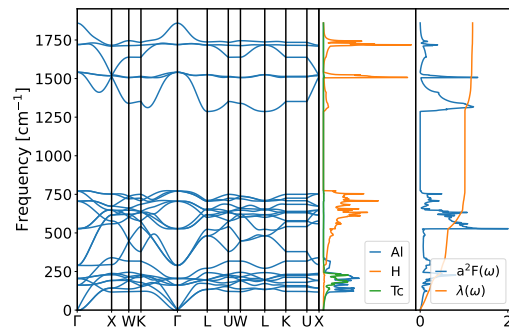


Phonon band structure

#9: Al_2ReH_6

```

mat id agm002374193
spg 225
nsites 9
e above hull 0.055 eV
e form -0.098 eV
decomposition Al2ReH7,Al11Re4,AlRe
ecutwfc 84.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qpts 3×3×3
λ 0.976
ωlog 504 K
ω2 994 K
TcMcMillan 33.9 K
TcAllen-Dynes 36.4 K
TcEliashberg 38.5 K

```

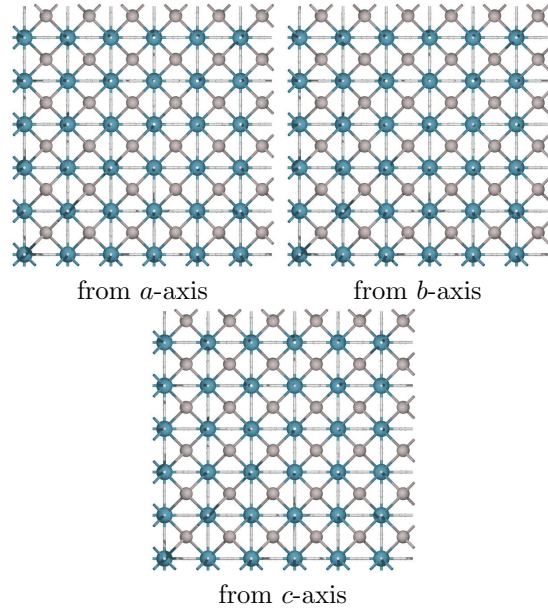


Primitive structure:

a: 4.4774 Å, *b*: 4.4774 Å, *c*: 4.4774 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Al [0.2500, 0.2500, 0.2500]
Al [0.7500, 0.7500, 0.7500]
Re [0.0000, 0.0000, 0.0000]
H [0.7231, 0.2769, 0.2769]
H [0.7231, 0.7231, 0.7231]
H [0.7231, 0.2769, 0.2769]
H [0.2769, 0.7231, 0.7231]
H [0.2769, 0.2769, 0.2769]
H [0.2769, 0.7231, 0.7231]

```

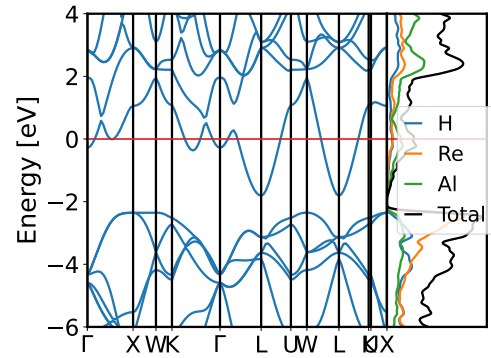

Electron band structure

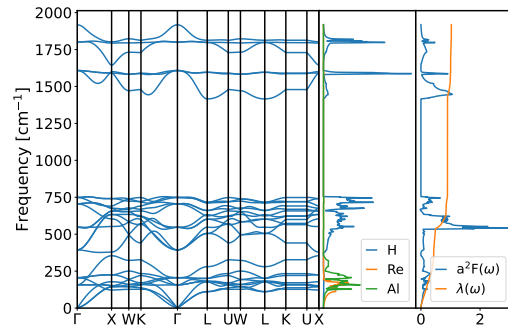


Phonon band structure

#10: Ca_2AgH_6

```

mat id agm005655392
spg 225
nsites 9
e above hull 0.166 eV
e form -0.259 eV
decomposition CaH2,H2,Ag
ecutwfc 94.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qppts 3×3×3
λ 1.089
ωlog 418 K
ω2 740 K
TcMcMillan 33.0 K
TcAllen-Dynes 35.9 K
TcEliashberg 43.1 K

```

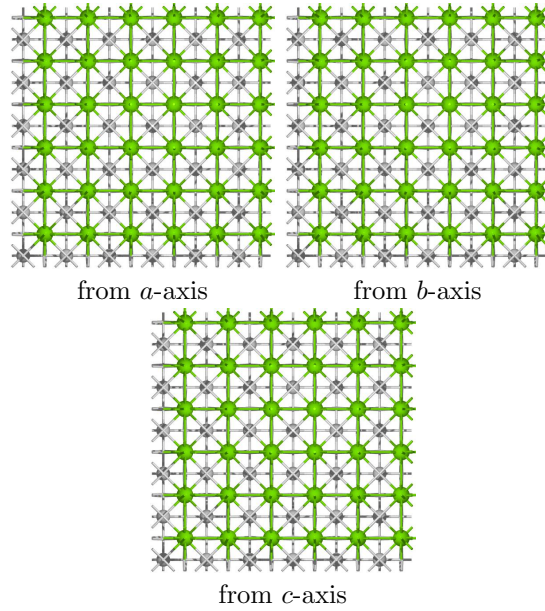


Primitive structure:

a: 5.0322 Å, *b*: 5.0322 Å, *c*: 5.0322 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Ca [0.2500, 0.2500, 0.2500]
Ca [0.7500, 0.7500, 0.7500]
Ag [0.0000, 0.0000, 0.0000]
H [0.7361, 0.7361, 0.7361]
H [0.2639, 0.7361, 0.7361]
H [0.2639, 0.7361, 0.7361]
H [0.2639, 0.2639, 0.2639]
H [0.7361, 0.2639, 0.2639]
H [0.7361, 0.2639, 0.2639]

```

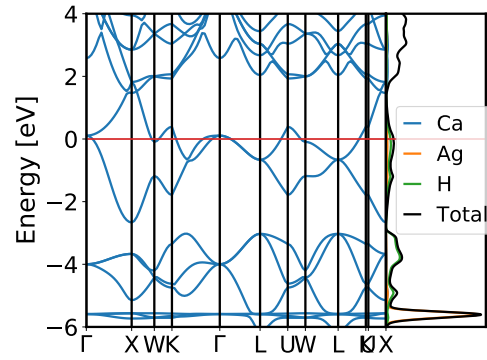

Electron band structure

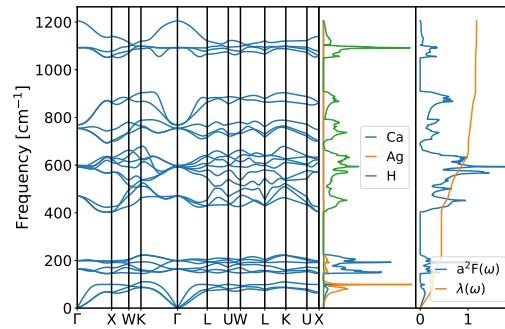

Phonon band structure

#11: $\text{Li}(\text{CaH}_3)_2$

```

mat id agm005655157
spg 225
nsites 9
e above hull 0.226 eV
e form -0.302 eV
decomposition CaH2,H2,LiH
ecutwfc 104.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qppts 3×3×3
λ 1.009
ωlog 433 K
ω2 706 K
TcMcmillan 30.6 K
TcAllen-Dynes 33.0 K
TcEliashberg 34.9 K

```



Primitive structure:

a : 4.9126 Å, b : 4.9126 Å, c : 4.9126 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Li [0.0000, 0.0000, 0.0000]
Ca [0.7500, 0.7500, 0.7500]
Ca [0.2500, 0.2500, 0.2500]
H [0.7435, 0.7435, 0.7435]
H [0.2565, 0.7435, 0.7435]
H [0.7435, 0.2565, 0.2565]
H [0.2565, 0.2565, 0.2565]
H [0.7435, 0.2565, 0.2565]
H [0.2565, 0.7435, 0.7435]

```

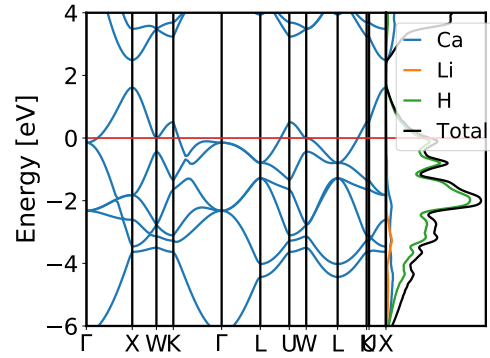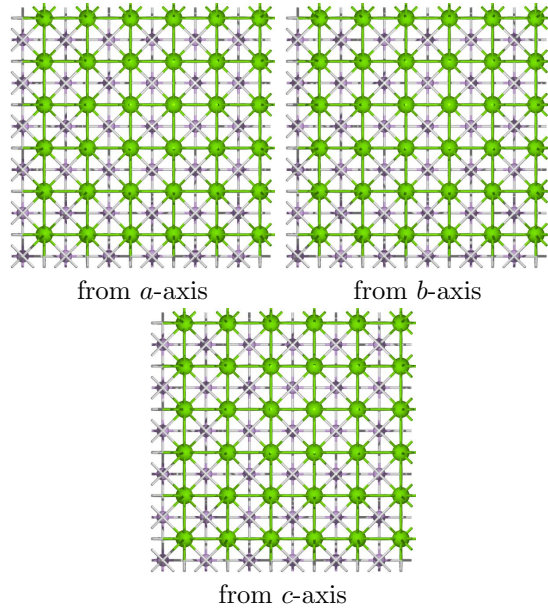

Electron band structure

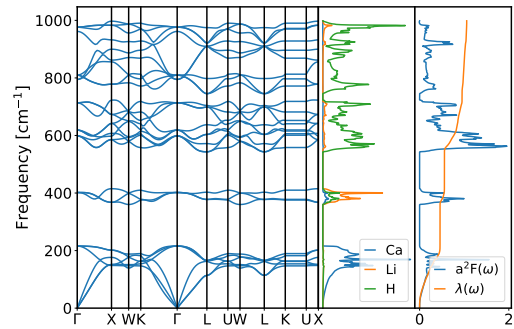


Phonon band structure

#12: Na₂H₆Au

```


mat id agm002153637
spg 225
nsites 9
e above hull 0.073 eV
e form -0.069 eV
decomposition NaH3Au,NaH,H2
ecutwfc 96.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qpts 3×3×3
λ 0.804
ωlog 632 K
ω2 1196 K
TcMcMillan 29.9 K
TcAllen-Dynes 31.6 K
TcEliashberg 32.9 K

```

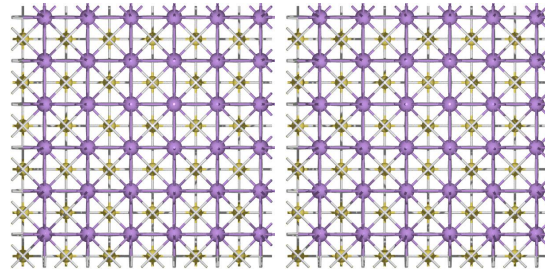

from *a*-axis

from *b*-axis

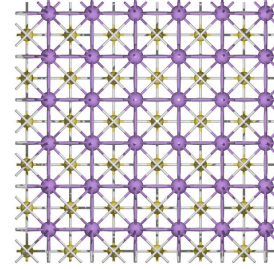

from *c*-axis


Primitive structure:

a: 5.0151 Å, *b*: 5.0151 Å, *c*: 5.0151 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Na [0.7500, 0.7500, 0.7500]
Na [0.2500, 0.2500, 0.2500]
H [0.7584, 0.7584, 0.7584]
H [0.2416, 0.7584, 0.7584]
H [0.7584, 0.2416, 0.2416]
H [0.2416, 0.2416, 0.2416]
H [0.7584, 0.2416, 0.2416]
H [0.2416, 0.7584, 0.7584]
Au [0.0000, 0.0000, 0.0000]

```

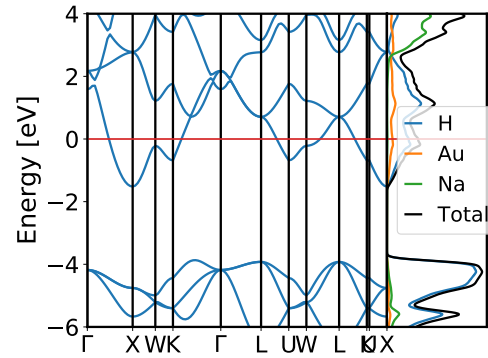

Electron band structure

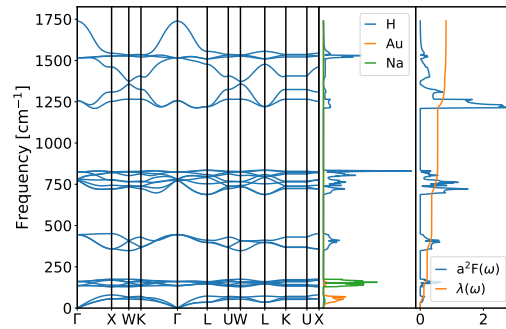

Phonon band structure

#13: Na₂CuH₆

```

mat id agm002153639
spg 225
nsites 9
e above hull 0.135 eV
e form 0.028 eV
decomposition Na3(CuH3)2,H2,NaH
ecutwfc 120.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qpts 3×3×3
λ 0.810
ωlog 580 K
ω2 1121 K
TcMcMillan 27.9 K
TcAllen-Dynes 29.5 K
TcEliashberg 30.0 K

```



Primitive structure:

a : 4.8976 Å, b : 4.8976 Å, c : 4.8976 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Na [0.7500, 0.7500, 0.7500]
Na [0.2500, 0.2500, 0.2500]
Cu [0.0000, 0.0000, 0.0000]
H [0.7734, 0.7734, 0.7734]
H [0.2266, 0.7734, 0.7734]
H [0.7734, 0.2266, 0.2266]
H [0.2266, 0.2266, 0.2266]
H [0.7734, 0.2266, 0.2266]
H [0.2266, 0.7734, 0.7734]

```

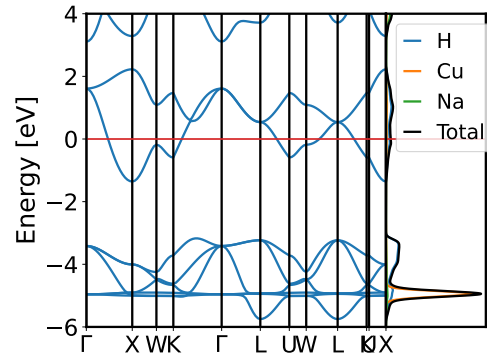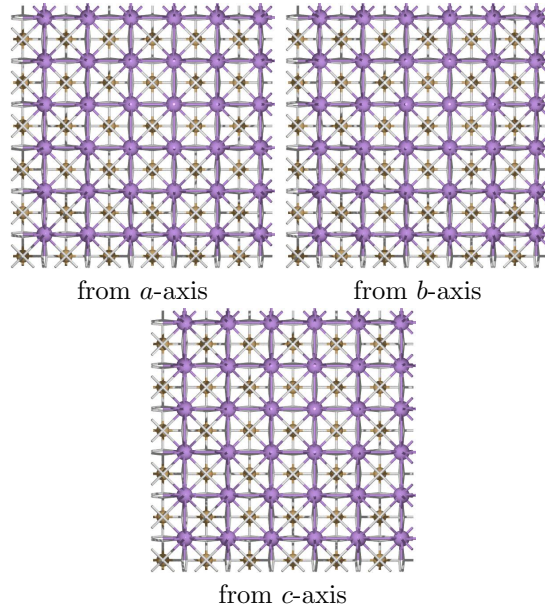

Electron band structure

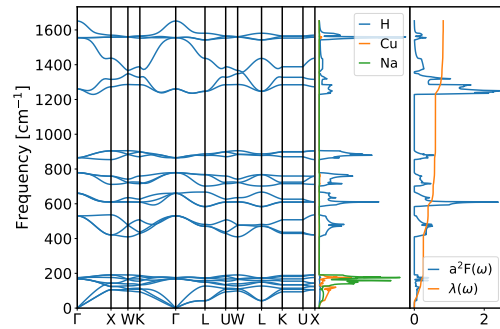

Phonon band structure

#14: Ga₂H₆Ru

```

mat id agm005683457
spg 225
nsites 9
e above hull 0.230 eV
e form 0.086 eV
decomposition Ga2Ru,H2
ecutwfc 122.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qppts 3×3×3
λ 1.141
ωlog 292 K
ω2 822 K
TcMcMillan 24.5 K
TcAllen-Dynes 26.9 K
TcEliashberg 28.4 K

```



Primitive structure:

a : 4.5634 Å, b : 4.5634 Å, c : 4.5634 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Ga [0.2500, 0.2500, 0.2500]
Ga [0.7500, 0.7500, 0.7500]
H [0.7321, 0.7321, 0.7321]
H [0.2679, 0.7321, 0.7321]
H [0.2679, 0.7321, 0.7321]
H [0.2679, 0.2679, 0.2679]
H [0.7321, 0.2679, 0.2679]
H [0.7321, 0.2679, 0.2679]
Ru [0.0000, 0.0000, 0.0000]

```

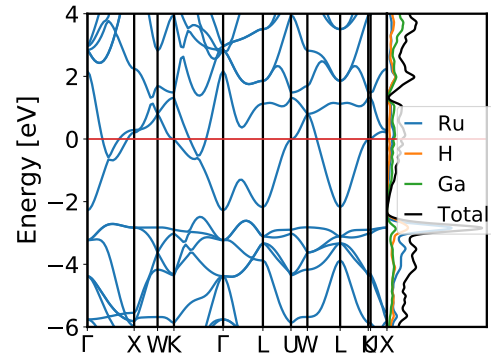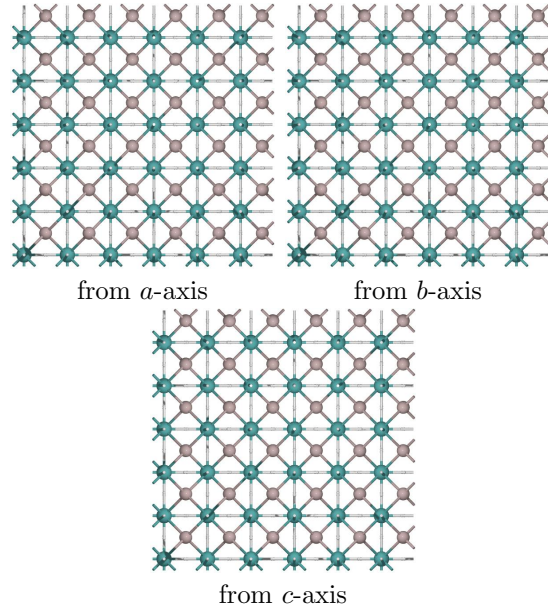

Electron band structure

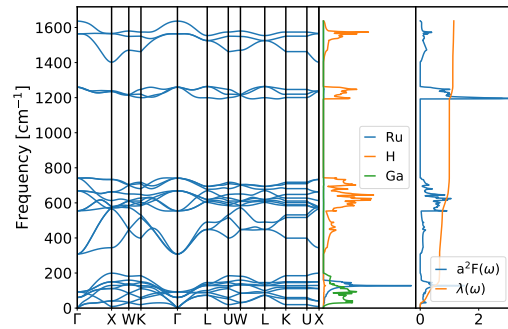

Phonon band structure

#15: Mg₂NiH₆

```

mat id agm002153625
spg 225
nsites 9
e above hull 0.063 eV
e form -0.185 eV
decomposition Mg2NiH4,H2
ecutwfc 116.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qpts 3×3×3
λ 0.609
ωlog 921 K
ω2 1120 K
TcMcMillan 22.0 K
TcAllen-Dynes 22.7 K
TcEliashberg 24.4 K

```



Primitive structure:

a : 4.4648 Å, b : 4.4648 Å, c : 4.4648 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Mg [0.7500, 0.7500, 0.7500]
Mg [0.2500, 0.2500, 0.2500]
Ni [0.0000, 0.0000, 0.0000]
H [0.2572, 0.7428, 0.7428]
H [0.7428, 0.7428, 0.7428]
H [0.7428, 0.2572, 0.2572]
H [0.7428, 0.2572, 0.2572]
H [0.2572, 0.2572, 0.2572]
H [0.2572, 0.7428, 0.7428]

```

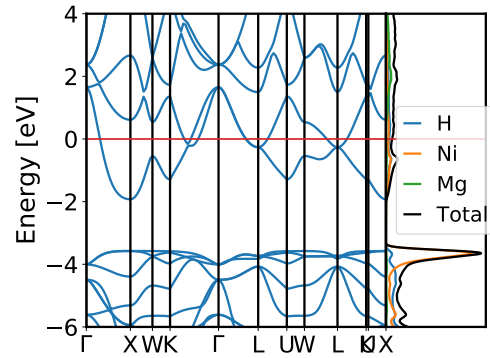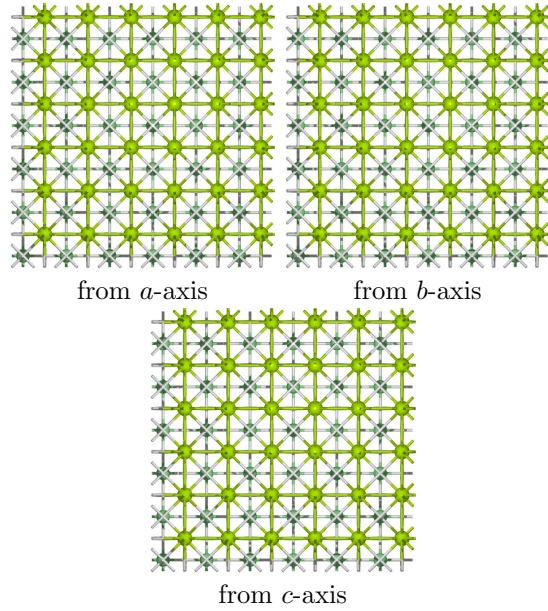

Electron band structure

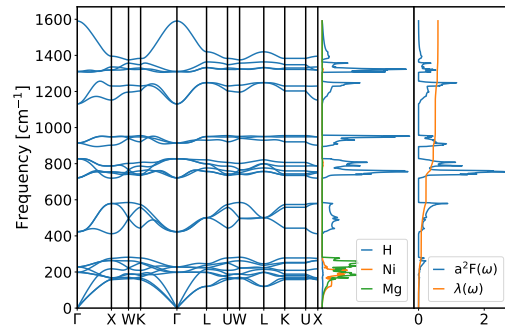

Phonon band structure

#16: Ga₂H₆Os

```

mat id agm005683659
spg 225
nsites 9
e above hull 0.179 eV
e form 0.101 eV
decomposition Ga3Os,Os,H2
ecutwfc 122.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qppts 3×3×3
λ 1.040
ωlog 262 K
ω2 841 K
TcMcMillan 19.4 K
TcAllen-Dynes 20.9 K
TcEliashberg 19.9 K

```



Primitive structure:

a : 4.5773 Å, b : 4.5773 Å, c : 4.5773 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Ga [0.2500, 0.2500, 0.2500]
Ga [0.7500, 0.7500, 0.7500]
H [0.7303, 0.7303, 0.7303]
H [0.2697, 0.7303, 0.7303]
H [0.2697, 0.7303, 0.7303]
H [0.2697, 0.2697, 0.2697]
H [0.7303, 0.2697, 0.2697]
H [0.7303, 0.2697, 0.2697]
Os [0.0000, 0.0000, 0.0000]

```

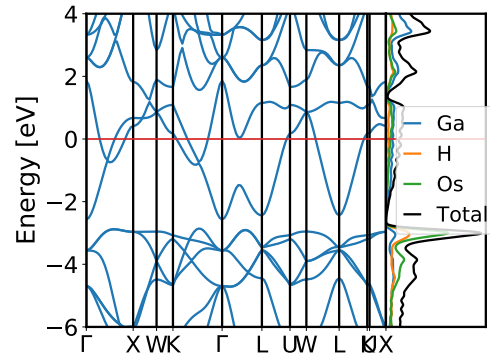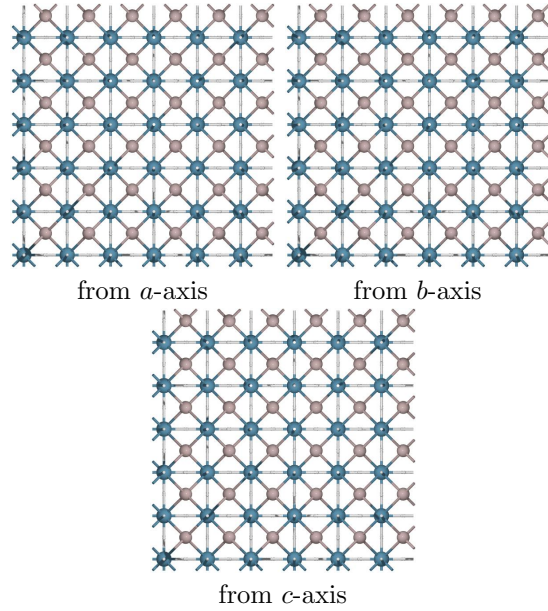

Electron band structure

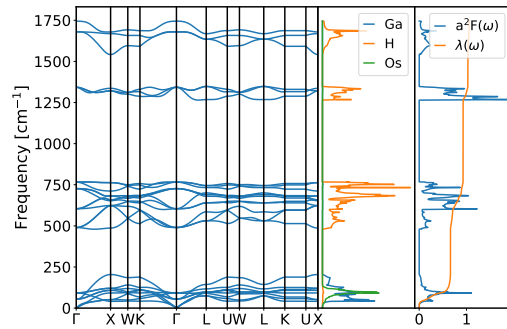

Phonon band structure

II – PEROVSKITES

#17: KInH_3

```

mat id agm002490653
spg 221
nsites 5
e above hull 0.077 eV
e form -0.028 eV
decomposition  $\text{KIn}_4\text{H}_2\text{KH}$ 
ecutwfc 98.0 Ry
kpts coarse  $16 \times 16 \times 16$ 
kpts fine  $32 \times 32 \times 32$ 
qppts  $4 \times 4 \times 4$ 
 $\lambda$  1.703
 $\omega_{\log}$  487 K
 $\omega_2$  698 K
 $T_c^{\text{McMillan}}$  62.1 K
 $T_c^{\text{Allen-Dynes}}$  72.9 K
 $T_c^{\text{Eliashberg}}$  86.6 K

```



Primitive structure:

a : 4.1641 Å, b : 4.1641 Å, c : 4.1641 Å
 α : 90.00°, β : 90.00°, γ : 90.00°


```

K [0.5000, 0.5000, 0.5000]
In [0.0000, 0.0000, 0.0000]
H [0.0000, 0.0000, 0.0000]
H [0.0000, 0.5000, 0.5000]
H [0.5000, 0.0000, 0.0000]

```

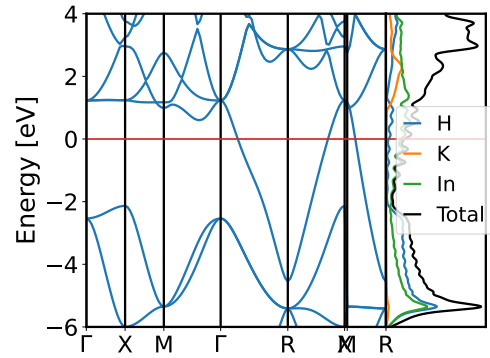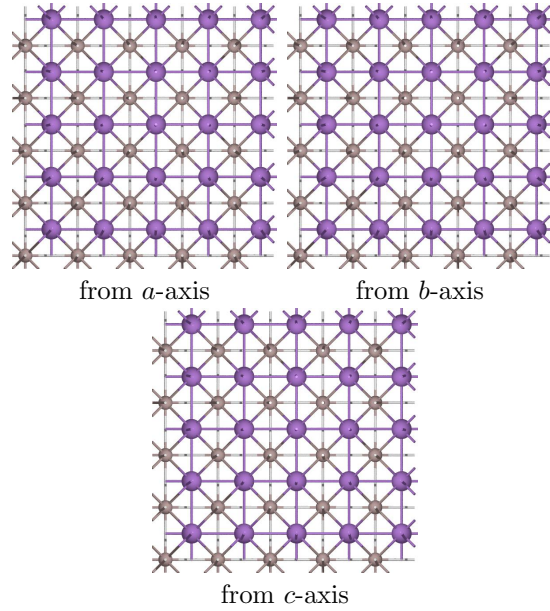

Electron band structure

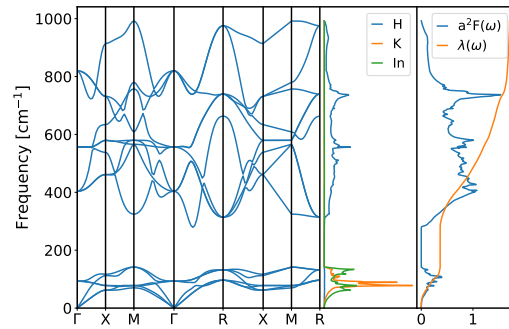

Phonon band structure

#18: Al_4H

```

mat id agm006176992
  spg 221
  nsites 5
e above hull 0.136 eV
e form 0.123 eV
decomposition AlH3,Al
ecutwfc 84.0 Ry
kpts coarse 16×16×16
kpts fine 32×32×32
qpts 4×4×4
  λ 0.969
  ωlog 430 K
  ω2 546 K
  TcMcMillan 28.5 K
  TcAllen-Dynes 30.4 K
  TcEliashberg 32.5 K

```



Primitive structure:

a : 4.0728 Å, b : 4.0728 Å, c : 4.0728 Å
 α : 90.00°, β : 90.00°, γ : 90.00°


```

Al [0.5000, 0.5000, 0.5000]
Al [0.5000, 0.0000, 0.0000]
Al [0.0000, 0.0000, 0.0000]
Al [0.0000, 0.5000, 0.5000]
H [0.0000, 0.0000, 0.0000]

```

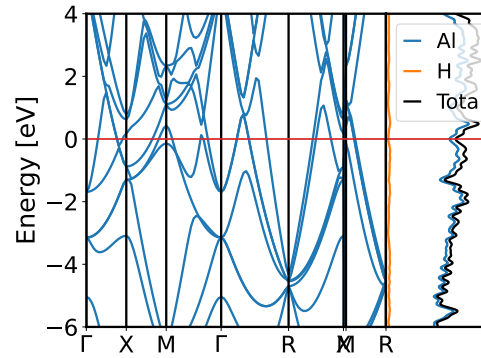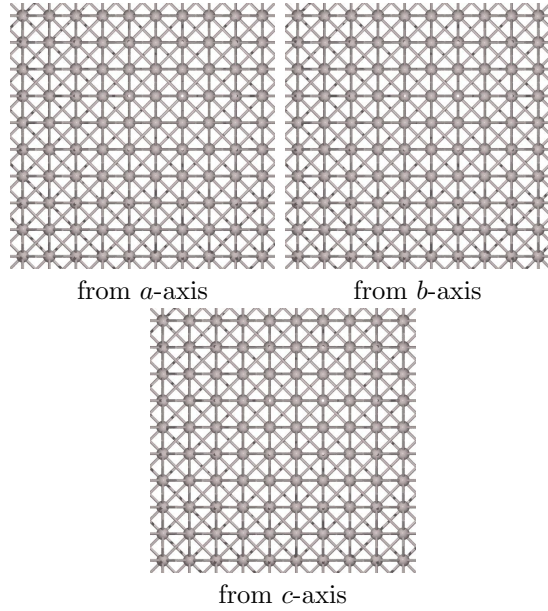

Electron band structure

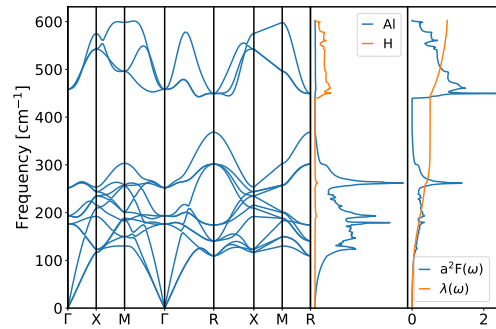

Phonon band structure

#19: AlHgH₃

```



mat id agm002493244
spg 221
nsites 5
e above hull 0.278 eV
e form 0.240 eV
decomposition Hg,AlH3
ecutwfc 100.0 Ry
kpts coarse 16×16×16
kpts fine 32×32×32
qppts 4×4×4
λ 0.963
ωlog 403 K
ω2 854 K
TcMcMillan 26.5 K
TcAllen-Dynes 28.4 K
TcEliashberg 31.7 K

```


Primitive structure:

a : 3.7419 Å, b : 3.7419 Å, c : 3.7419 Å
 α : 90.00°, β : 90.00°, γ : 90.00°

Al	[0.0000, 0.0000, 0.0000]
Hg	[0.5000, 0.5000, 0.5000]
H	[0.0000, 0.0000, 0.0000]
H	[0.0000, 0.5000, 0.5000]
H	[0.5000, 0.0000, 0.0000]

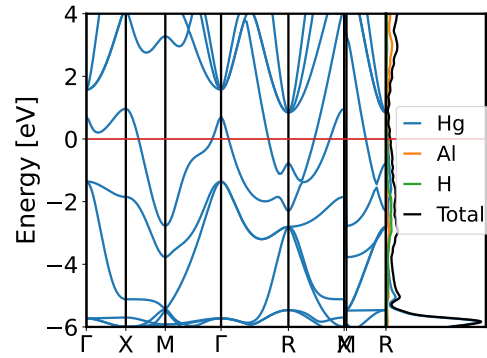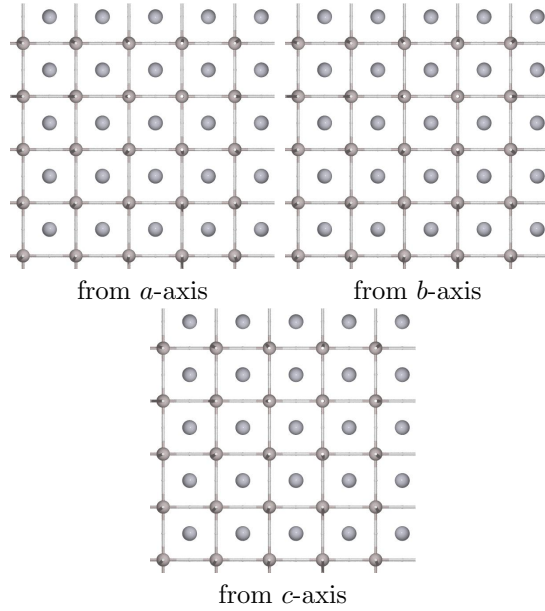

Electron band structure

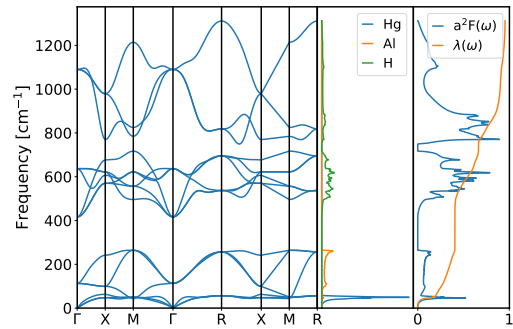

Phonon band structure

#20: HgH₃Pb

```

mat id agm002496201
spg 221
nsites 5
e above hull 0.420 eV
e form 0.419 eV
decomposition Hg,H2,HgPb2
ecutwfc 100.0 Ry
kpts coarse 16×16×16
kpts fine 32×32×32
qpts 4×4×4
λ 0.849
ωlog 462 K
ω2 808 K
TcMcMillan 24.3 K
TcAllen-Dynes 25.8 K
TcEliashberg 29.3 K

```



Primitive structure:

a : 4.1584 Å, b : 4.1584 Å, c : 4.1584 Å
 α : 90.00°, β : 90.00°, γ : 90.00°


```

Hg [0.5000, 0.5000, 0.5000]
H [0.0000, 0.0000, 0.0000]
H [0.0000, 0.5000, 0.5000]
H [0.5000, 0.0000, 0.0000]
Pb [0.0000, 0.0000, 0.0000]

```

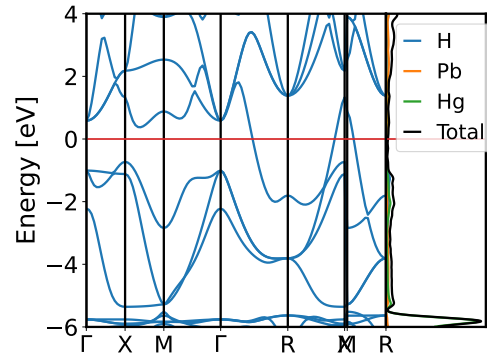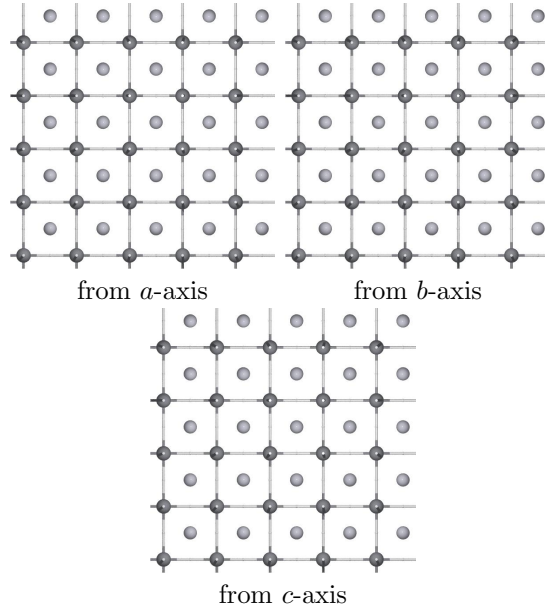

Electron band structure

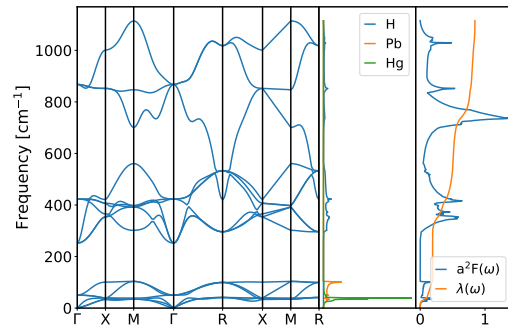

Phonon band structure

#21: H₃OsPb

```



mat id agm002493550
spg 221
nsites 5
e above hull 0.369 eV
e form 0.369 eV
decomposition H2,Os,Pb
ecutwfc 100.0 Ry
kpts coarse 16×16×16
kpts fine 32×32×32
qpts 4×4×4
λ 1.034
ωlog 292 K
ω2 722 K
TcMcMillan 21.4 K
TcAllen-Dynes 23.2 K
TcEliashberg 25.2 K

```


Primitive structure:

a : 3.6927 Å, b : 3.6927 Å, c : 3.6927 Å
 α : 90.00°, β : 90.00°, γ : 90.00°

H	[0.0000, 0.0000, 0.0000]
H	[0.0000, 0.5000, 0.5000]
H	[0.5000, 0.0000, 0.0000]
Os	[0.0000, 0.0000, 0.0000]
Pb	[0.5000, 0.5000, 0.5000]

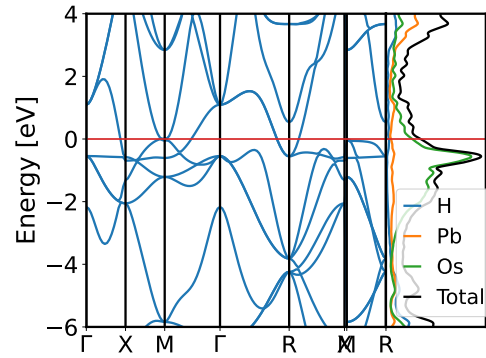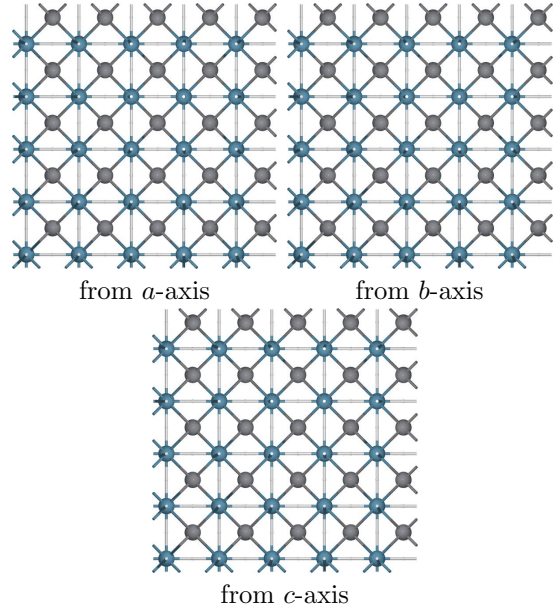

Electron band structure

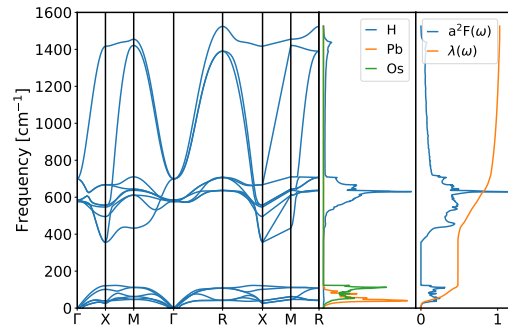

Phonon band structure

#22: Mg₃TiH

```

mat id agm002495459
spg 221
nsites 5
e above hull 0.370 eV
e form 0.190 eV
decomposition TiH2,Mg,Ti
ecutwfc 96.0 Ry
kpts coarse 16×16×16
kpts fine 32×32×32
qpts 4×4×4
λ 1.310
ωlog 196 K
ω2 362 K
TcMcMillan 19.4 K
TcAllen-Dynes 21.8 K
TcEliashberg 23.5 K

```



Primitive structure:

a : 4.3602 Å, b : 4.3602 Å, c : 4.3602 Å
 α : 90.00°, β : 90.00°, γ : 90.00°


```

Mg [0.0000, 0.0000, 0.0000]
Mg [0.0000, 0.5000, 0.5000]
Mg [0.5000, 0.0000, 0.0000]
Ti [0.5000, 0.5000, 0.5000]
H [0.0000, 0.0000, 0.0000]

```

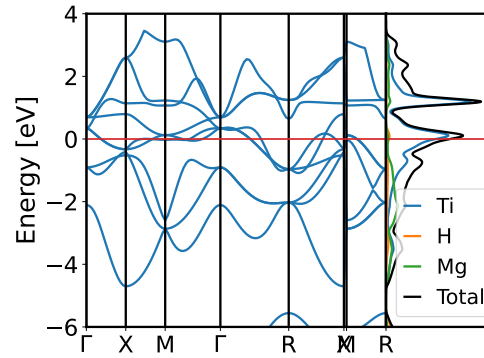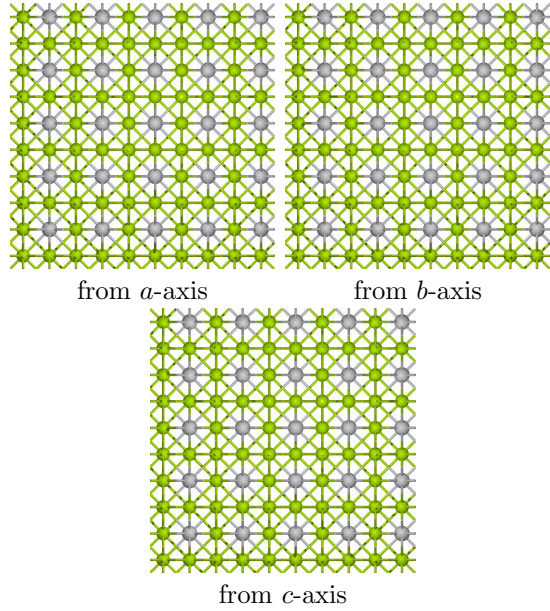

Electron band structure

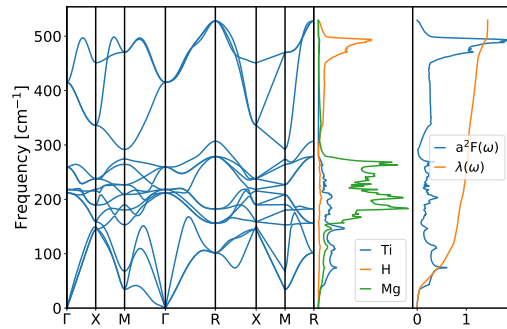

Phonon band structure


III – DOUBLE PEROVSKITES

#23: K_2InCuH_6

```

mat id agm004929677
spg 225
nsites 10
e above hull 0.047 eV
e form -0.075 eV
decomposition InCu2,K2CuH3,KIn4,H2
ecutwfc 120.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qppts 3×3×3
λ 1.250
ωlog 510 K
ω2 716 K
TcMcMillan 47.9 K
TcAllen-Dynes 53.0 K
TcEliashberg 58.1 K


```

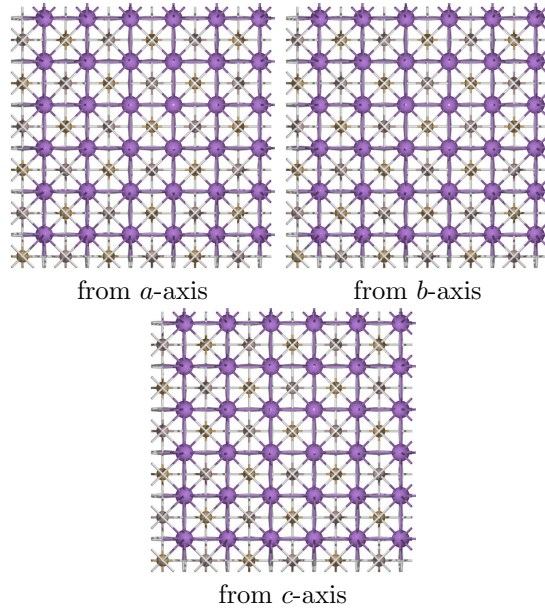


Primitive structure:

a : 5.4865 Å, b : 5.4865 Å, c : 5.4865 Å
 α : 60.00°, β : 60.00°, γ : 60.00°

K	[0.7500, 0.7500, 0.7500]
K	[0.2500, 0.2500, 0.2500]
In	[0.0000, 0.0000, 0.0000]
Cu	[0.5000, 0.5000, 0.5000]
H	[0.7293, 0.2707, 0.2707]
H	[0.7293, 0.7293, 0.7293]
H	[0.7293, 0.2707, 0.2707]
H	[0.2707, 0.7293, 0.7293]
H	[0.2707, 0.2707, 0.2707]
H	[0.2707, 0.7293, 0.7293]

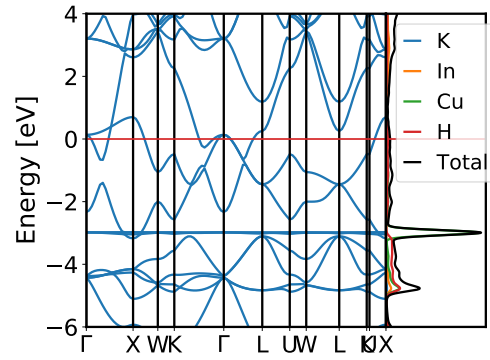

Electron band structure

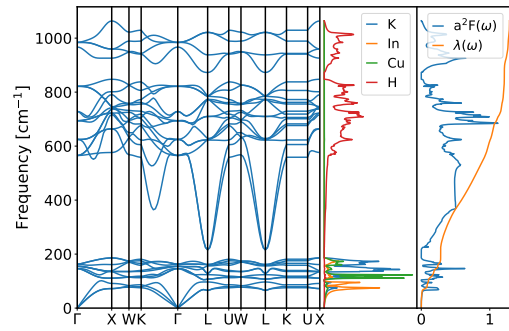

Phonon band structure

#24: K_2LiCuH_6

```



mat id agm002340583
spg 225
nsites 10
e above hull 0.116 eV
e form -0.095 eV
decomposition  $\text{K}_2\text{CuH}_3, \text{LiH}, \text{H}_2$ 
ecutwfc 120.0 Ry
kpts coarse  $12 \times 12 \times 12$ 
kpts fine  $24 \times 24 \times 24$ 
qppts  $3 \times 3 \times 3$ 
 $\lambda$  1.213
 $\omega_{\log}$  470 K
 $\omega_2$  719 K
 $T_c^{\text{McMillan}}$  42.7 K
 $T_c^{\text{Allen-Dynes}}$  47.1 K
 $T_c^{\text{Eliashberg}}$  50.3 K

```


Primitive structure:

a : 5.4138 Å, b : 5.4138 Å, c : 5.4138 Å
 α : 60.00°, β : 60.00°, γ : 60.00°

K	[0.7500, 0.7500, 0.7500]
K	[0.2500, 0.2500, 0.2500]
Li	[0.5000, 0.5000, 0.5000]
Cu	[0.0000, 0.0000, 0.0000]
H	[0.7824, 0.7824, 0.7824]
H	[0.2176, 0.7824, 0.7824]
H	[0.7824, 0.2176, 0.2176]
H	[0.2176, 0.2176, 0.2176]
H	[0.7824, 0.2176, 0.2176]
H	[0.2176, 0.7824, 0.7824]

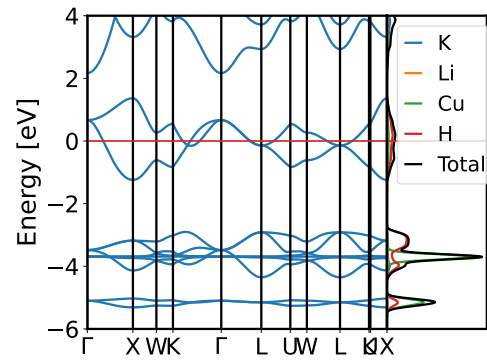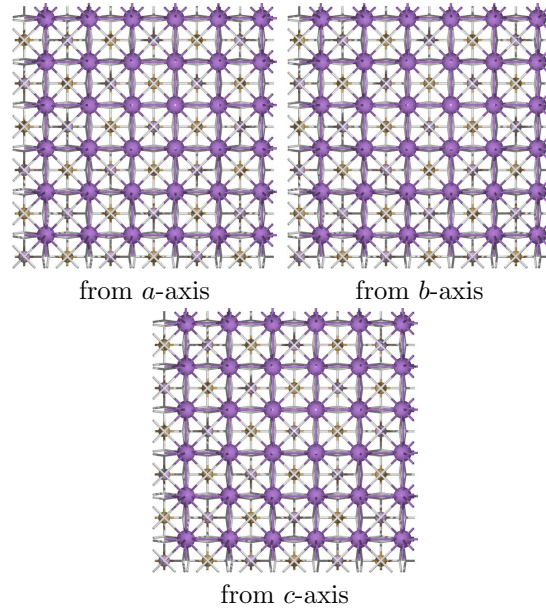

Electron band structure

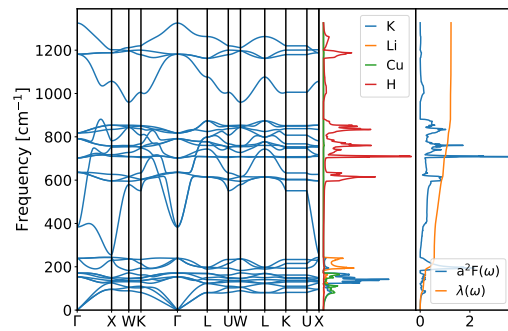


Phonon band structure

#25: Na₂LiCuH₆

```


mat id agm002280446
spg 225
nsites 10
e above hull 0.102 eV
e form -0.087 eV
decomposition Na3(CuH3)2,LiH,H2,NaH
ecutwfc 120.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qppts 3×3×3
λ 0.952
ωlog 666 K
ω2 950 K
TcMcMillan 42.9 K
TcAllen-Dynes 45.9 K
TcEliashberg 48.5 K

```

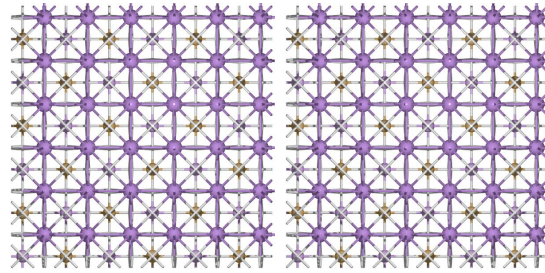

from *a*-axis

from *b*-axis

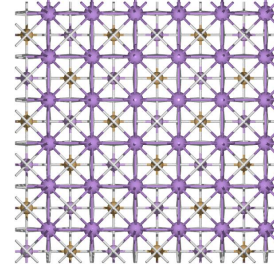

from *c*-axis


Primitive structure:

a: 5.0176 Å, *b*: 5.0176 Å, *c*: 5.0176 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Na [0.7500, 0.7500, 0.7500]
Na [0.2500, 0.2500, 0.2500]
Li [0.5000, 0.5000, 0.5000]
Cu [0.0000, 0.0000, 0.0000]
H [0.7677, 0.7677, 0.7677]
H [0.2323, 0.7677, 0.7677]
H [0.7677, 0.2323, 0.2323]
H [0.2323, 0.2323, 0.2323]
H [0.7677, 0.2323, 0.2323]
H [0.2323, 0.7677, 0.7677]

```

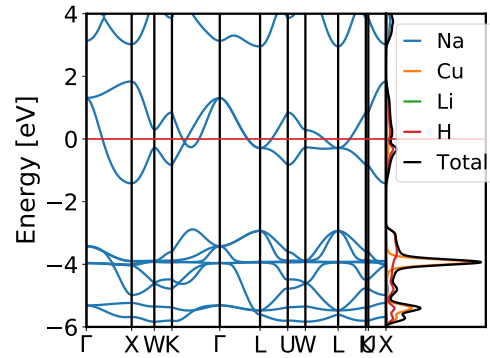

Electron band structure

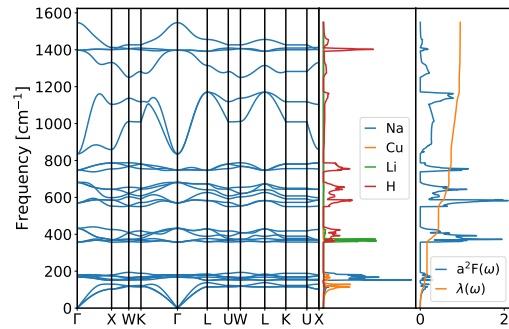


Phonon band structure

#26: Na₂SiH₆Pd

```

mat id agm004984390
spg 225
nsites 10
e above hull 0.084 eV
e form -0.148 eV
decomposition Na2H6Pd,Na2SiH6,SiPd
ecutwfc 98.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qpts 3×3×3
λ 0.772
ωlog 875 K
ω2 1062 K
TcMcMillan 38.1 K
TcAllen-Dynes 39.8 K
TcEliashberg 42.8 K

```

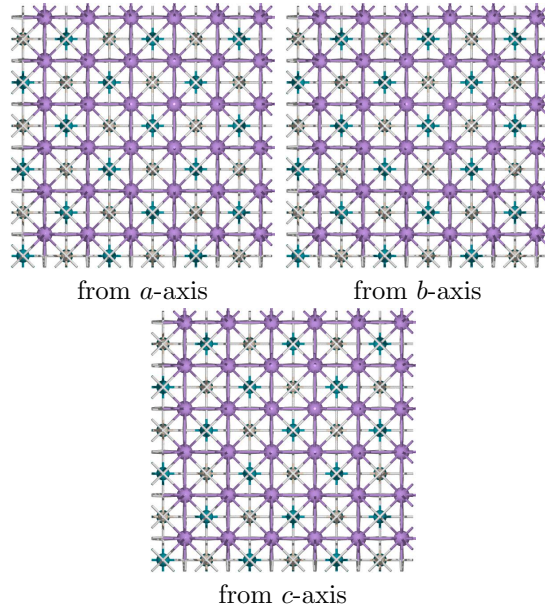


Primitive structure:

a: 5.0950 Å, *b*: 5.0950 Å, *c*: 5.0950 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Na [0.7500, 0.7500, 0.7500]
Na [0.2500, 0.2500, 0.2500]
Si [0.0000, 0.0000, 0.0000]
H [0.2455, 0.7545, 0.7545]
H [0.7545, 0.2455, 0.2455]
H [0.7545, 0.2455, 0.2455]
H [0.2455, 0.2455, 0.2455]
H [0.2455, 0.7545, 0.7545]
H [0.7545, 0.7545, 0.7545]
Pd [0.5000, 0.5000, 0.5000]

```

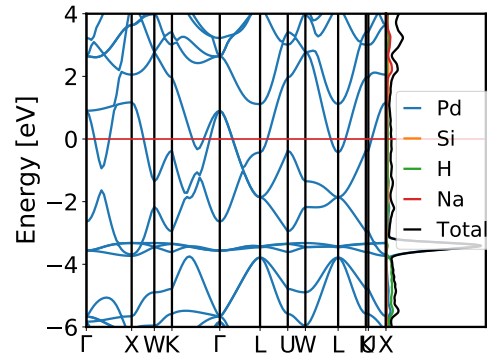

Electron band structure

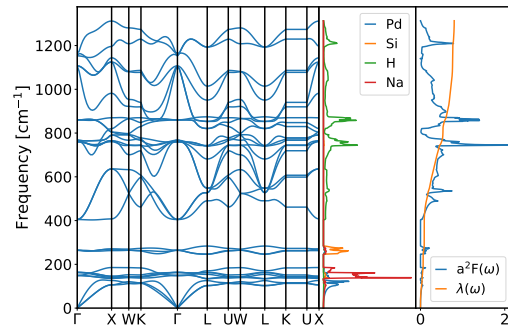

Phonon band structure

#27: Na₂LiZnH₆

```

mat id agm002279787
spg 225
nsites 10
e above hull 0.146 eV
e form -0.072 eV
decomposition Na2ZnH4,LiH,H2
ecutwfc 104.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qppts 3×3×3
λ 0.983
ωlog 519 K
ω2 763 K
TcMcMillan 35.2 K
TcAllen-Dynes 37.8 K
TcEliashberg 39.7 K

```



Primitive structure:

a : 5.0986 Å, b : 5.0986 Å, c : 5.0986 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Na [0.2500, 0.2500, 0.2500]
Na [0.7500, 0.7500, 0.7500]
Li [0.5000, 0.5000, 0.5000]
Zn [0.0000, 0.0000, 0.0000]
H [0.7570, 0.7570, 0.7570]
H [0.2430, 0.7570, 0.7570]
H [0.2430, 0.7570, 0.7570]
H [0.2430, 0.2430, 0.2430]
H [0.7570, 0.2430, 0.2430]
H [0.7570, 0.2430, 0.2430]

```

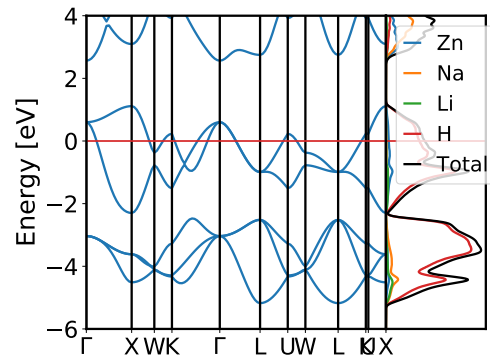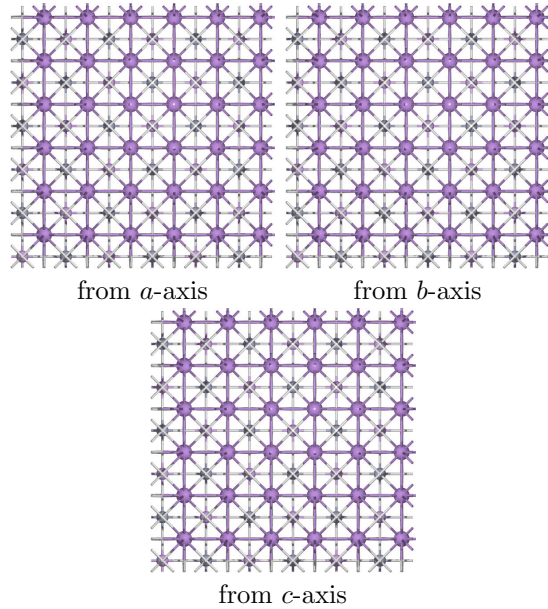

Electron band structure

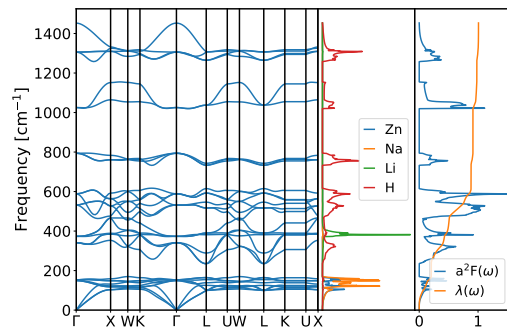

Phonon band structure

#28: Na₂GaH₆Ru

```



mat id agm004927065
spg 225
nsites 10
e above hull 0.162 eV
e form -0.118 eV
decomposition Ga3Ru,Na3H7Ru,H2
ecutwfc 122.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qppts 3×3×3
λ 0.926
ωlog 535 K
ω2 863 K
TcMcMillan 32.9 K
TcAllen-Dynes 35.2 K
TcEliashberg 35.5 K

```


Primitive structure:

a : 5.0473 Å, b : 5.0473 Å, c : 5.0473 Å
 α : 60.00°, β : 60.00°, γ : 60.00°

Na	[0.2500, 0.2500, 0.2500]
Na	[0.7500, 0.7500, 0.7500]
Ga	[0.5000, 0.5000, 0.5000]
H	[0.7583, 0.2417, 0.2417]
H	[0.2417, 0.7583, 0.7583]
H	[0.7583, 0.7583, 0.7583]
H	[0.2417, 0.2417, 0.2417]
H	[0.7583, 0.2417, 0.2417]
H	[0.2417, 0.7583, 0.7583]
Ru	[0.0000, 0.0000, 0.0000]

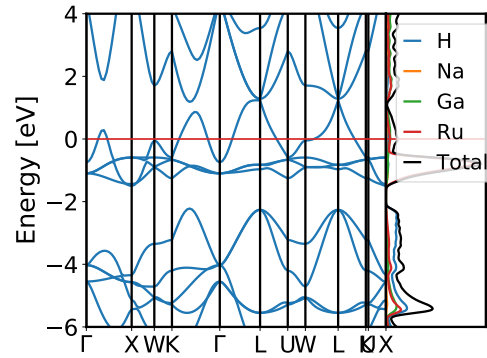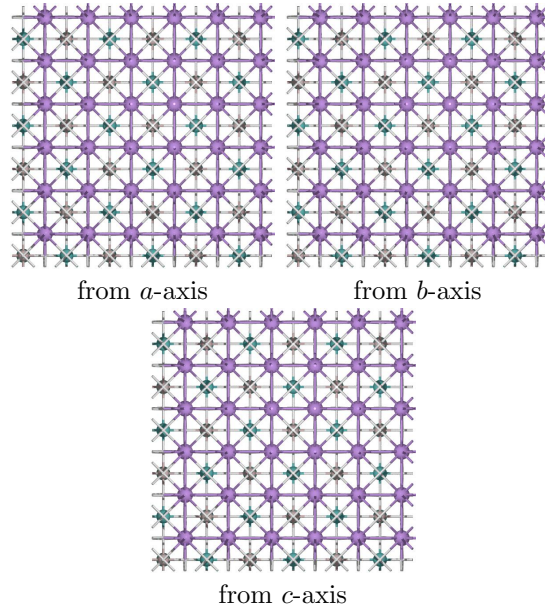

Electron band structure

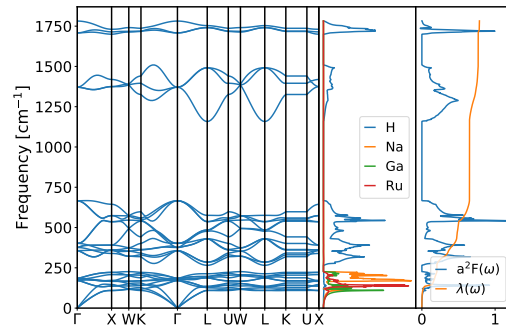

Phonon band structure

#29: Cs₂NaSnH₆

```



mat id agm002153654
spg 225
nsites 10
e above hull 0.067 eV
e form -0.097 eV
decomposition CsH3,CsH9,CsSnH,NaH
ecutwfc 114.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qpts 3×3×3
λ 1.266
ωlog 324 K
ω2 588 K
TcMcMillan 30.9 K
TcAllen-Dynes 34.5 K
TcEliashberg 40.0 K

```


Primitive structure:

a : 6.2527 Å, b : 6.2527 Å, c : 6.2527 Å
 α : 60.00°, β : 60.00°, γ : 60.00°

Cs	[0.2500, 0.2500, 0.2500]
Cs	[0.7500, 0.7500, 0.7500]
Na	[0.5000, 0.5000, 0.5000]
Sn	[0.0000, 0.0000, 0.0000]
H	[0.2254, 0.7746, 0.7746]
H	[0.7746, 0.2254, 0.2254]
H	[0.2254, 0.7746, 0.7746]
H	[0.2254, 0.2254, 0.2254]
H	[0.7746, 0.7746, 0.7746]
H	[0.7746, 0.2254, 0.2254]

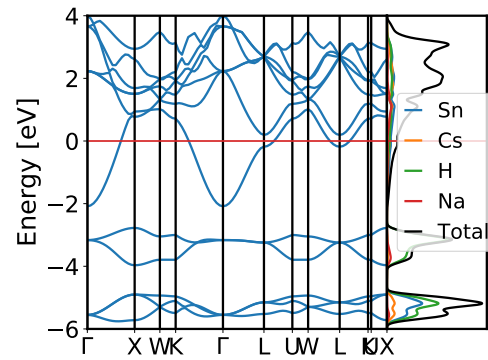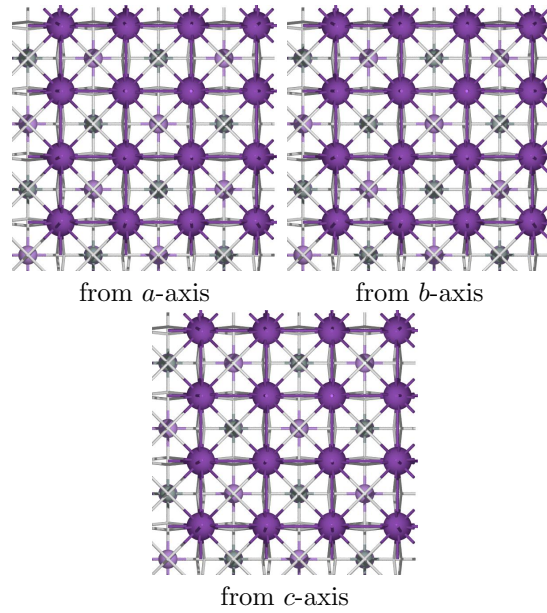

Electron band structure

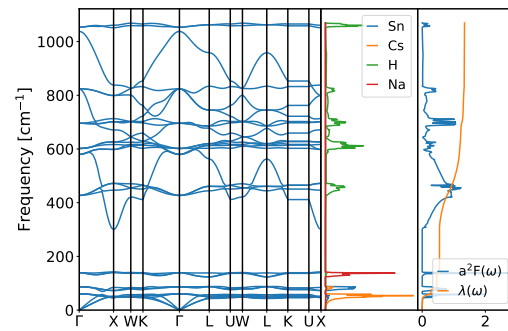


Phonon band structure

#30: K_2AlHgH_6

```

mat id agm004984734
spg 225
nsites 10
e above hull 0.086 eV
e form -0.140 eV
decomposition  $\text{K}_2\text{AlH}_5, \text{K}_2\text{Hg}_7, \text{K}_3\text{Al}_2\text{H}_9, \text{H}_2$ 
ecutwfc 100.0 Ry
kpts coarse  $12 \times 12 \times 12$ 
kpts fine  $24 \times 24 \times 24$ 
qppts  $3 \times 3 \times 3$ 
 $\lambda$  1.148
 $\omega_{\log}$  349 K
 $\omega_2$  701 K
 $T_c^{\text{McMillan}}$  29.6 K
 $T_c^{\text{Allen-Dynes}}$  32.5 K
 $T_c^{\text{Eliashberg}}$  33.8 K


```

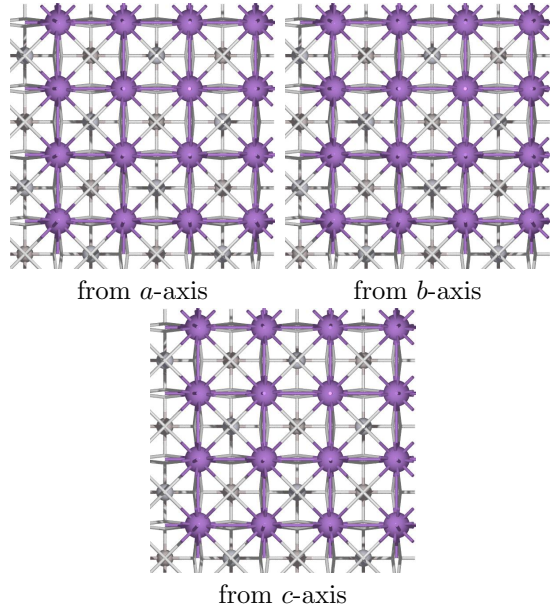


Primitive structure:

a : 5.6450 Å, b : 5.6450 Å, c : 5.6450 Å
 α : 60.00°, β : 60.00°, γ : 60.00°

K	[0.7500, 0.7500, 0.7500]
K	[0.2500, 0.2500, 0.2500]
Al	[0.5000, 0.5000, 0.5000]
Hg	[0.0000, 0.0000, 0.0000]
H	[0.2751, 0.2751, 0.2751]
H	[0.2751, 0.7249, 0.7249]
H	[0.7249, 0.7249, 0.7249]
H	[0.7249, 0.2751, 0.2751]
H	[0.7249, 0.2751, 0.2751]
H	[0.2751, 0.7249, 0.7249]

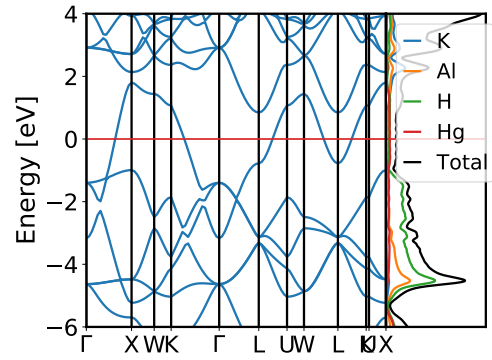

Electron band structure

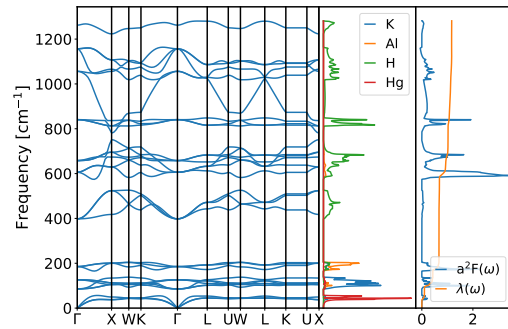

Phonon band structure

#31: K_2HgH_6Au

```



mat id agm004930514
spg 225
nsites 10
e above hull 0.049 eV
e form -0.138 eV
decomposition  $K_2HgH_4, K_2Hg_7, KH_3Au, H_2$ 
ecutwfc 100.0 Ry
kpts coarse  $12 \times 12 \times 12$ 
kpts fine  $24 \times 24 \times 24$ 
qppts  $3 \times 3 \times 3$ 
 $\lambda$  1.056
 $\omega_{log}$  396 K
 $\omega_2$  913 K
 $T_c^{McMillan}$  29.9 K
 $T_c^{Allen-Dynes}$  32.5 K
 $T_c^{Eliashberg}$  39.7 K

```


Primitive structure:

a : 5.6531 Å, b : 5.6531 Å, c : 5.6531 Å
 α : 60.00°, β : 60.00°, γ : 60.00°

K	[0.7500, 0.7500, 0.7500]
K	[0.2500, 0.2500, 0.2500]
Hg	[0.0000, 0.0000, 0.0000]
H	[0.2792, 0.2792, 0.2792]
H	[0.2792, 0.7208, 0.7208]
H	[0.7208, 0.7208, 0.7208]
H	[0.7208, 0.2792, 0.2792]
H	[0.7208, 0.2792, 0.2792]
H	[0.2792, 0.7208, 0.7208]
Au	[0.5000, 0.5000, 0.5000]

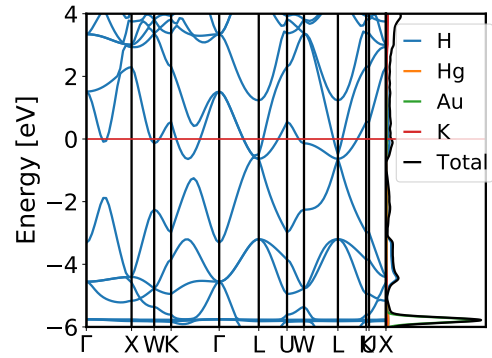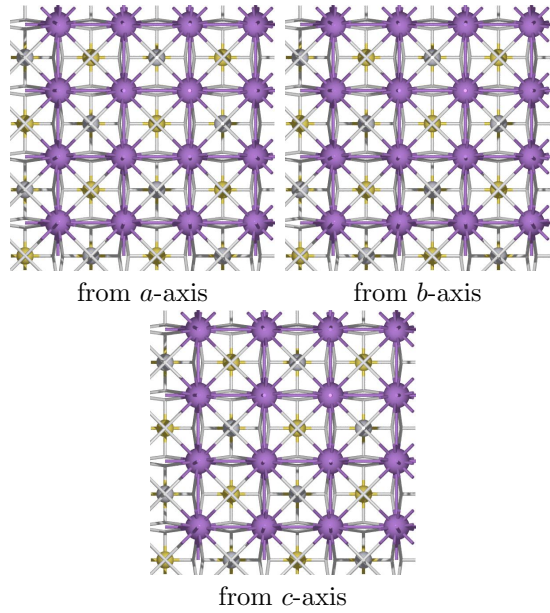

Electron band structure

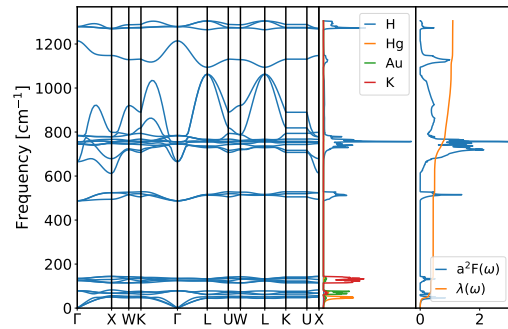

Phonon band structure

#32: K_2InAgH_6

```



mat id agm004930190
spg 225
nsites 10
e above hull 0.032 eV
e form -0.075 eV
decomposition K(InAg)6,H2,KH
ecutwfc 98.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qppts 3×3×3
λ 0.791
ωlog 660 K
ω2 860 K
TcMcMillan 30.2 K
TcAllen-Dynes 31.7 K
TcEliashberg 34.3 K

```


Primitive structure:

a : 5.6271 Å, b : 5.6271 Å, c : 5.6271 Å
 α : 60.00°, β : 60.00°, γ : 60.00°

K	[0.2500, 0.2500, 0.2500]
K	[0.7500, 0.7500, 0.7500]
In	[0.5000, 0.5000, 0.5000]
Ag	[0.0000, 0.0000, 0.0000]
H	[0.2466, 0.7534, 0.7534]
H	[0.2466, 0.2466, 0.2466]
H	[0.2466, 0.7534, 0.7534]
H	[0.7534, 0.2466, 0.2466]
H	[0.7534, 0.7534, 0.7534]
H	[0.7534, 0.2466, 0.2466]

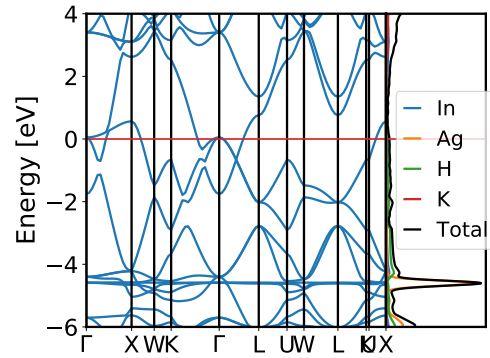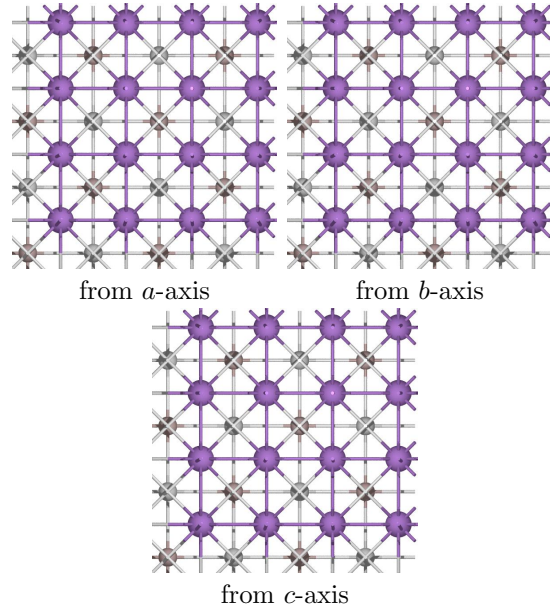

Electron band structure

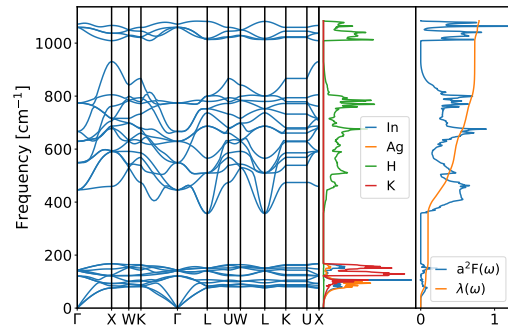


Phonon band structure

#33: $\text{Rb}_2\text{AlHgH}_6$

```

mat id agm004984647
spg 225
nsites 10
e above hull 0.083 eV
e form -0.138 eV
decomposition  $\text{Rb}_5\text{Hg}_{19}, \text{Rb}_3\text{HgH}_5, \text{Rb}_3\text{Al}_2\text{H}_9, \text{H}_2$ 
ecutwfc 100.0 Ry
kpts coarse  $12 \times 12 \times 12$ 
kpts fine  $24 \times 24 \times 24$ 
qppts  $3 \times 3 \times 3$ 
 $\lambda$  2.533
 $\omega_{\log}$  140 K
 $\omega_2$  463 K
 $T_c^{\text{McMillan}}$  23.3 K
 $T_c^{\text{Allen-Dynes}}$  31.4 K
 $T_c^{\text{Eliashberg}}$  43.8 K


```

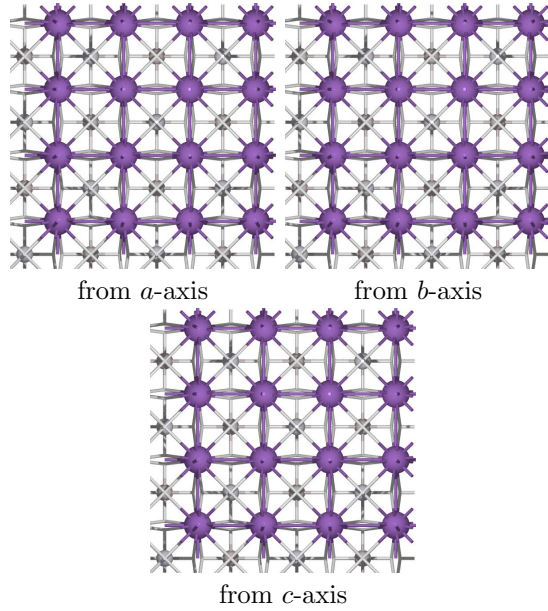


Primitive structure:

a : 5.7626 Å, b : 5.7626 Å, c : 5.7626 Å
 α : 60.00°, β : 60.00°, γ : 60.00°

Rb	[0.2500, 0.2500, 0.2500]
Rb	[0.7500, 0.7500, 0.7500]
Al	[0.0000, 0.0000, 0.0000]
Hg	[0.5000, 0.5000, 0.5000]
H	[0.7788, 0.7788, 0.7788]
H	[0.7788, 0.2212, 0.2212]
H	[0.2212, 0.2212, 0.2212]
H	[0.2212, 0.7788, 0.7788]
H	[0.2212, 0.7788, 0.7788]
H	[0.7788, 0.2212, 0.2212]

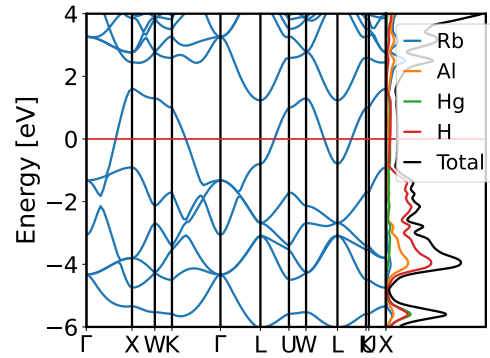

Electron band structure

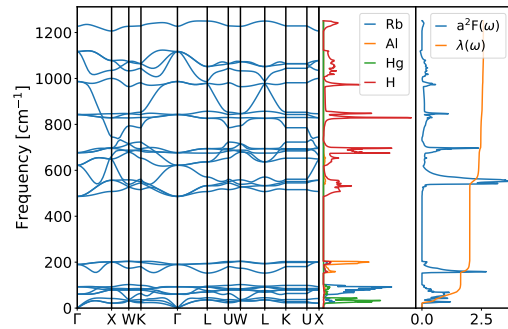


Phonon band structure

#34: Na₂CdCuH₆

```

mat id agm004928403
spg 225
nsites 10
e above hull 0.063 eV
e form -0.035 eV
decomposition Na3(CuH3)2,Na2Cd11,H2,NaH
ecutwfc 132.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qppts 3×3×3
λ 0.691
ωlog 740 K
ω2 986 K
TcMcMillan 25.0 K
TcAllen-Dynes 26.0 K
TcEliashberg 27.3 K

```

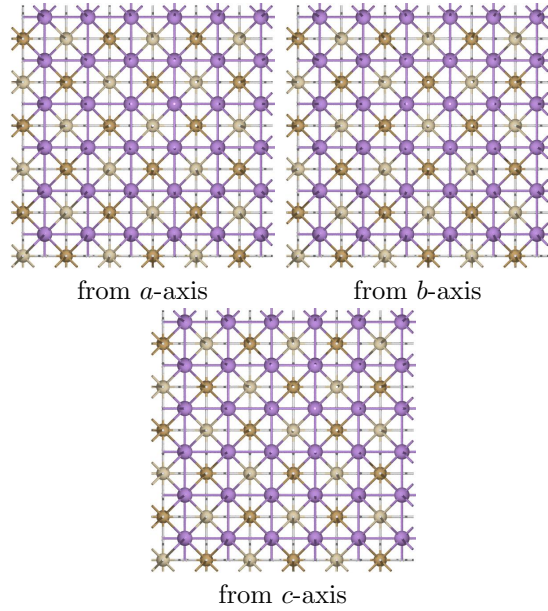


Primitive structure:

a: 5.2050 Å, *b*: 5.2050 Å, *c*: 5.2050 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Na [0.2500, 0.2500, 0.2500]
Na [0.7500, 0.7500, 0.7500]
Cd [0.5000, 0.5000, 0.5000]
Cu [0.0000, 0.0000, 0.0000]
H [0.2309, 0.7691, 0.7691]
H [0.2309, 0.2309, 0.2309]
H [0.2309, 0.7691, 0.7691]
H [0.7691, 0.2309, 0.2309]
H [0.7691, 0.7691, 0.7691]
H [0.7691, 0.2309, 0.2309]

```

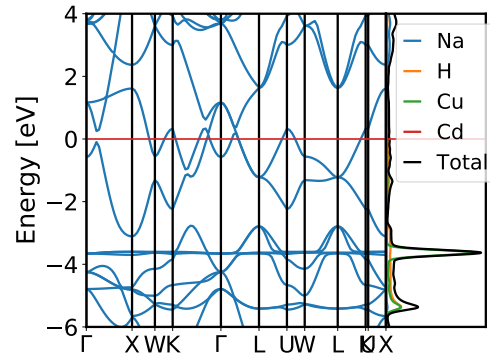

Electron band structure

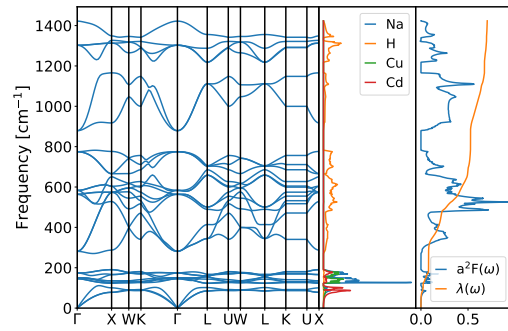

Phonon band structure

#35: Na₂MgCuH₆

```



mat id agm004929626
spg 225
nsites 10
e above hull 0.092 eV
e form -0.089 eV
decomposition NaMgCuH4,H2,NaH
ecutwfc 120.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qppts 3×3×3
λ 1.197
ωlog 251 K
ω2 707 K
TcMcMillan 22.4 K
TcAllen-Dynes 24.7 K
TcEliashberg 29.4 K

```


Primitive structure:

a : 5.1720 Å, b : 5.1720 Å, c : 5.1720 Å
 α : 60.00°, β : 60.00°, γ : 60.00°

Na	[0.7500, 0.7500, 0.7500]
Na	[0.2500, 0.2500, 0.2500]
Mg	[0.0000, 0.0000, 0.0000]
Cu	[0.5000, 0.5000, 0.5000]
H	[0.7340, 0.2660, 0.2660]
H	[0.7340, 0.7340, 0.7340]
H	[0.7340, 0.2660, 0.2660]
H	[0.2660, 0.7340, 0.7340]
H	[0.2660, 0.2660, 0.2660]
H	[0.2660, 0.7340, 0.7340]

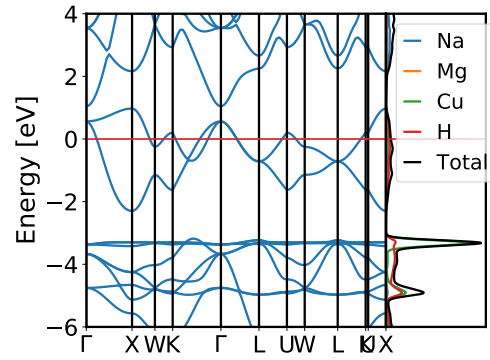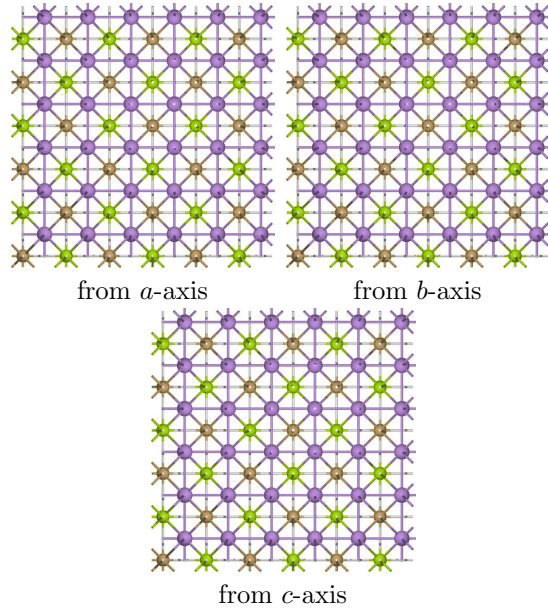


Electron band structure

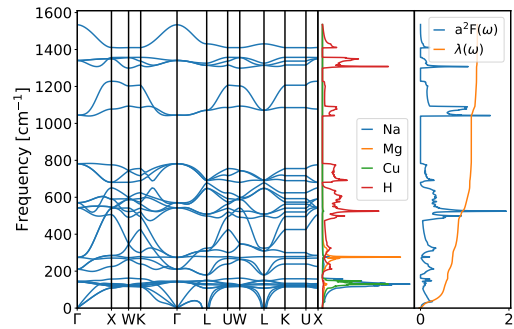

Phonon band structure

#36: $\text{CuH}_6\text{RuPb}_2$


mat id agm004927040
 spg 225
 nsites 10
 e above hull 0.149 eV
 e form 0.149 eV
 decomposition Cu,Ru,H₂,Pb
 ecutwfc 120.0 Ry
 kpts coarse 12×12×12
 kpts fine 24×24×24
 qpts 3×3×3
 λ 1.191
 ω_{log} 243 K
 ω_2 712 K
 T_c^{McMillan} 21.5 K
 $T_c^{\text{Allen-Dynes}}$ 23.7 K
 $T_c^{\text{Eliashberg}}$ 26.2 K

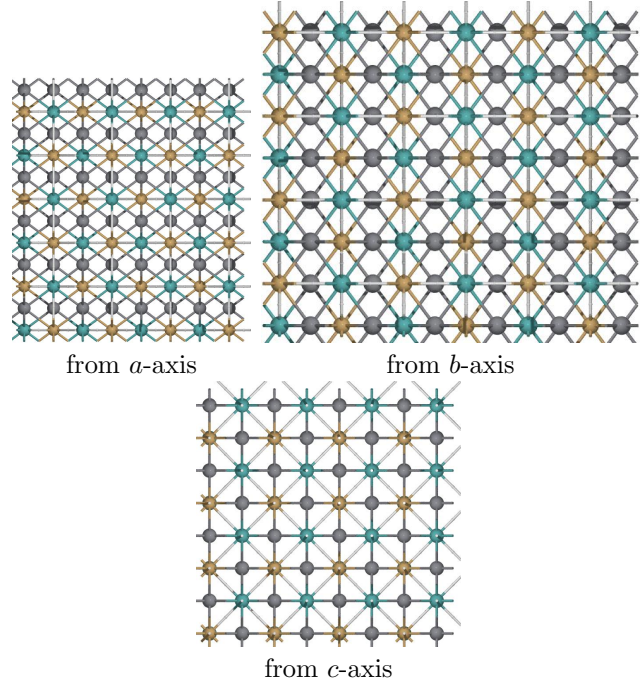


Primitive structure:

a : 5.2383 Å, b : 5.2383 Å, c : 5.2383 Å
 α : 60.00°, β : 60.00°, γ : 60.00°

Cu [0.5000, 0.5000, 0.5000]
 H [0.2429, 0.2429, 0.2429]
 H [0.7571, 0.2429, 0.2429]
 H [0.7571, 0.2429, 0.2429]
 H [0.2429, 0.7571, 0.7571]
 H [0.2429, 0.7571, 0.7571]
 H [0.7571, 0.7571, 0.7571]
 Ru [0.0000, 0.0000, 0.0000]
 Pb [0.2500, 0.2500, 0.2500]
 Pb [0.7500, 0.7500, 0.7500]

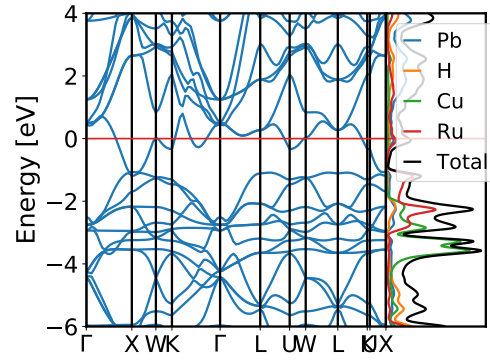

Electron band structure

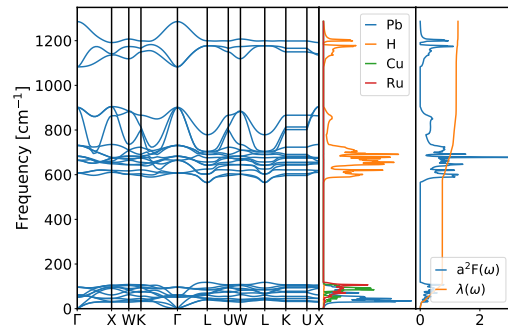


Phonon band structure

#37: K_2AlCdH_6

```

mat id agm004984504
spg 225
nsites 10
e above hull 0.074 eV
e form -0.145 eV
decomposition  $KCd_{13}, K_2AlH_5, K_3Al_2H_9, H_2$ 
ecutwfc 132.0 Ry
kpts coarse  $12 \times 12 \times 12$ 
kpts fine  $24 \times 24 \times 24$ 
qpts  $3 \times 3 \times 3$ 
 $\lambda$  0.739
 $\omega_{log}$  507 K
 $\omega_2$  834 K
 $T_c^{McMillan}$  20.0 K
 $T_c^{Allen-Dynes}$  21.0 K
 $T_c^{Eliashberg}$  20.8 K


```

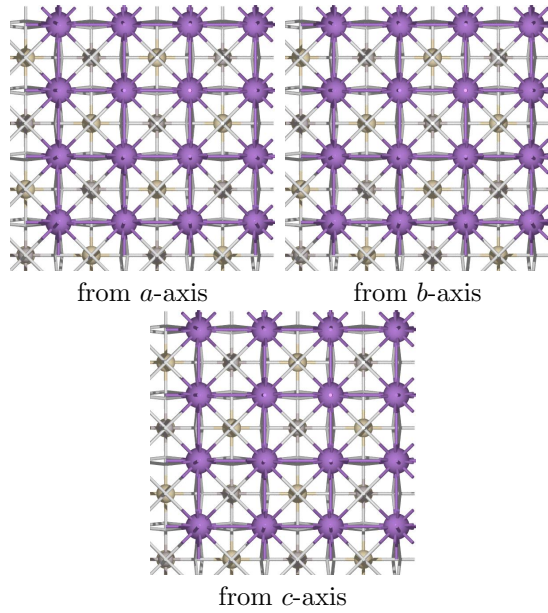


Primitive structure:

a : 5.6380 Å, b : 5.6380 Å, c : 5.6380 Å
 α : 60.00°, β : 60.00°, γ : 60.00°

K	[0.7500, 0.7500, 0.7500]
K	[0.2500, 0.2500, 0.2500]
Al	[0.5000, 0.5000, 0.5000]
Cd	[0.0000, 0.0000, 0.0000]
H	[0.2728, 0.2728, 0.2728]
H	[0.2728, 0.7272, 0.7272]
H	[0.7272, 0.7272, 0.7272]
H	[0.7272, 0.2728, 0.2728]
H	[0.7272, 0.2728, 0.2728]
H	[0.2728, 0.2728, 0.2728]
H	[0.2728, 0.7272, 0.7272]

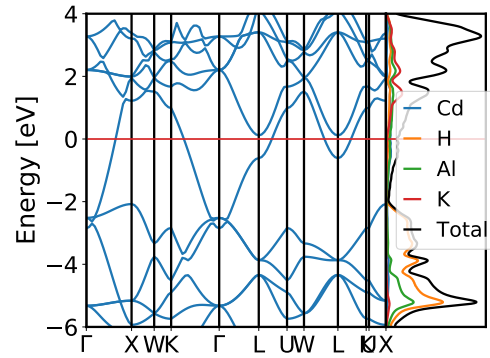

Electron band structure

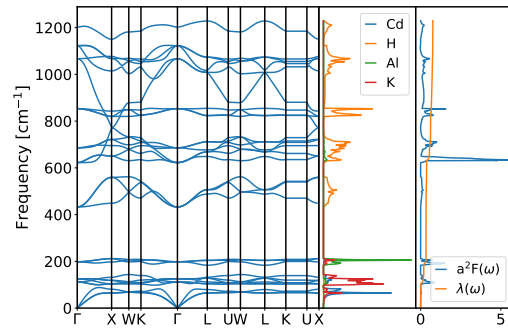

Phonon band structure


IV – OTHER STRUCTURES

#38: Be₈H

```

mat id agm006190471
spg 164
nsites 9
e above hull 0.202 eV
e form 0.190 eV
decomposition BeH2,Be
ecutwfc 118.0 Ry
kpts coarse 12×12×16
kpts fine 24×24×32
qpts 3×3×4
λ 1.337
ωlog 588 K
ω2 718 K
TcMcMillan 59.7 K
TcAllen-Dynes 65.9 K
TcEliashberg 68.7 K

```

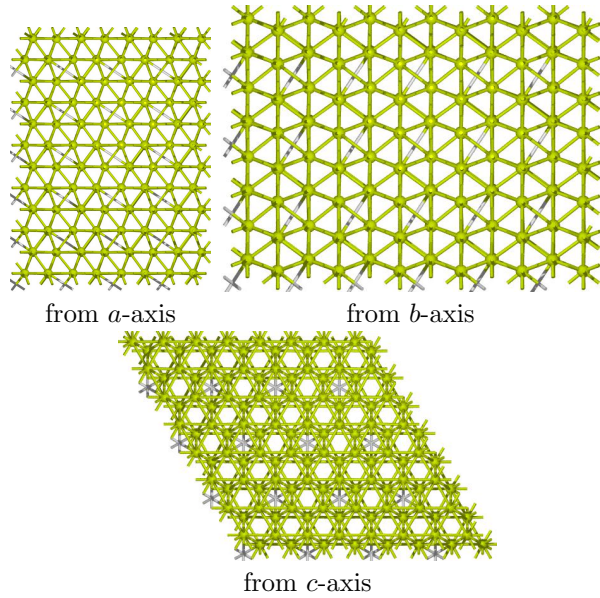


Primitive structure:

a: 4.6591 Å, *b*: 4.6591 Å, *c*: 3.5550 Å
 α : 90.00°, β : 90.00°, γ : 120.00°


```

Be [0.1724, 0.7443, 0.7443]
Be [0.8276, 0.2557, 0.2557]
Be [0.1724, 0.7443, 0.7443]
Be [0.3448, 0.2557, 0.2557]
Be [0.6552, 0.7443, 0.7443]
Be [0.8276, 0.2557, 0.2557]
Be [0.3333, 0.2406, 0.2406]
Be [0.6667, 0.7594, 0.7594]
H [0.0000, 0.0000, 0.0000]

```

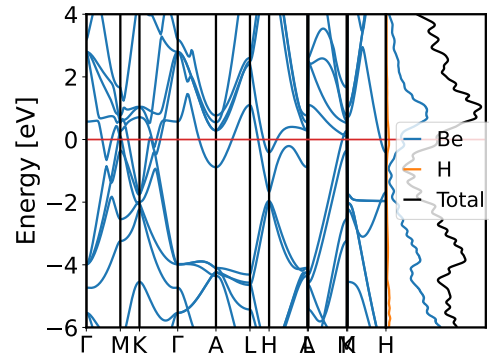

Electron band structure

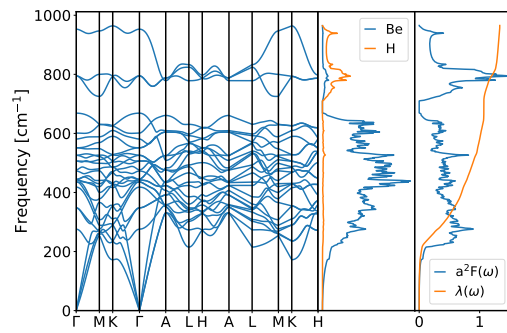


Phonon band structure

#39: SrMg₂H₈Pt

```

mat id agm002280639
spg 164
nsites 12
e above hull 0.117 eV
e form -0.310 eV
decomposition Mg2H4Pt,Sr2H6Pt,SrH6Pt,MgH2
ecutwfc 100.0 Ry
kpts coarse 16×16×8
kpts fine 32×32×16
qpts 4×4×2
λ 1.097
ωlog 568 K
ω2 925 K
TcMcMillan 45.3 K
TcAllen-Dynes 49.4 K
TcEliashberg 53.9 K


```

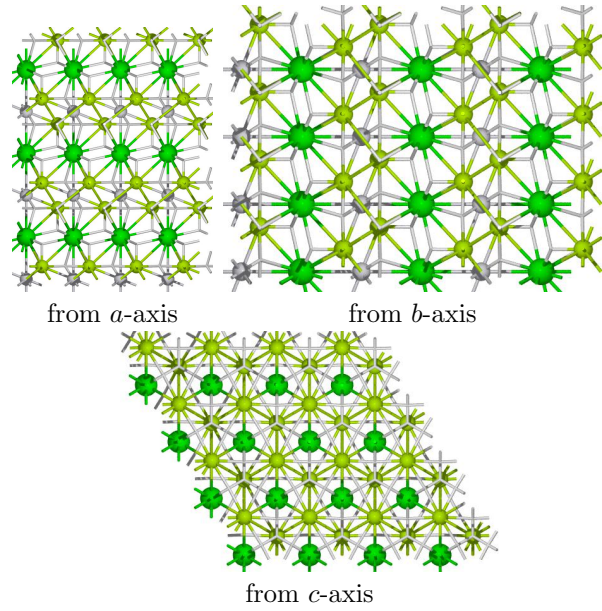


Primitive structure:

a: 4.5011 Å, *b*: 4.5011 Å, *c*: 6.9279 Å
 α : 90.00°, β : 90.00°, γ : 120.00°

Sr	[0.0000, 0.5000, 0.5000]
Mg	[0.6667, 0.1487, 0.1487]
Mg	[0.3333, 0.8513, 0.8513]
H	[0.8218, 0.8445, 0.8445]
H	[0.3565, 0.8445, 0.8445]
H	[0.8218, 0.8445, 0.8445]
H	[0.1782, 0.1555, 0.1555]
H	[0.6435, 0.1555, 0.1555]
H	[0.1782, 0.1555, 0.1555]
H	[0.6667, 0.4180, 0.4180]
H	[0.3333, 0.5820, 0.5820]
Pt	[0.0000, 0.0000, 0.0000]

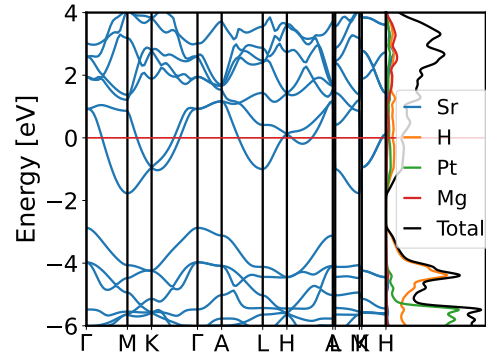

Electron band structure

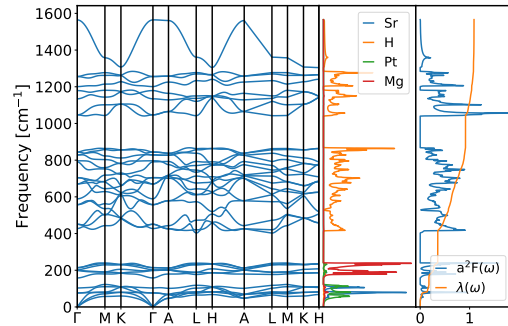


Phonon band structure

#40: SrMg₂H₈Pd

```

mat id agm002280638
spg 164
nsites 12
e above hull 0.093 eV
e form -0.276 eV
decomposition MgH2,SrH3Pd,H2
ecutwfc 98.0 Ry
kpts coarse 16×16×8
kpts fine 32×32×16
qppts 4×4×2
λ 1.005
ωlog 652 K
ω2 925 K
TcMcmillan 45.7 K
TcAllen-Dynes 49.1 K
TcEliashberg 52.4 K

```

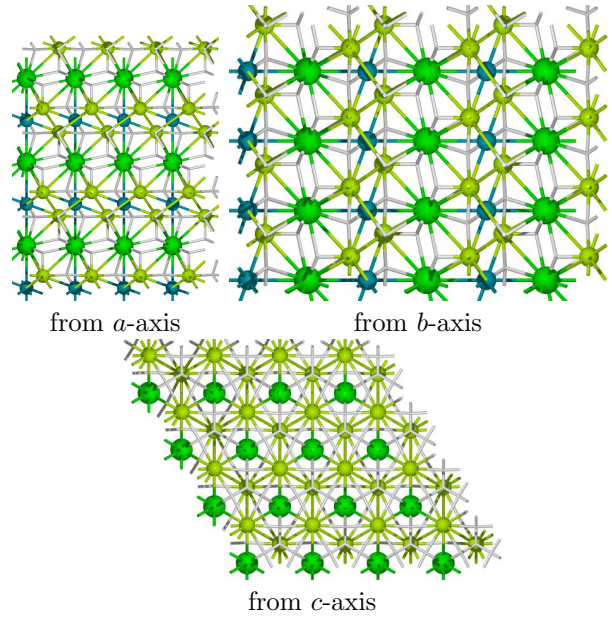


Primitive structure:

a: 4.5138 Å, *b*: 4.5138 Å, *c*: 6.7671 Å
 α : 90.00°, β : 90.00°, γ : 120.00°


```

Sr [0.0000, 0.5000, 0.5000]
Mg [0.6667, 0.1415, 0.1415]
Mg [0.3333, 0.8585, 0.8585]
H [0.8196, 0.8447, 0.8447]
H [0.3608, 0.8447, 0.8447]
H [0.8196, 0.8447, 0.8447]
H [0.1804, 0.1553, 0.1553]
H [0.6392, 0.1553, 0.1553]
H [0.1804, 0.1553, 0.1553]
H [0.6667, 0.4193, 0.4193]
H [0.3333, 0.5807, 0.5807]
Pd [0.0000, 0.0000, 0.0000]

```

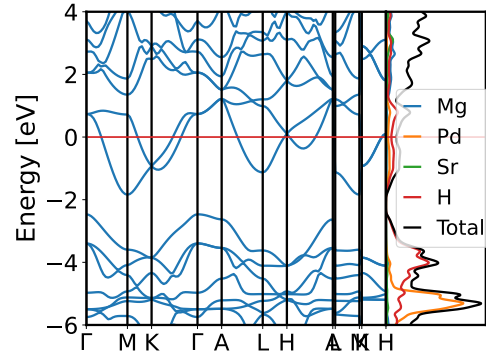

Electron band structure

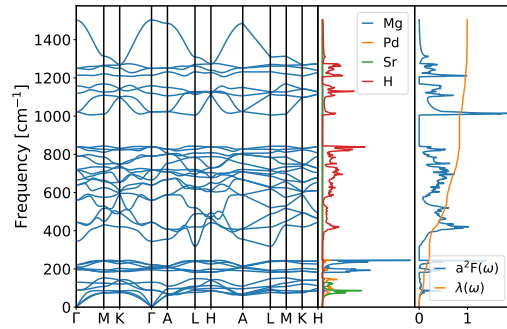


Phonon band structure

#41: BaMg₂H₈Pd

```

mat id agm002280631
spg 164
nsites 12
e above hull 0.063 eV
e form -0.292 eV
decomposition Ba2Mg3H10,Mg(HPd)2,H2
ecutwfc 98.0 Ry
kpts coarse 16×16×8
kpts fine 32×32×16
qppts 4×4×2
λ 0.917
ωlog 645 K
ω2 939 K
TcMcMillan 39.0 K
TcAllen-Dynes 41.6 K
TcEliashberg 44.1 K


```

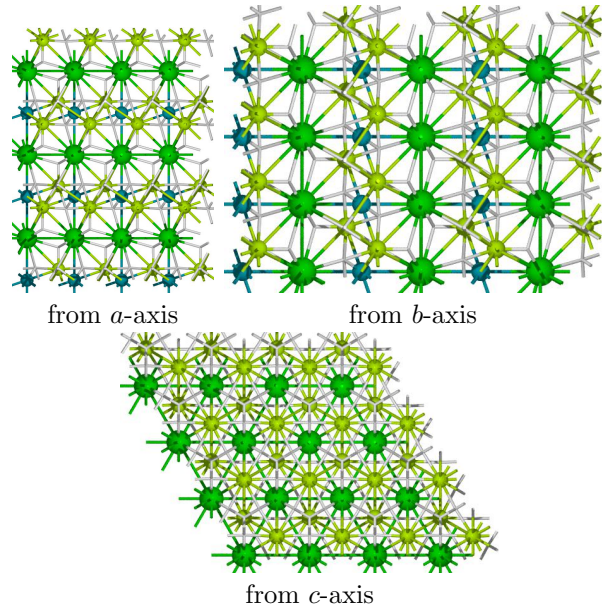


Primitive structure:

a: 4.5852 Å, *b*: 4.5852 Å, *c*: 7.0777 Å
 α : 90.00°, β : 90.00°, γ : 120.00°

Ba	[0.0000, 0.5000, 0.5000]
Mg	[0.6667, 0.8689, 0.8689]
Mg	[0.3333, 0.1311, 0.1311]
H	[0.3561, 0.1464, 0.1464]
H	[0.8220, 0.1464, 0.1464]
H	[0.8220, 0.1464, 0.1464]
H	[0.6439, 0.8536, 0.8536]
H	[0.1780, 0.8536, 0.8536]
H	[0.1780, 0.8536, 0.8536]
H	[0.6667, 0.6039, 0.6039]
H	[0.3333, 0.3961, 0.3961]
Pd	[0.0000, 0.0000, 0.0000]

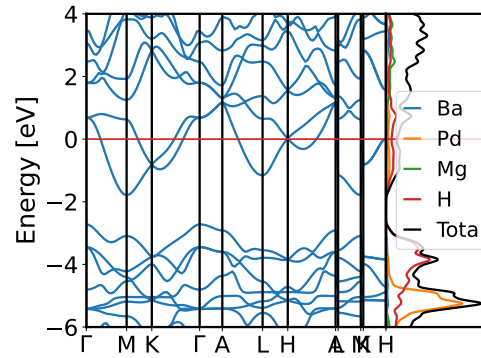

Electron band structure

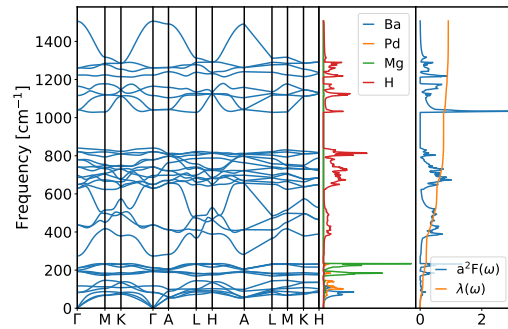


Phonon band structure

#42: BaMg₂H₈Pt

```

mat id agm002280563
spg 164
nsites 12
e above hull 0.102 eV
e form -0.332 eV
decomposition Mg2H4Pt,Ba2Mg3H10,BaH6Pt,MgH2
ecutwfc 100.0 Ry
kpts coarse 16×16×8
kpts fine 32×32×16
qpts 4×4×2
λ 0.922
ωlog 590 K
ω2 961 K
TcMcMillan 36.0 K
TcAllen-Dynes 38.4 K
TcEliashberg 40.4 K


```

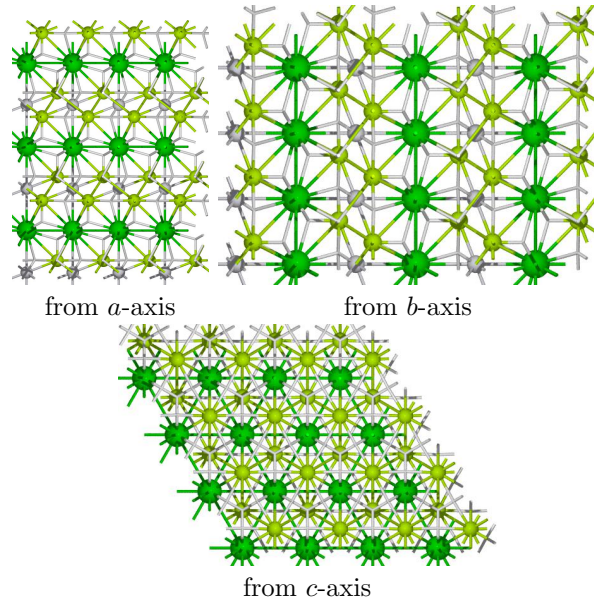


Primitive structure:

a: 4.5649 Å, *b*: 4.5649 Å, *c*: 7.2465 Å
 α : 90.00°, β : 90.00°, γ : 120.00°

Ba	[0.0000, 0.5000, 0.5000]
Mg	[0.6667, 0.8598, 0.8598]
Mg	[0.3333, 0.1402, 0.1402]
H	[0.3515, 0.1469, 0.1469]
H	[0.8243, 0.1469, 0.1469]
H	[0.8243, 0.1469, 0.1469]
H	[0.6485, 0.8531, 0.8531]
H	[0.1757, 0.8531, 0.8531]
H	[0.1757, 0.8531, 0.8531]
H	[0.6667, 0.6033, 0.6033]
H	[0.3333, 0.3967, 0.3967]
Pt	[0.0000, 0.0000, 0.0000]

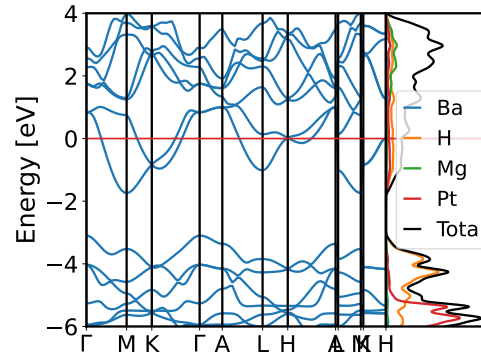

Electron band structure

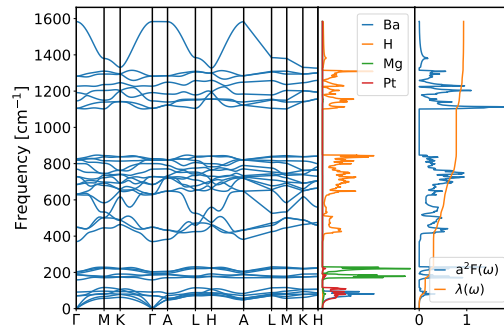


Phonon band structure

#43: Na₂H₄Au

```

mat id agm002153449
spg 139
nsites 7
e above hull 0.035 eV
e form -0.148 eV
decomposition NaH3Au,NaH
ecutwfc 96.0 Ry
kpts coarse 16×16×16
kpts fine 32×32×32
qpts 4×4×4
λ 1.312
ωlog 394 K
ω2 598 K
TcMcMillan 39.1 K
TcAllen-Dynes 43.8 K
TcEliashberg 47.3 K


```

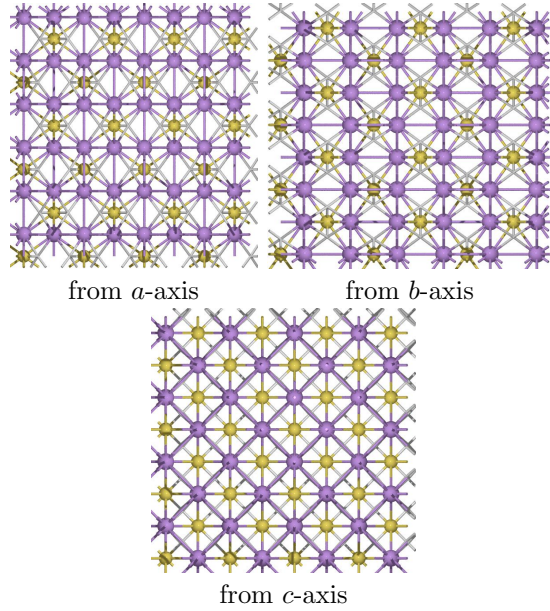


Primitive structure:

a: 5.0415 Å, *b*: 5.0415 Å, *c*: 5.0415 Å
 α : 120.69°, β : 120.69°, γ : 88.81°

Na	[0.7500, 0.5000, 0.5000]
Na	[0.2500, 0.5000, 0.5000]
H	[0.7627, 0.5253, 0.5253]
H	[0.2373, 0.4747, 0.4747]
H	[0.2373, 0.0000, 0.0000]
H	[0.7627, 0.0000, 0.0000]
Au	[0.0000, 0.0000, 0.0000]

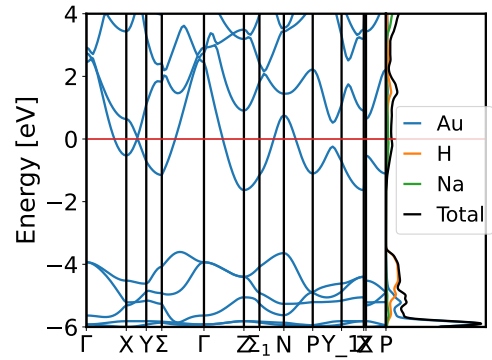


Electron band structure

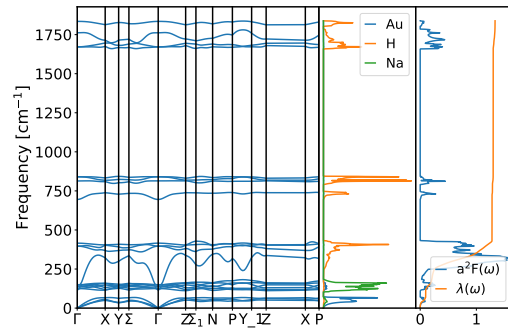

Phonon band structure

#44: LiH₂Pd


mat id agm001945535
 spg 166
 nsites 4
 e above hull 0.108 eV
 e form -0.350 eV
 decomposition LiH₂Pd
 ecutwfc 104.0 Ry
 kpts coarse 20×20×20
 kpts fine 40×40×40
 qpts 5×5×5
 λ 0.981
 ω_{log} 532 K
 ω₂ 849 K
 T_c^{Mcmillan} 35.9 K
 T_c^{Allen-Dynes} 38.6 K
 T_c^{Eliashberg} 43.2 K

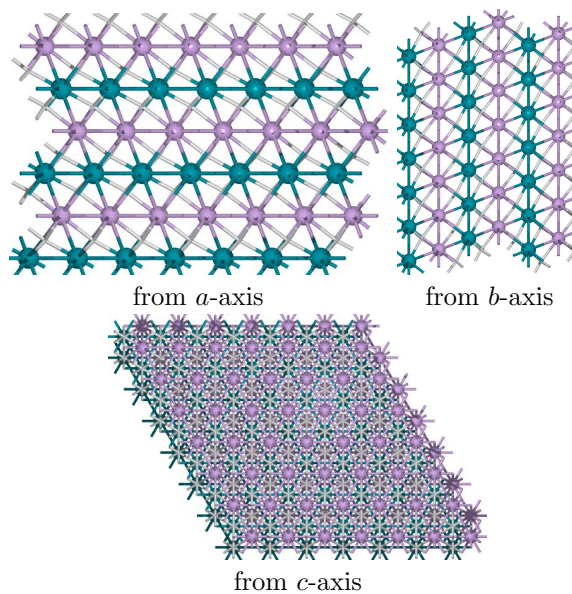


Primitive structure:

$a: 4.7796 \text{ \AA}, b: 4.7796 \text{ \AA}, c: 4.7796 \text{ \AA}$
 $\alpha: 35.62^\circ, \beta: 35.62^\circ, \gamma: 35.62^\circ$

Li [0.5000, 0.5000, 0.5000]
 H [0.7346, 0.7346, 0.7346]
 H [0.2654, 0.2654, 0.2654]
 Pd [0.0000, 0.0000, 0.0000]

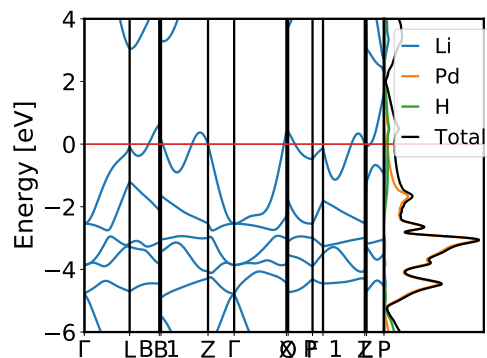

Electron band structure

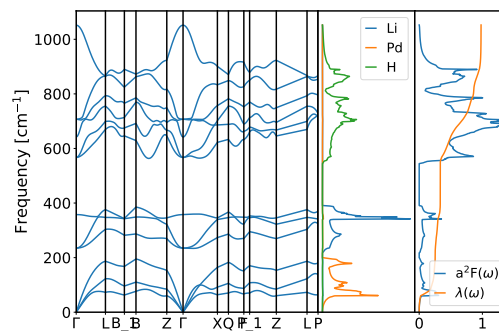

Phonon band structure

#45: NaH₃Pd

```

mat id agm003068400
spg 227
nsites 20
e above hull 0.193 eV
e form -0.139 eV
decomposition NaH3Pd
ecutwfc 98.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qppts 3×3×3
λ 1.556
ωlog 215 K
ω2 722 K
TcMcMillan 25.3 K
TcAllen-Dynes 29.3 K
TcEliashberg 34.4 K

```



Primitive structure:

a : 6.5808 Å, b : 6.5808 Å, c : 6.5808 Å
 α : 60.00°, β : 60.00°, γ : 60.00°


```

Na [0.1250, 0.1250, 0.1250]
Na [0.1250, 0.6250, 0.6250]
Na [0.1250, 0.1250, 0.1250]
Na [0.6250, 0.1250, 0.1250]
H [0.3053, 0.3053, 0.3053]
H [0.5553, 0.5553, 0.5553]
H [0.9447, 0.5553, 0.5553]
H [0.9447, 0.9447, 0.9447]
H [0.9447, 0.5553, 0.5553]
H [0.6947, 0.3053, 0.3053]
H [0.5553, 0.9447, 0.9447]
H [0.5553, 0.9447, 0.9447]
H [0.3053, 0.6947, 0.6947]
H [0.6947, 0.6947, 0.6947]
H [0.6947, 0.3053, 0.3053]
H [0.3053, 0.6947, 0.6947]
Pd [0.6250, 0.6250, 0.6250]
Pd [0.6250, 0.1250, 0.1250]
Pd [0.6250, 0.6250, 0.6250]
Pd [0.1250, 0.6250, 0.6250]

```

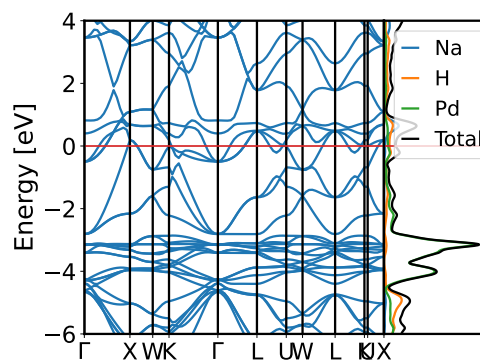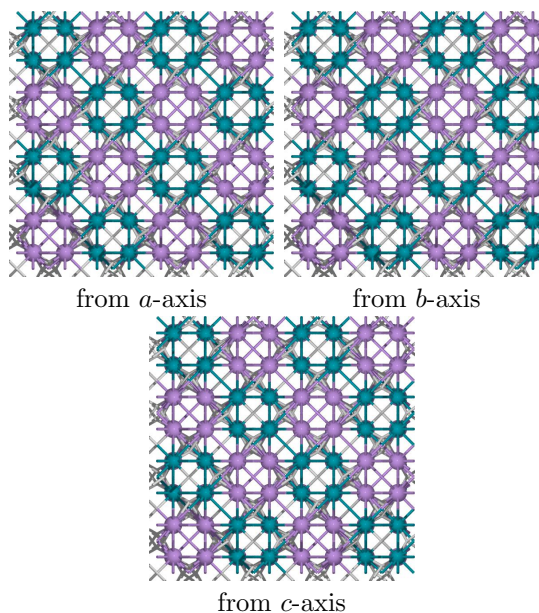

Electron band structure

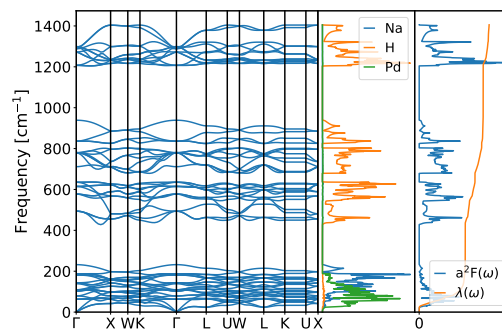


Phonon band structure

#46: $\text{Na}_3\text{H}_9\text{Pd}_2$

```

mat id agm005611460
spg 164
nsites 14
e above hull 0.086 eV
e form -0.199 eV
decomposition  $\text{Na}_2\text{H}_6\text{Pd}, \text{NaH}_3\text{Pd}$ 
ecutwfc 98.0 Ry
kpts coarse  $12 \times 12 \times 12$ 
kpts fine  $24 \times 24 \times 24$ 
qppts  $3 \times 3 \times 3$ 
lambda 0.797
omega_log 516 K
omega_2 1031 K
Tc^McMillan 24.0 K
Tc^Allen-Dynes 25.3 K
Tc^Eliashberg 25.9 K

```

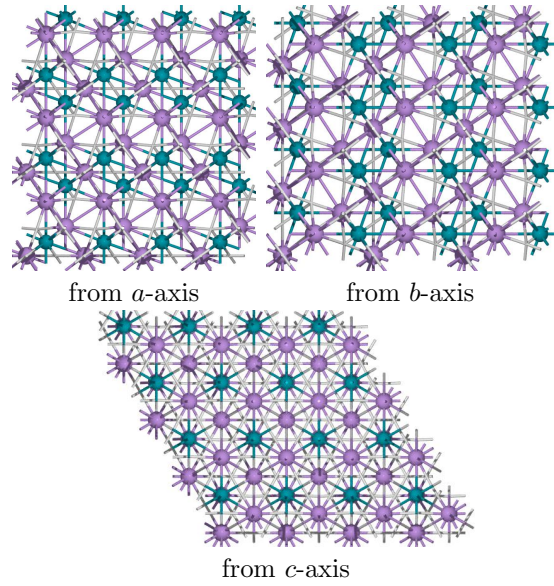


Primitive structure:

a: 4.9650 Å, *b*: 4.9650 Å, *c*: 6.1997 Å
 α : 90.00°, β : 90.00°, γ : 120.00°


```

Na [0.6667, 0.6509, 0.6509]
Na [0.0000, 0.0000, 0.0000]
Na [0.3333, 0.3491, 0.3491]
H [0.1746, 0.6814, 0.6814]
H [0.1746, 0.6814, 0.6814]
H [0.5000, 0.0000, 0.0000]
H [0.8254, 0.3186, 0.3186]
H [0.3491, 0.3186, 0.3186]
H [0.6509, 0.6814, 0.6814]
H [0.8254, 0.3186, 0.3186]
H [0.0000, 0.0000, 0.0000]
H [0.5000, 0.0000, 0.0000]
Pd [0.6667, 0.1659, 0.1659]
Pd [0.3333, 0.8341, 0.8341]

```

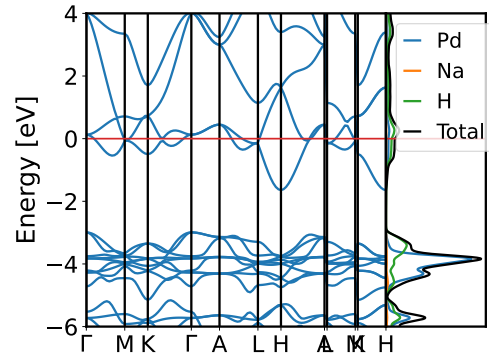

Electron band structure

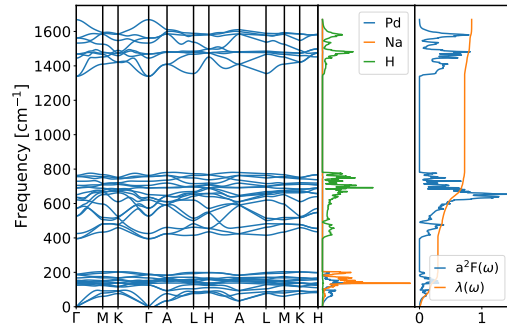

Phonon band structure

#47: $\text{Li}_2\text{H}_2\text{Au}$

```



mat id agm002153052
spg 139
nsites 5
e above hull 0.059 eV
e form -0.353 eV
decomposition LiHAu,LiH
ecutwfc 104.0 Ry
kpts coarse 16×16×16
kpts fine 32×32×32
qpts 4×4×4
λ 0.855
ωlog 368 K
ω2 762 K
TcMcMillan 19.6 K
TcAllen-Dynes 20.8 K
TcEliashberg 21.8 K

```


Primitive structure:

a : 6.0824 Å, b : 6.0824 Å, c : 6.0824 Å
 α : 151.54°, β : 151.54°, γ : 40.69°

Li	[0.6501, 0.0000, 0.0000]
Li	[0.3499, 0.0000, 0.0000]
H	[0.8447, 0.0000, 0.0000]
H	[0.1553, 0.0000, 0.0000]
Au	[0.0000, 0.0000, 0.0000]

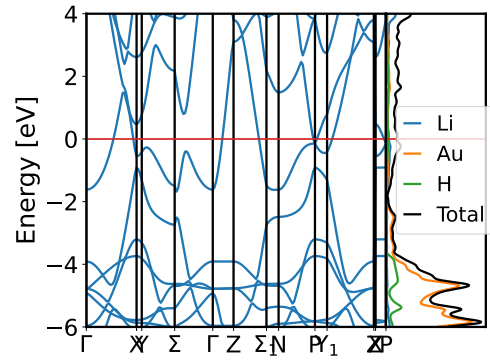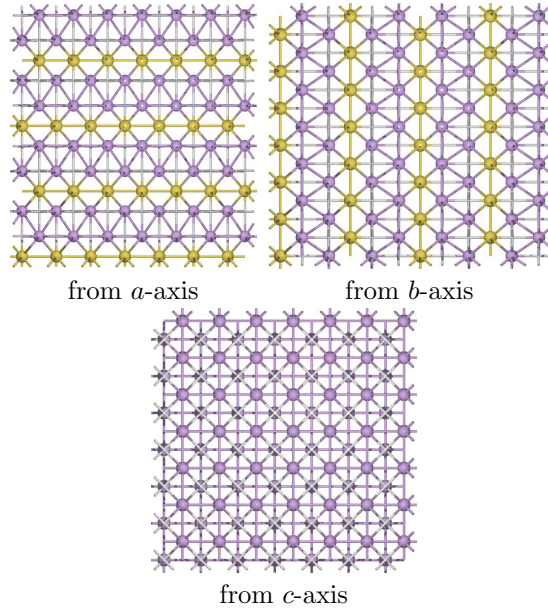

Electron band structure

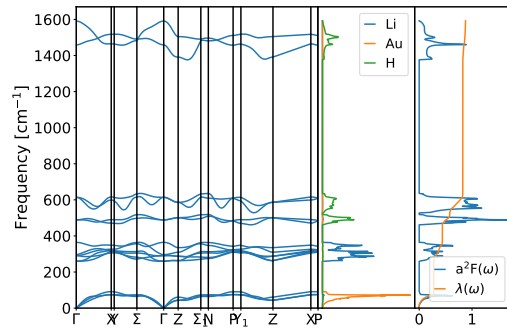


Phonon band structure

#48: Li_4BeH_5

```

mat id agm003659872
spg 79
nsites 10
e above hull 0.155 eV
e form -0.233 eV
decomposition  $\text{Li}_2\text{BeH}_4, \text{Be}, \text{LiH}$ 
ecutwfc 118.0 Ry
kpts coarse  $12 \times 12 \times 12$ 
kpts fine  $24 \times 24 \times 24$ 
qpts  $3 \times 3 \times 3$ 
   $\lambda$  1.042
   $\omega_{\log}$  465 K
   $\omega_2$  716 K
   $T_c^{\text{McMillan}}$  34.4 K
   $T_c^{\text{Allen-Dynes}}$  37.3 K
   $T_c^{\text{Eliashberg}}$  38.2 K
  
```

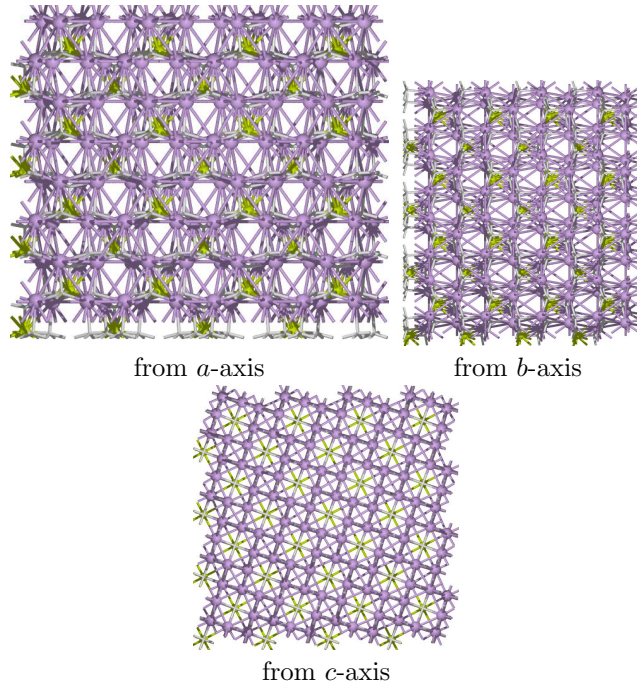


Primitive structure:


a : 4.7358 Å, b : 4.7358 Å, c : 4.7358 Å
 α : 106.64°, β : 106.64°, γ : 115.31°

```

Li [0.8495, 0.4200, 0.4200]
Li [0.6638, 0.8143, 0.8143]
Li [0.4296, 0.1857, 0.1857]
Li [0.2438, 0.5800, 0.5800]
Be [0.9205, 0.0000, 0.0000]
H [0.2172, 0.3639, 0.3639]
H [0.0318, 0.8146, 0.8146]
H [0.8533, 0.1854, 0.1854]
H [0.6678, 0.6361, 0.6361]
H [0.6124, 0.0000, 0.0000]
  
```

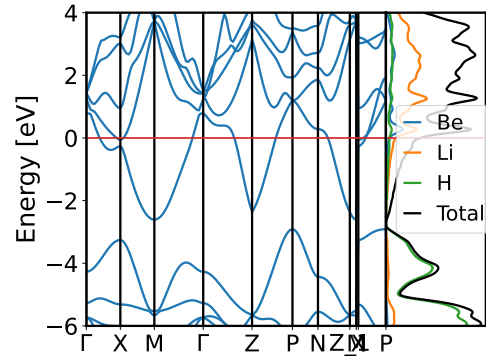

Electron band structure

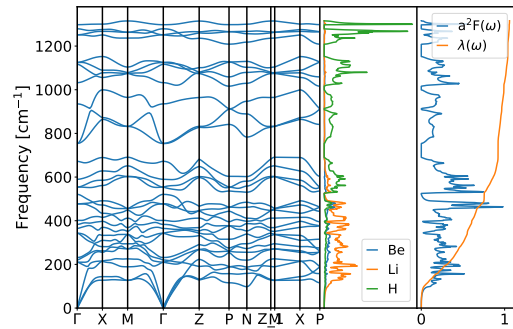

Phonon band structure

#49: HPd

```



mat id agm003157455
spg 225
nsites 2
e above hull 0.008 eV
e form -0.176 eV
decomposition HPd
ecutwfc 98.0 Ry
kpts coarse 24×24×24
kpts fine 48×48×48
qppts 6×6×6
λ 1.239
ωlog 342 K
ω2 429 K
TcMcMillan 31.9 K
TcAllen-Dynes 34.9 K
TcEliashberg 37.4 K

```


Primitive structure:

a : 2.8728 Å, b : 2.8728 Å, c : 2.8728 Å
 α : 60.00°, β : 60.00°, γ : 60.00°

H [0.5000, 0.5000, 0.5000]
 Pd [0.0000, 0.0000, 0.0000]

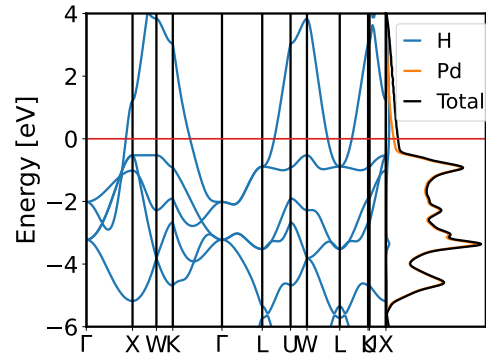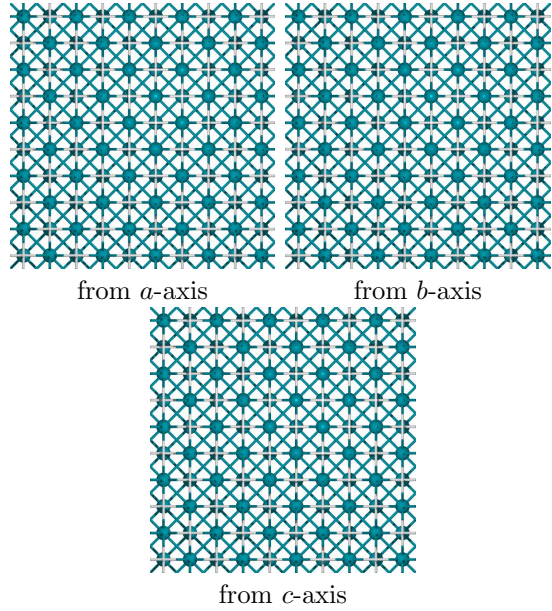

Electron band structure

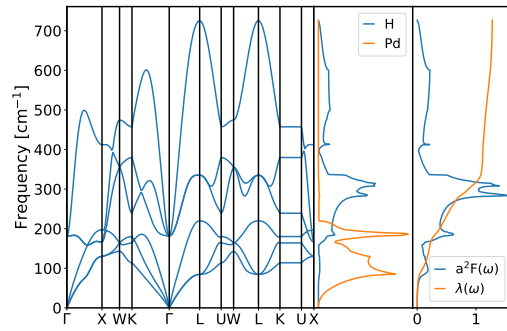

Phonon band structure

#50: InH

```



mat id agm002078382
spg 191
nsites 2
e above hull 0.223 eV
e form 0.223 eV
decomposition H2,In
ecutwfc 98.0 Ry
kpts coarse 24×24×20
kpts fine 48×48×40
qpts 6×6×5
λ 1.207
ωlog 312 K
ω2 724 K
TcMcMillan 28.2 K
TcAllen-Dynes 31.2 K
TcEliashberg 32.6 K

```


Primitive structure:

a : 3.0473 Å, b : 3.0473 Å, c : 3.8561 Å
 α : 90.00°, β : 90.00°, γ : 120.00°

In [0.0000, 0.5000, 0.5000]
 H [0.0000, 0.0000, 0.0000]

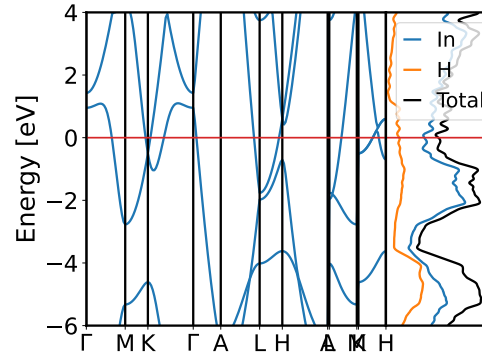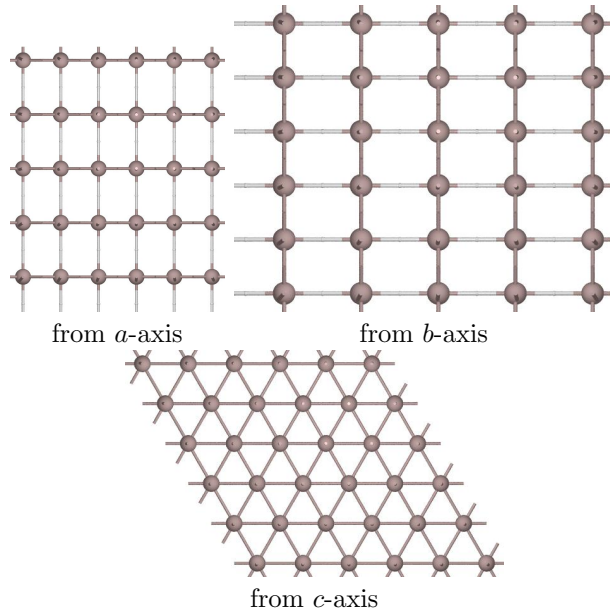

Electron band structure

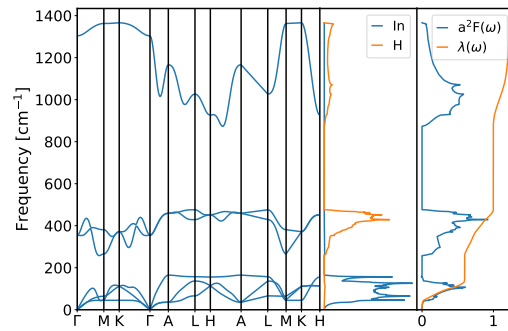

Phonon band structure

#51: ZrH₃

```

mat id agm001282320
spg 139
nsites 4
e above hull 0.105 eV
e form -0.428 eV
decomposition Zr4H15,ZrH2
ecutwfc 98.0 Ry
kpts coarse 20×20×20
kpts fine 40×40×40
qppts 5×5×5
λ 0.967
ωlog 363 K
ω2 747 K
TcMcMillan 24.0 K
TcAllen-Dynes 25.8 K
TcEliashberg 24.9 K

```



Primitive structure:

a : 3.6258 Å, b : 3.6258 Å, c : 3.6258 Å
 α : 129.51°, β : 129.51°, γ : 74.18°


```

Zr [0.0000, 0.0000, 0.0000]
H [0.7500, 0.5000, 0.5000]
H [0.5000, 0.0000, 0.0000]
H [0.2500, 0.5000, 0.5000]

```

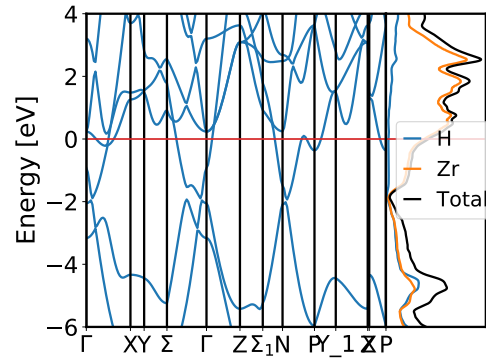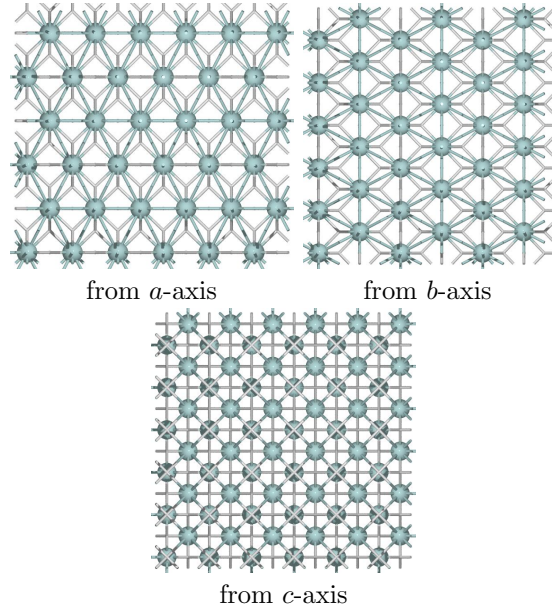


Electron band structure

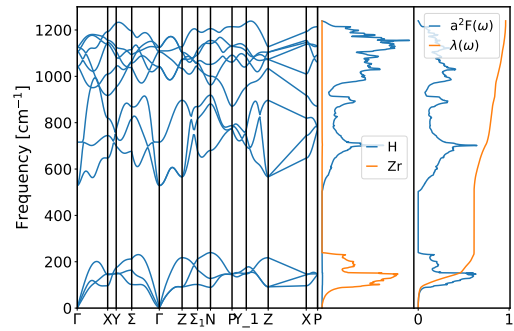

Phonon band structure

#52: InH₃


mat id agm002153249
 spg 167
 nsites 8
 e above hull 0.286 eV
 e form 0.286 eV
 decomposition H₂,In
 ecutwfc 98.0 Ry
 kpts coarse 16×16×16
 kpts fine 32×32×32
 qpts 4×4×4
 λ 1.167
 ω_{log} 218 K
 ω₂ 700 K
 T_c^{Mcmillan} 18.8 K
 T_c^{Allen-Dynes} 20.7 K
 T_c^{Eliashberg} 24.6 K

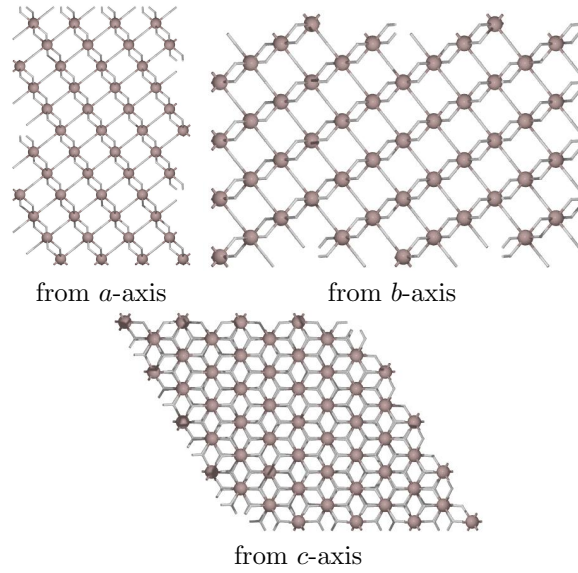


Primitive structure:

a : 5.1459 Å, b : 5.1459 Å, c : 5.1459 Å
 α : 54.38°, β : 54.38°, γ : 54.38°

In [0.0000, 0.0000, 0.0000]
 In [0.5000, 0.5000, 0.5000]
 H [0.4219, 0.7500, 0.7500]
 H [0.0781, 0.4219, 0.4219]
 H [0.2500, 0.9219, 0.9219]
 H [0.9219, 0.5781, 0.5781]
 H [0.5781, 0.2500, 0.2500]
 H [0.7500, 0.0781, 0.0781]

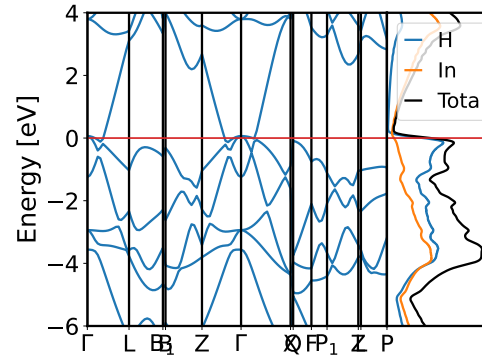

Electron band structure

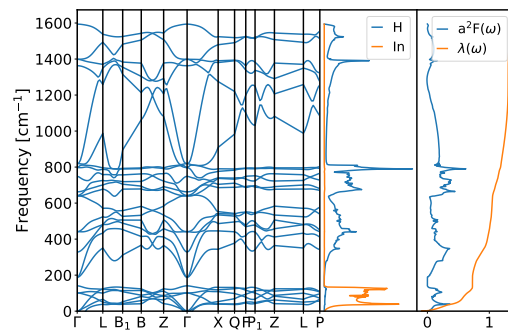


Phonon band structure

#53: Hf(ZrH₄)₂

```

mat id agm005945812
spg 71
nsites 11
e above hull 0.094 eV
e form -0.459 eV
decomposition HfZrH4,Hf2ZrH6,Zr4H15
ecutwfc 144.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qppts 3×3×3
λ 1.158
ωlog 266 K
ω2 663 K
TcMcMillan 22.8 K
TcAllen-Dynes 25.1 K
TcEliashberg 25.3 K

```

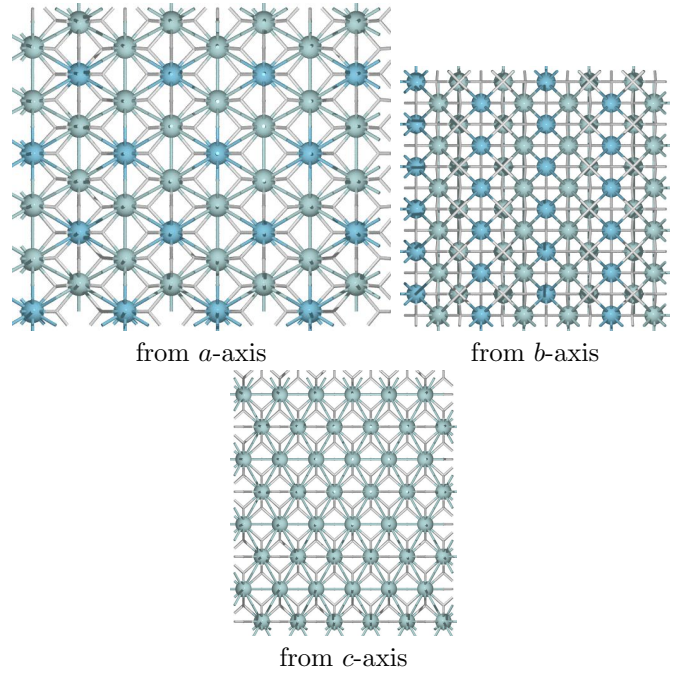


Primitive structure:

a: 5.6748 Å, *b*: 5.6748 Å, *c*: 5.6748 Å
 α : 148.04°, β : 122.93°, γ : 66.92°


```

Hf [1.0000, 0.5000, 0.5000]
Zr [0.6717, 0.5000, 0.5000]
Zr [0.3283, 0.5000, 0.5000]
H [0.9054, 0.2456, 0.2456]
H [0.5858, 0.2456, 0.2456]
H [0.1668, 0.0000, 0.0000]
H [0.2567, 0.2567, 0.2567]
H [0.8332, 0.0000, 0.0000]
H [0.4142, 0.7544, 0.7544]
H [0.0946, 0.7544, 0.7544]
H [0.7433, 0.7433, 0.7433]

```

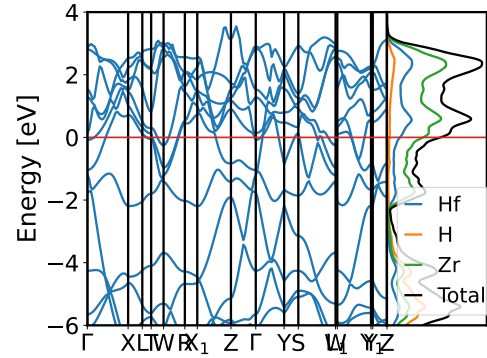

Electron band structure

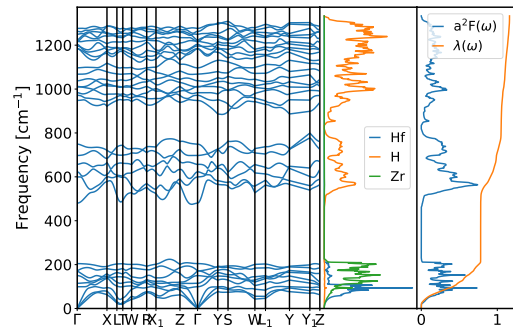


Phonon band structure

#54: KBeH6Pt

```

mat id agm005096310
spg 149
nsites 9
e above hull 0.138 eV
e form -0.199 eV
decomposition Be2Pt,K2H6Pt,H2
ecutwfc 118.0 Ry
kpts coarse 16x16x12
kpts fine 32x32x24
qpts 4x4x3
lambda 1.273
omega_log 371 K
omega_2 764 K
Tc_McMillan 35.6 K
Tc_Allen-Dynes 39.9 K
Tc_Eliashberg 42.1 K


```

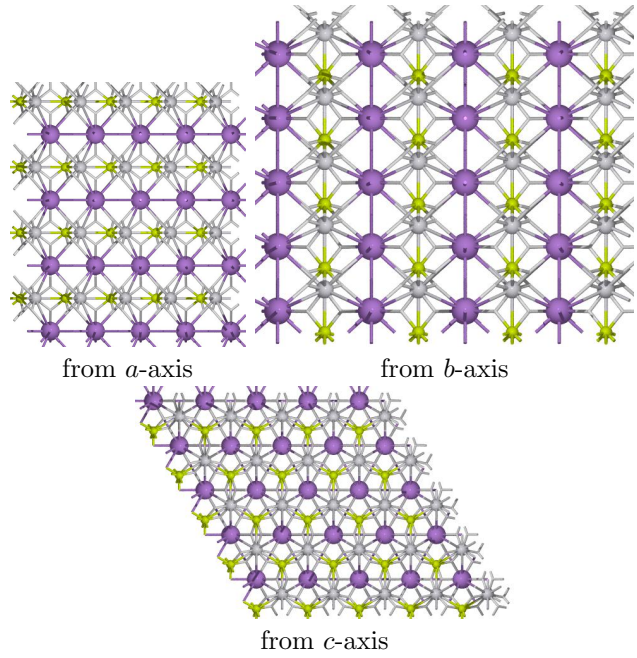


Primitive structure:

a: 4.3795 Å, *b*: 4.3795 Å, *c*: 5.5329 Å
 α : 90.00°, β : 90.00°, γ : 120.00°

K	[0.3333, 0.0000, 0.0000]
Be	[0.0000, 0.5000, 0.5000]
H	[0.7348, 0.3176, 0.3176]
H	[0.3278, 0.6824, 0.6824]
H	[0.7348, 0.6824, 0.6824]
H	[0.9374, 0.6824, 0.6824]
H	[0.9374, 0.3176, 0.3176]
H	[0.3278, 0.3176, 0.3176]
Pt	[0.6667, 0.5000, 0.5000]

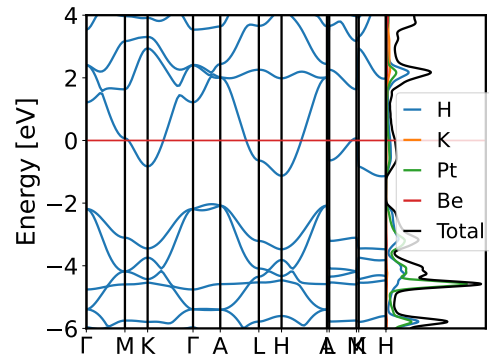

Electron band structure

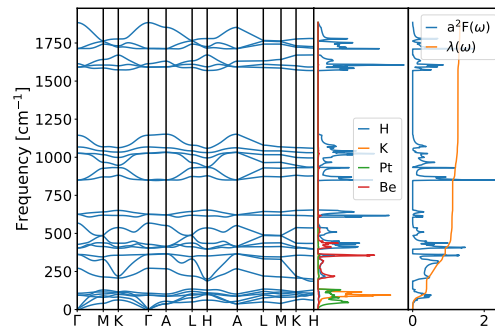

Phonon band structure



#55: RbBeH₆Pt

mat id agm005096259
 spg 149
 nsites 9
 e above hull 0.135 eV
 e form -0.196 eV
 decomposition Be₂Pt,Rb₂H₆Pt,H₂
 ecutfc 118.0 Ry
 kpts coarse 16×16×12
 kpts fine 32×32×24
 qppts 4×4×3
 λ 1.209
 ω_{log} 379 K
 ω₂ 767 K
 T_c^{Mcmillan} 34.2 K
 T_c^{Allen-Dynes} 37.9 K
 T_c^{Eliashberg} 40.8 K


Primitive structure:

a: 4.3844 Å, *b*: 4.3844 Å, *c*: 5.8941 Å
 α: 90.00°, β: 90.00°, γ: 120.00°

Rb [0.0000, 0.0000, 0.0000]
 Be [0.3333, 0.5000, 0.5000]
 H [0.3922, 0.3300, 0.3300]
 H [0.3922, 0.6700, 0.6700]
 H [0.0049, 0.6700, 0.6700]
 H [0.6029, 0.6700, 0.6700]
 H [0.0049, 0.3300, 0.3300]
 H [0.6029, 0.3300, 0.3300]
 Pt [0.6667, 0.5000, 0.5000]

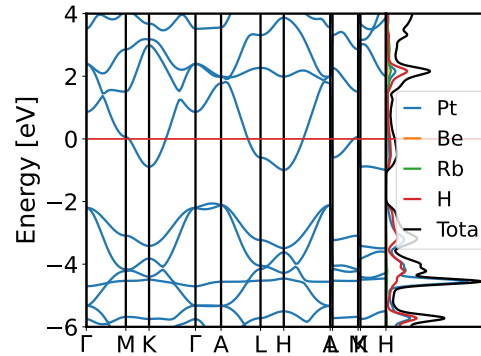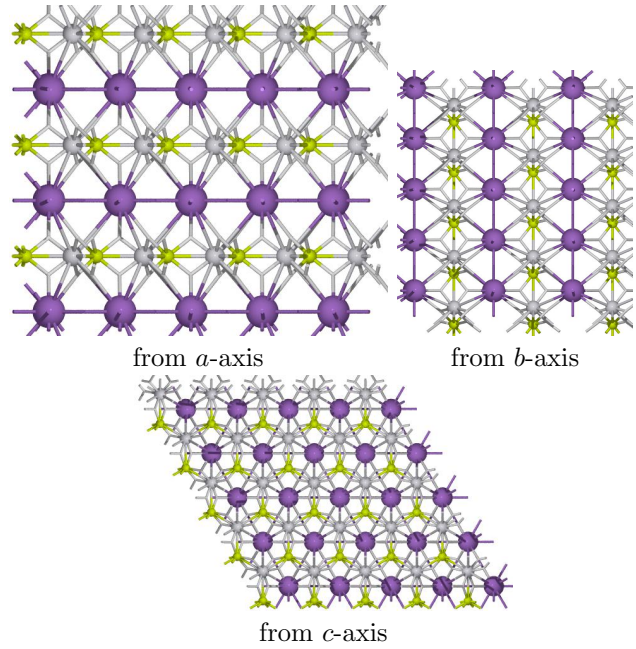


Electron band structure

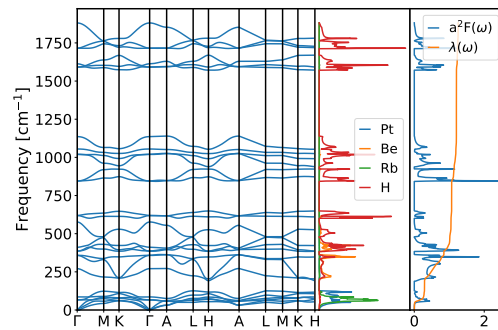

Phonon band structure

#56: CsBeH₆Pt


mat id agm005096309
 spg 149
 nsites 9
 e above hull 0.130 eV
 e form -0.205 eV
 decomposition Be₂Pt,Cs₂H₆Pt,H₂
 ecutwfc 118.0 Ry
 kpts coarse 16×16×12
 kpts fine 32×32×24
 qppts 4×4×3
 λ 1.066
 ω_{log} 370 K
 ω₂ 787 K
 T_c^{McMillan} 28.4 K
 T_c^{Allen-Dynes} 30.9 K
 T_c^{Eliashberg} 33.6 K

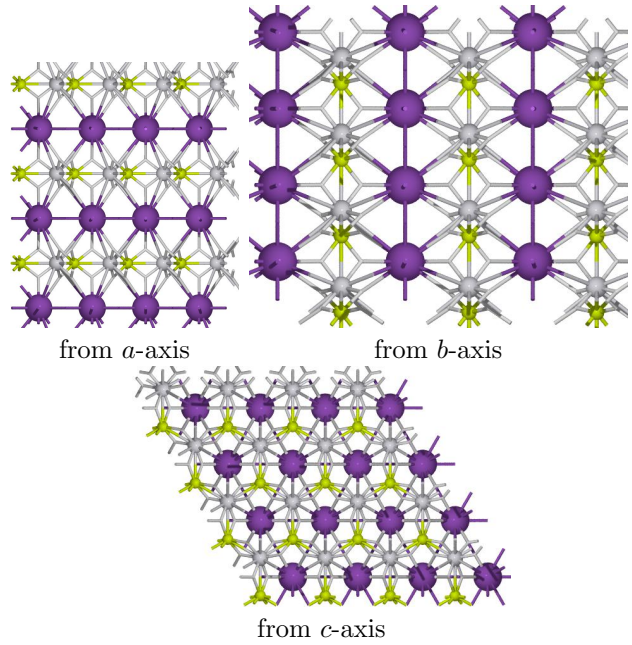


Primitive structure:

a: 4.3744 Å, *b*: 4.3744 Å, *c*: 6.3116 Å
 α: 90.00°, β: 90.00°, γ: 120.00°

Cs [0.0000, 0.0000, 0.0000]
 Be [0.3333, 0.5000, 0.5000]
 H [0.3886, 0.3415, 0.3415]
 H [0.3886, 0.6585, 0.6585]
 H [0.0037, 0.6585, 0.6585]
 H [0.6077, 0.6585, 0.6585]
 H [0.0037, 0.3415, 0.3415]
 H [0.6077, 0.3415, 0.3415]
 Pt [0.6667, 0.5000, 0.5000]

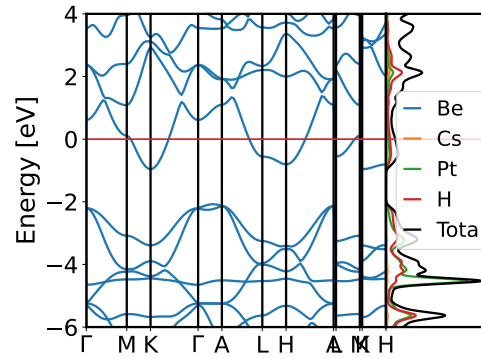

Electron band structure

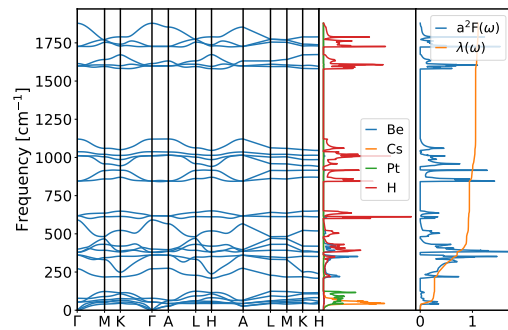


Phonon band structure

#57: $\text{Li}_2\text{GaCuH}_6$

```

mat id agm004959278
spg 146
nsites 10
e above hull 0.133 eV
e form -0.076 eV
decomposition GaCu2H2LiH
ecutwfc 122.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qpts 3×3×3
λ 0.974
ωlog 527 K
ω2 891 K
TcMcmillan 35.2 K
TcAllen-Dynes 37.9 K
TcEliashberg 39.9 K

```

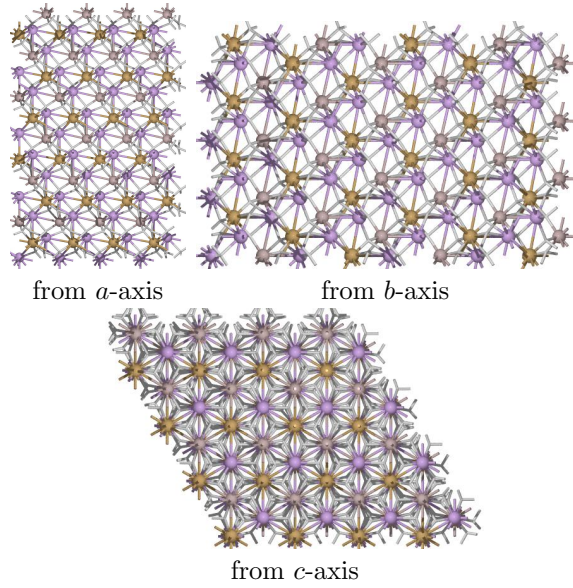


Primitive structure:

a: 4.9930 Å, *b*: 4.9930 Å, *c*: 4.9930 Å
 α : 56.65°, β : 56.65°, γ : 56.65°


```

Li [0.5280, 0.5280, 0.5280]
Li [0.0349, 0.0349, 0.0349]
Ga [0.3174, 0.3174, 0.3174]
Cu [0.8187, 0.8187, 0.8187]
H [0.5904, 0.1649, 0.1649]
H [0.1649, 0.9715, 0.9715]
H [0.9715, 0.5904, 0.5904]
H [0.4771, 0.6783, 0.6783]
H [0.6783, 0.0818, 0.0818]
H [0.0818, 0.4771, 0.4771]

```

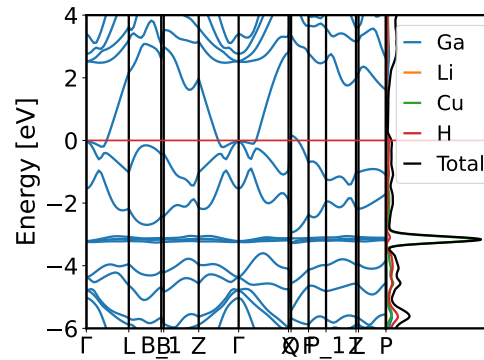

Electron band structure

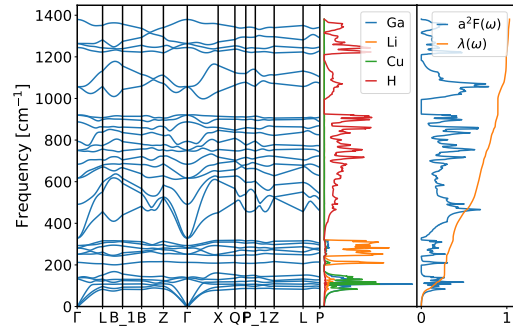


Phonon band structure

#58: K_2CdAgH_6

```

mat id agm004928433
spg 139
nsites 10
e above hull 0.075 eV
e form -0.063 eV
decomposition  $\text{K}_2\text{CdH}_4, \text{H}_2, \text{Ag}$ 
ecutwfc 132.0 Ry
kpts coarse  $12 \times 12 \times 12$ 
kpts fine  $24 \times 24 \times 24$ 
qppts  $3 \times 3 \times 3$ 
lambda 0.922
omega_log 422 K
omega_2 775 K
T_c^McMillan 25.7 K
T_c^Allen-Dynes 27.5 K
T_c^Eliashberg 29.3 K

```

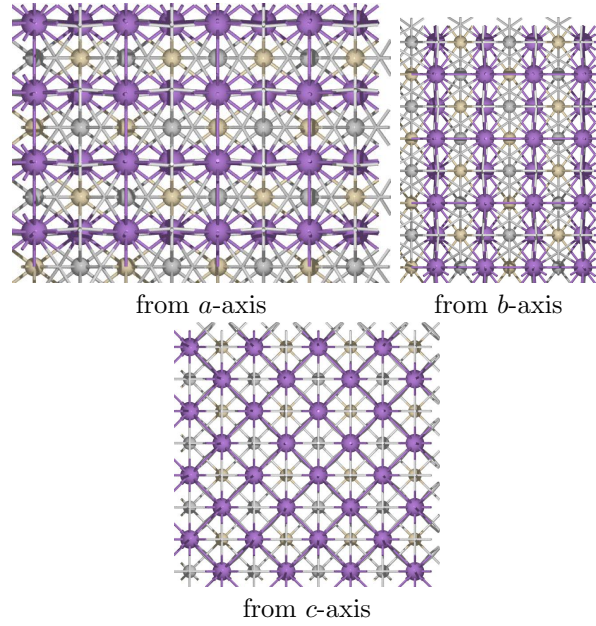


Primitive structure:

a : 5.5994 Å, b : 5.5994 Å, c : 5.5994 Å
 α : 120.61°, β : 120.61°, γ : 88.94°


```

K [0.7500, 0.5000, 0.5000]
K [0.2500, 0.5000, 0.5000]
Cd [0.0000, 0.0000, 0.0000]
Ag [0.5000, 0.0000, 0.0000]
H [0.7591, 0.0000, 0.0000]
H [0.7343, 0.4686, 0.4686]
H [0.7343, 1.0000, 1.0000]
H [0.2657, 0.0000, 0.0000]
H [0.2657, 0.5314, 0.5314]
H [0.2409, 0.0000, 0.0000]

```

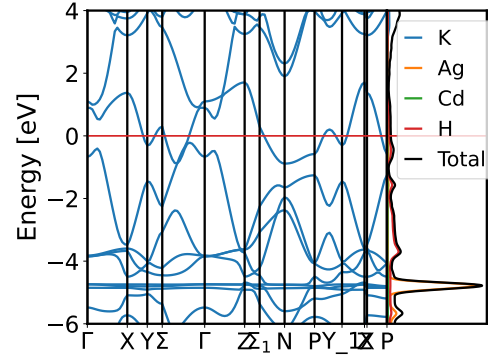

Electron band structure

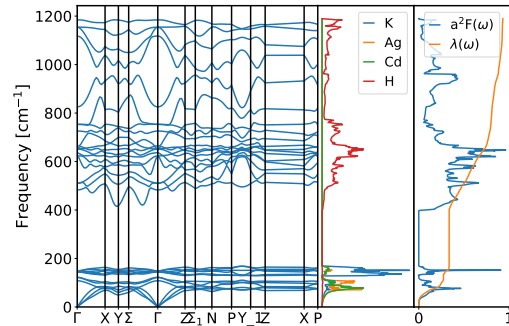


Phonon band structure

#59: Na₂H₆IrPd

```

mat id agm004930563
spg 164
nsites 10
e above hull 0.093 eV
e form -0.246 eV
decomposition Na2H7Ir,HPd,Na3H6Ir,Ir
ecutwfc 98.0 Ry
kpts coarse 12×12×12
kpts fine 24×24×24
qpts 3×3×3
λ 0.816
ωlog 456 K
ω2 736 K
TcMcMillan 22.2 K
TcAllen-Dynes 23.5 K
TcEliashberg 25.7 K

```

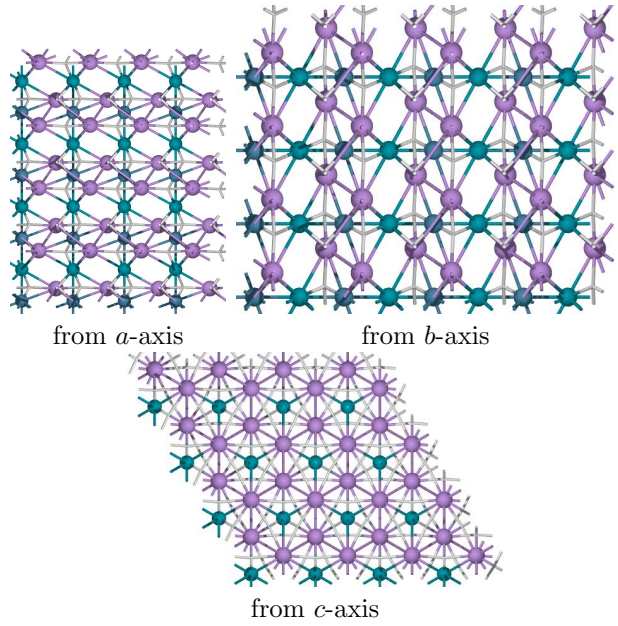


Primitive structure:

a: 4.9413 Å, *b*: 4.9413 Å, *c*: 5.2361 Å
 α : 90.00°, β : 90.00°, γ : 120.00°


```

Na [0.3333, 0.2036, 0.2036]
Na [0.6667, 0.7964, 0.7964]
H [0.1462, 0.7741, 0.7741]
H [0.1462, 0.7741, 0.7741]
H [0.7076, 0.7741, 0.7741]
H [0.8538, 0.2259, 0.2259]
H [0.2924, 0.2259, 0.2259]
H [0.8538, 0.2259, 0.2259]
Ir [0.0000, 0.0000, 0.0000]
Pd [0.0000, 0.5000, 0.5000]

```

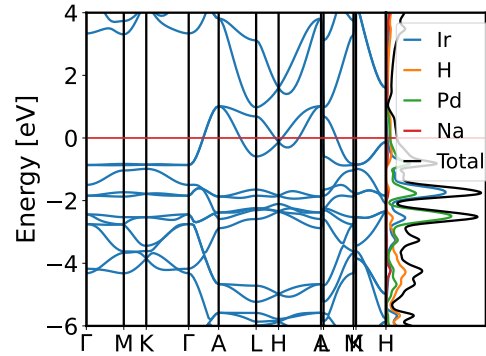

Electron band structure

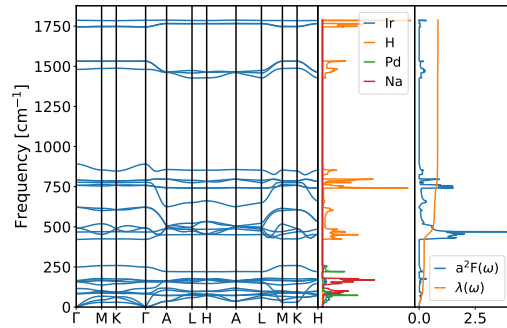

Phonon band structure